



FINNISH ROAD  
ADMINISTRATION



Pentti Lahtinen

# Fly Ash Mixtures as Flexible Structural Materials for Low-Volume Roads

Finnra Reports 70/2001

## Fly Ash

Depth profile mid-0.7 m

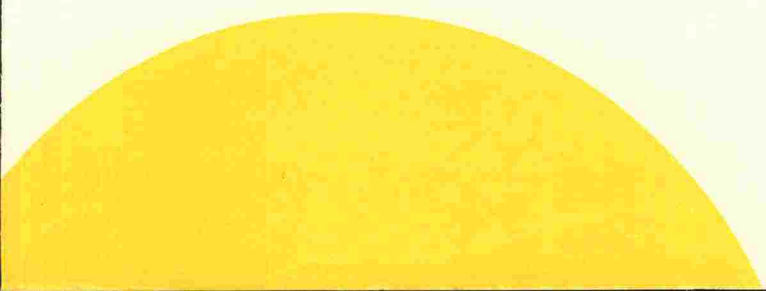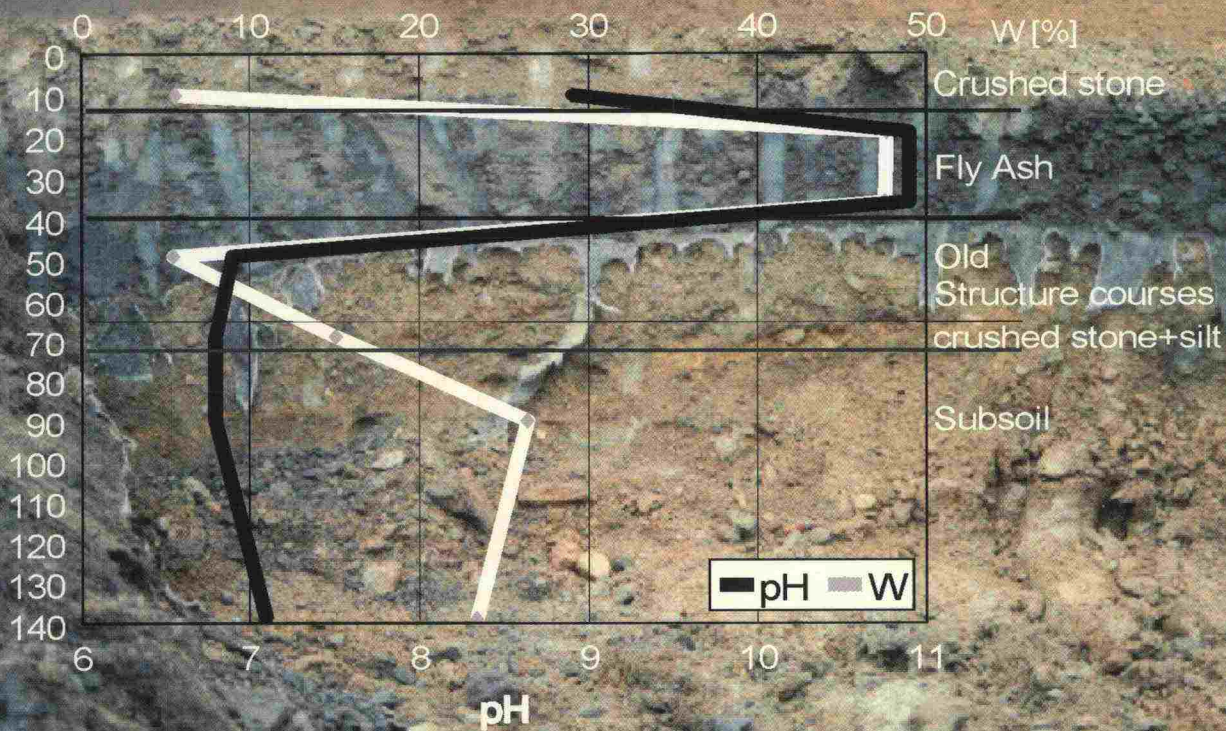

VIATEK  
SGT

Pentti Lahtinen

# **Fly Ash Mixtures as Flexible Structural Materials for Low-Volume Roads**

**Finnra Reports 70/2001**

**Doctoral Thesis of Pentti Lahtinen**

Helsinki University of Technology  
Department of Civil and Environmental Engineering

Finnish Road Administration  
Helsinki 2001



ISSN 1457-9871  
ISBN 951-726-826-2  
TIEH 3200716E

Edita Oyj  
Helsinki 2001

This Publication is available at Finnra Publications Sales  
telefax int. +358 (0)204 22 2652  
e-mail [julkaisumyynti@tiehallinto.fi](mailto:julkaisumyynti@tiehallinto.fi)  
[www.tiehallinto.fi/julk2.htm](http://www.tiehallinto.fi/julk2.htm)

Finnish Road Administration  
Opastinsilta 12 A  
P.O.Box 33  
FIN-00521 HELSINKI  
Tel. int. +358 (0)204 22 11

SCC Viatek Oy SGT  
Vohlisaarentie 2  
FIN-36760 LUOPIOINEN  
Tel. int. +358 3 524 3200  
Telefax +358 3 524 3222  
e-mail: [pentti.lahtinen@viatek.fi](mailto:pentti.lahtinen@viatek.fi)

**Pentti Lahtinen: Lentotuhkapohjaiset seokset alempiasteisten teiden elastisena rakennemateriaalina.** [Fly Ash Mixtures as Flexible Structural Materials For Low-Volume Roads]. Helsinki 2001. Tiehallinto, Uudenmaan tiepiiri. Finnra Reports 70/2001. 95 s. + liitt. 55 s. ISSN 1457-9871, ISBN 951-726-826-2, TIEH 3200716E..

**Asiasanat:** uudelleenkäyttö, jätteet, sivutuotteet, tierakennusaineet, tierakenteet, rakentaminen, geotekniikka, ympäristövaikutukset, alempiasteiset tiet, soratiet, lentotuhka

**Aiheluokka:** 55

## TIIVISTELMÄ

Suomessa tehtiin 1990-luvulla tehtiin lukuisia tutkimuksia teollisuuden sivutuotteiden maarakennushyötykäytöstä teollisuudelle, tielaitokselle ja kunnille. Pääosa tutkimuksista tehtiin SCC Viatek Oy SGT:n laboratoriossa yhteistyössä julkisten tutkimuslaitosten kanssa. Tämä väitöskirja keskittyy Suomessa syntyvien tuhkien ja niiden seosten maarakennushyötykäyttöön. Tuhkat ovat peräisin kivihiilen ja biopolttoaineiden poltosta ja niistä on tehty seoksia erilaisten muiden teollisuuden sivutuotteiden kanssa.

Tutkimusten yhteydessä on kehitetty uusia NRC-materiaaleja (NRC on lyhennelmä sanoista New Recycling Construction) ja -rakennesovellutuksia alempiasteisille teille. Samassa yhteydessä on kehitetty ja testattu sekä laitteita että työmenetelmiä NRC-rakenteiden tekemiseksi. NRC-materiaaleja, -rakennesovellutuksia, laitteistoja ja työmenetelmiä, ts. NRC-teknologiaa on testattu yhteensä 33 koerakenteessa. Materiaalien sekoitus osoittautui erittäin tärkeäksi tekijäksi NRC-teknologian onnistumisen kannalta. Tutkimusprojektien yhteydessä onnistuttiinkin löytämään useita hyvin soveltuvia menetelmiä ja laitteistoja tähän tarkoitukseen.

Väitöskirjaan liittyvissä tutkimuksissa kehitettiin uusia lentotuhkapohjaisia materiaaleja, kuten; a) rakennekerrosmateriaaleja eri tyyppisistä tuhista, kuitu-tuhista, kipsi-tuhkasta ja kuona-tuhkasta, b) vanhan rakenteen stabilointiin soveltuvia lentotuhkapohjaisia sideaineseoksia, ja c) pehmeiden maiden, kuten turve-, lieju- ja savi-maiden, massa- ja pilaristabilointiin soveltuvia lentotuhkapohjaisia sideaineseoksia. Nämä tutkimukset osoittavat, että biopolton tuhkat, joiden maarakennushyötykäyttöä on aiemmin tutkittu varsin vähän, ovat teknisesti ja ympäristöllisesti osittain jopa parempia kuin kivihiilen polton tuhkat. Tutkimuksilla on voitu osoittaa, että tuhkillä voidaan usein korvata perinteisiä sideaineita kerros-, pilari- ja massastabiloinnissa. Tämän lisäksi on onnistuttu kehittämään aivan uusia materiaaleja sekoittamalla tuhkiin kuitulietettä, prosessikipsiä tai terässulattokuonaa. Näiden seoksien ominaisuuksia voidaan muuttaa eri materiaalien seossuhteita muuttamalla. Alempiasteisilla teillä korostuvat lämmöneristävyys, muodonmuutoskestävyys ja kantavuus. Erityisesti kuitutuhkaseokset ovat myötölujuunevia ja omaavat suuren muodonmuutoskestävyyden, mikä tekee ne lähes rikkoutumattomiksi.

NRC-materiaalien tutkimus- ja testausmenetelmät ovat kehittyneet tutkimuksen aikana. Tutkimuksissa on mm. pitkäaikaiskestävyyden tutkimukseen soveltuvia testaustapoja ja arviointikriteerejä. Tutkimuksien yhteydessä on voitu osoittaa, että NRC-materiaalien pitkäaikaiskestävyys on tutkittava erityisesti routa- ja jäätymsulamiskokeiden avulla. Pelkästään lujuus-muodonmuutos -tutkimuksilla ei vielä voida tehdä johtopäätöksiä materiaalien pitkäaikaiskestävyydestä.

Myös NRC-materiaalien ympäristökelpoisuutta on tutkittu sekä laboratoriossa että koerakenteissa. Useat pitkäaikaisliukoisuustestit antavat varmuutta näiden materiaalien erittäin vähäisestä riskistä ympäristölle. Tuhkien molybdeenin on aiheuttanut paljon keskustelua, minkä vuoksi molybdeenin liukenemista ja kulkeutumista tyyppirakenteissa on tutkittu dynaamisen kulkeutumismallin avulla. Tutkimus osoitti, että molybdeenista aiheutuva riski on erittäin vähäinen, ja että ko. mallia voisi soveltaa myös muiden aineiden kulkeutumisen tutkimiseen.



Tutkimusten perusteella on voitu osoittaa, että tuhkaan pohjautuvilla NRC-materiaaleilla voidaan rakentaa teknisesti hyvin toimivia ja perinteisiin kiviainesrakenteisiin verrattuna selvästi kestävämpiä rakenteita. NRC-teknologialla on saavutettavissa myös oleellista taloudellista säästöä, kun otetaan huomioon rakenteiden koko elinkaari. Lisäksi NRC-teknologia on osoittautunut kestävä kehityksen mukaiseksi menetelmäksi, sillä tutkittuja materiaaleja käyttämällä voitaisiin säästää jopa 24 % uusiutumattomista sora- ym. luonnonvaroja. Samalla vähenee tarve teollisuuden kaatopaikkoihin sekä soranottoon aroilla pohjavesialueilla.

**Pentti Lahtinen: Inblandningar av flygaska som flexibla gravelvägars strukturer.** Helsinki 2001. Vägförvaltningen, Nylands vägdistrikt. Finnra Reports 70/2001. 95 s. + bilagor 55 s. ISSN 1457-9871, ISBN 951-726-826-2, TIEH 3200716E.

**Nyckelord:** Återvinning, avfall, biprodukter, vägbyggmaterial, vägkonstruktioner, vägbyggnad, geoteknik, miljökonsekvenser, tillämpningar, gravelvägar

## SAMMANFATTNING

På 1990-talet genomfördes flera undersökningar på användningen av industriella restprodukter i jordbyggandet. De mesta av dessa undersökningar gjordes av SCC Viatek Oy tillsammans med industrin, vägverket och kommuner. Denna doktorsavhandling fokuserar på de mångsidiga möjligheter att använda askor och deras inblandningar som jordbyggnadsmaterial. Askor kommer från brännandet av kol och biobränsle, och de har inblandats med olika andra industriella restprodukter. Det huvudsakliga syftet är att bevisa på vilka villkor olika NRC-material är åtminstone lika bra, t.o.m. bättre än naturligt sten material för grusvägarnas strukturlager (NRC = förkortning av ord New Recycling Construction).

I samband med undersökningarna har vi utvecklat nya NRC-material och strukturtyper för grusvägar. Därmed har man utvecklat, applicerat och testat både verktyg, maskiner och arbetsmetoder för byggandet av NRC-strukturer. NRC-teknologi med flygaska har testats tillsammans i 33 testbyggnader. En lyckad NRC-tillämpning är särskilt beroende på den inblandningsmetod som används. I samband med olika forskningsprojekt har man lyckats att finna flera passande metoder och maskiner för inblandningen.

I undersökningarna för min avhandling har man utvecklat nya material baserade på flygaskor, liksom a) askor, fiberaskor, gipsaskor och slaggaskor som byggnadsmaterial för olika strukturlager, b) bindemedel med flygaskor för stabiliseringen av gamla grusvägsstrukturer och c) bindemedel med flygaskor för mass- och pelarestabiliseringen av mjuka jordtyper liksom torv, lera och gyttja. Dessa undersökningar har givit prov på, att bioaskor, som tills vidare har undersökts endast i liten grad, är på tekniska och miljö grunder delvis t.o.m. bättre än kolaskor. Därtill har man bevisat, att askor kan ofta kompensera traditionella bindemedel för mass- och pelarestabiliseringen. Man har också lyckats att utveckla alldeles nya material genom att inblanda askor med fiberslam, processgips eller stålsmältningsslagg. Egenskaper av dessa inblandningar kan man modifiera med olika inblandningsproportioner. För grusvägar understryks sådana egenskaper som värmeisoleringsförmåga, deformationsbeständighet och bärförmåga. Fiberaskornas relativt stor deformationsbeständighet innebär, att dessa är nästan obruten.

Undersöknings- och testmetoder för NRC-material har också utvecklats under olika FoU-projekt. Detta gäller lämpliga metoder att optimera materialegenskaper samt testmetoder och kriterier för att bestämma materialens långtidsbeständighet. Det har varit möjligt att bevisa, att långtidsbeständigheten av NRC-material skulle undersökas med tester på tjal- och frysning-smältningsbeständigheten. Spänning-deformationstester är inte tillräckliga för detta ändamål.

Även NRC-materialens miljöduglighet har undersökts både i laboratoriet och med fälttester. Resultat av tester på den långtidiga lakningen övertygar, att dessa material inte innebär någon miljörisk. Askorna innehåller t.ex. molybdenium, vilkas miljöskadlighet har mycket diskuterats i Finland. Därför har man undersökt molybdeniums lakning och transport från vägens strukturlager till omgivningen med en dynamisk transportsmodell. Enligt resultat är molybdenium en mycket liten risk för miljön. Transportsmodellen kan användas för dylika undersökningar också på andra element.



På grund av undersökningarna har vi blivit övertygade, att NRC-material kan användas för att bygga tekniskt funktionella och beständiga vägstrukturer i jämförelse med de traditionella grusvägsstrukturer. NRC-teknologin är också ekonomiskt konkurrensduglig på grund av de besparingar, som kan vinnas under en grusvägs hela livscykel. Därtill är NRC-teknologin en hållbar jordbyggnadsmetod, då genom att utnyttja de undersökta materialtyper är det möjligt att spara t.o.m. 24 % av oersättliga naturtillgångar som grus och annat stenmaterial, och behovet av deponier samt grustäcker på känsliga grundvattenområden blir mindre.

**Pentti Lahtinen: Fly Ash Mixtures as Flexible Structure Materials for Low-Volume Roads.** Helsinki 2001. Finnish Road Administration, Uusimaa Region. Finnra Reports 70/2001. 95 p. + app. 55 p. ISSN 0788-3722, ISBN 951-726-826-2, TIEH 3200716E.

**Keywords:** recycling, waste, residues, by-products, road materials, road structures, applications, construction, geotechnics, environmental effects, low-volume roads, gravel roads, fly ash

## SUMMARY

Extensive research and several studies have been carried out on the recycling of industrial by-products in soil construction in Finland in the 1990's. The research and studies have been made mainly in the laboratory of SCC Viatek Ltd SGT in cooperation with the public research institutes. The main beneficiaries have been the industry, the national road administration and the municipalities.

The Doctoral Thesis focuses on the versatile usage opportunities of the fly ashes (FA) from the combustion of coal and biofuel like peat and wood and their mixtures with certain other industrial by-products in soil construction. The main objective of this thesis is to show the conditions and premises on which the NRC (New Recycled Construction) -materials are at least as viable or even more viable than the natural stone materials in the applications for low-volume roads. The research and studies have succeeded in the development of new materials and structure applications for low-volume roads, proper equipment and work methods to manufacture the NRC-structures and proper test methods for the quality assurance of the materials.

The new FA-based construction materials include; a) materials based on FA, fibre-ashes, gypsum-ashes and slag-ashes for NRC-solid structures; b) binder admixtures based on FA for the stabilisation of old road structure courses; c) binder admixtures based on FA for the mass-column stabilisation of soft soil. It has been shown that FA from biofuel that have been studied relatively little so far may have even better geotechnical properties than the FA from coal. Additionally it has been possible to attain a versatile array of materials by mixing the FA with fibre sludge (outcome: fibre-ashes), process gypsum (outcome: gypsum-ashes) or stainless steel slag (outcome: slag-ashes). The properties of the different mixtures can be regulated by changing the proportion of different components. Thus, it has been possible to find proper materials for low-volume roads that require high heat insulation, deformation durability and bearing capacity.

The studies on the test methods have been focused on the methods and criteria to optimise the properties and to assess the long-term durability of the NRC-materials. It has been possible to show that the most important methods to assess the long-term durability are the tests for frost susceptibility and the freeze-thaw durability. It is not possible to judge the long-term durability of NRC-materials with the mere stress-strain tests. Also the environmental impact of the NRC-materials has been studied both in the laboratory by leaching tests and in the full-scale test structures with samples of soil and groundwater. The studies include also the use of a mathematical dynamic transportation model to predict the distribution of molybdenum from the coal ash structures to the environment surrounding the structures. The environmental studies indicate that there is no environmental risk involved in the use of FA-based materials in soil construction, assuming that the materials are used in a proper way.

NRC-technology will make the sustainable road construction possible. The durable NRC-structures will be economically viable alternatives to the conventional stone structures. Additionally it will be possible to save even 24 % of the non-renewable gravel and other natural resources, and there will be less need to use land for deposits or for stone intake at sensitive groundwater areas.



## LIST OF PAPERS

This thesis is based on the following papers, which are being referred to in the text by roman numerals:

- I Lahtinen, P., Jyrävä, H., Suni, H. (1999): **New methods for the renovation of gravel roads.** Paper for IRF Regional Conference, European Transport and Roads, Lahti 24-26. May 1999. 8 pages.
- II Lahtinen, P., Fagerhed, J.A., Ronkainen, M. (1998): **Paper Sludge in Road Construction.** Paper for the Proceedings of the 4<sup>th</sup> International Symposium on Environmental Geotechnology and Global Sustainable Development, 9. - 13. August 1998, Boston (Danvers). University of Massachusetts, Lowell, pp. 410-419. 9 pages.
- III Lahtinen, P., Jyrävä, H., Kuusipuro, K. (2000): **Deep Stabilisation of Organic Soft Soils.** Paper for the Proceedings of the Grouting Soil Improvement Geosystems including Reinforcement of the 4<sup>th</sup> GIGS, the International Conference on Ground Improvement Geosystems, by the Finnish Geotechnical Society in Helsinki, 7-9. June 2000, pp. 89-98. 10 pages.
- IV Lahtinen, P., Jyrävä, H., Suni, H. (2000): **New Methods for the Renovation of Gravel Roads.** Paper for the Proceedings of the NGM-2000, XIII Nordiska Geoteknikermötet, Helsinki 5. - 7. Juni 2000. Building Information Ltd., Helsinki, pp. 531-538. 8 pages.
- V Lahtinen, P., Jyrävä, H., Suni, H. (2000): **Use of Industrial Wastes in the Construction of Low-Volume Roads.** Paper for the conference of Geo-Denver 2000, 5. - 8. August 2000. Proceedings pending. 11 pages.
- VI Lahtinen, P., Palko, J., Karvonen, T. (2000): **Molybdenum transport in coal fly ash soil constructions.** Paper for Ecogeo-2000, International Conference on Practical Applications in Environmental Geotechnology, Helsinki 4. - 6. September 2000. Proceedings pending. 7 pages.

## ACKNOWLEDGEMENTS

My thesis is based on 12 years' research and development work, most of it in the geotechnical laboratory SGT of SCC Viatek Oy, and on the full-scale field tests of 33 different structures at different sites in Finland. Therefore, I am grateful to many people for assisting me, in several ways, during the work with the thesis.

First of all I would like to express my gratitude to SCC Viatek Oy, and especially to Jaakko Heikkilä, the managing director, and Mikko Leppänen, the director of geotechnics, for their support and encouragement to produce this thesis. Also, I would like to thank the personnel of SGT for their impact on the work; to Aino Maijala who has helped me to collect and edit the research material; to M.Sc. Harri Jyrävä with whom I have created ideas and developed many of the innovations for the work; to Marjo Ronkainen, Tero Jokinen, Elina Ahlqvist, and Marjatta Jaakkola for their important work and studies carried out in the laboratory and at the field test sites; and to Ms. Terttu Salmela for her help in editing this thesis for its publication.

I would also like to thank the active and innovative personnel of developers and industry without which the research work would not have been possible, especially and amongst many others:

- Finnish Road Administration
- Finnish Road Enterprise
- Helsinki City
- Luopioinen municipality
- Georgia Pacific Finland Oy
- UPM-Kymmene Oy
- Stora Enso Oy
- Finncao Oy
- Partek Nordkalk Oy Ab
- Fortum Heat and Power Oy
- Helsinki Energy
- Pohjolan Voima, PVO
- Avesta Polarit Oy
- Kemira Phosphates Oy, Kemira Chemicals Oy and Kemira Pigments Oy

Further, I would like to thank my supervisor Professor Olli Ravaska and the examiners of my thesis, Professor Thomas Zimmie and Dr. Masaaki Terashi for their advice and guidance to accomplish this thesis.

Finally, warm thanks to my dear wife Elisa for all her support and encouragement over these years, that made it possible for me to spend so much of my time for this thesis.

I hope that all this work will have practical impact to increase the exploitation of the sustainable NRC-technology for the saving of our most valuable natural resources.

I am very grateful to Finnish Road Administration, Uusimaa Region and Pekka Kontiala for making it possible to publish this thesis.

Luopioinen 8.11.2001

Pentti Lahtinen



## LIST OF SYMBOLS AND ABBREVIATIONS

5(F+L, 1:1) or 5(FL, 1:1)	Example of notation: Abbreviation for "5 % of an admixture of components F and lime. The proportion of the components is 1:1 in the admixture". Normally given in relation to the dry mass of the basic NRC-material
5Ce	Example of notation: Abbreviation for "5 % cement". Normally given in relation to the dry mass of the basic NRC-material
C or Ce	Cement in general
CaO or L	Lime
CC	Calcium chloride, $\text{CaCl}_2$ ; salt
D	Relative compaction; relative to the maximum Proctor density of the material [%]
dry FA	FA taken directly from the dust filters, from a silo or from another dry storage
F	Finnstabi® ; by-product gypsum from the production of $\text{TiO}_2$
FA	Fly ash, in general. The specific types of fly ash are expressed according to the type of fuel in the combustion: CFA = Coal fly ash MFA = Miscellaneous fly ash, i.e. fly ash from the combustion of mixed fuel like fibre sludge and wood PFA = Peat fly ash WFA = Wood fly ash
FGD or D	Flue gas desulphurization residue
FS	Fibre sludge
FW	Filterwaste or -cake from the production of CC
LoI	Loss of incineration [%]
M	Blast-furnace slag
n/a	not available data or information
NRC	i.e. "New Recycled Construction"; an abbreviation for "New construction based on recycled materials" (NRC materials, structures, construction, technology)
PG or G	Phosphogypsum
pile-FA	FA taken from an open-air storage (a pile, a lagoon), usually moist
S	Stainless steel slag
SGT	Geotechnical R&D unit of SCC Viatek Oy Ltd, the employer of the author, in Finland
SP <sub>o</sub>	Segregation potential [ $\text{mm}^2/\text{Kh}$ ]
T or THK2	Hydrated lime ( $\text{Ca}(\text{OH})_2$ ) or secondary hydrated lime with at least 50 % $\text{Ca}(\text{OH})_2$
UCS	Unconfined compression strength
w	water content [%]; geotechnical
w <sub>o</sub>	water content, optimum [%]

## Table of Contents

TIIVISTELMÄ  
SAMMANFATTNING  
SUMMARY  
LIST OF PAPERS  
ACKNOWLEDGEMENTS  
LIST OF SYMBOLS AND ABBREVIATIONS

1	INTRODUCTION	15
2	LITERATURE REVIEW	17
3	RESEARCH PHILOSOPHY AND METHODOLOGY	20
3.1	NRC-structures	20
3.2	Upgrading material properties	21
3.2.1	Proportion of components in the material mixes	21
3.2.2	Stabilisation	22
3.2.3	Storage	22
3.2.4	Mixing and compaction	23
3.3	Criteria and acceptability tests on materials	25
3.3.1	Criteria on materials	25
3.3.2	Testing of materials	26
4	MATERIALS AND APPLICATIONS	32
4.1	Fly Ashes (FA)	32
4.2	Improvement of FA properties with binders	37
	FA mixtures with other industrial residues	41
4.3.1	Fibre-ash	42
4.3.2	Gypsum-ash	43
4.3.3	Slag-ash	44
4.4	FA as binder	48
4.4.1	Stabilisation of soft soil	48
4.4.2	Stabilisation of old road structures	51
4.5	Long-term stability of materials	54
4.5.1	Water resistance, frost resistance and freeze-thaw durability	54
4.5.2	Frost susceptibility	58
4.5.3	Biodegradability	58
4.6	Environmental impacts	59
5	FULL-SCALE TESTS ON NRC-STRUCTURES	60
5.1	Different types of NRC-structures	60
5.2	Test sites	62

---

5.3	Tests on recycled structures	63
5.4	Storage, equipment and work methods	64
5.5	Follow-up studies	73
6	EVALUATION OF NRC-TECHNOLOGY	80
6.1	Life Cycle	80
6.2	Economic and Environmental Benefits	81
6.3	Environmental Impact	85
7	CONCLUSIONS AND FURTHER RESEARCH	87
7.1	In General	87
7.2	NRC-materials	87
7.3	Laboratory Tests	88
7.4	Environmental Acceptability	89
7.5	NRC-structures and -construction	89
7.6	Further Research	90
	REFERENCES	92
	APPENDICES	95

---



## 1 INTRODUCTION

Fly ashes (FA) are being quite widely utilised in many countries. However, a significant part of these materials are still not recycled or are being deposited into landfills. Cement and concrete industries are the biggest users of FA having established standards for their use. Also in soil construction applications FA have significant usage potential but the efforts to develop other FA than CFA into construction materials have been minor and incomplete, to date. However, there are large soil construction markets for FA everywhere where the materials are being produced.

It has been found that it is possible to develop many new types of geotechnical applications based on FA with or without other industrial residues. However, every new type of material or application needs extensive technical and environmental studies, first at the laboratory level and finally at full scale. Expensive geotechnical instrumentation and long-term follow-up measurements at field test sites are required for the assurance of the technical and environmental acceptability of the new application.

The research for the doctoral thesis concentrated on FA from coal, peat, wood and mixed fuel combustion. Mixed fuels also include different types of sludge from the paper industry. The average annual production of FA in Finland is about 1,2 million tonnes (the annual variation of the production is relatively large).

The following FA applications have been studied for this research:

- FA as bearing and insulating courses in road construction [I, IV, V] [15]
- Mixtures of FA and paper sludge as bearing and insulating courses [II, V] [15]
- Mixtures of phospho-gypsum and FA as soil construction material [15]
- New FA-based binders for the stabilisation of low-volume roads [I, IV, V]
- New FA-based binders for soft soil stabilisation [III], [5]
- Mixtures of FA and stainless steel slag in road construction [15]
- Mixtures of FA and desulphurization residues (FGD) for geotechnical applications [5, 6, 15]

It is also necessary to study the total economical and environmental benefits of the new types of applications based on the use of FA in order to ascertain their advantages. The calculations have shown that the life-cycle costs of FA constructions will be about 30 % less than the life-cycle costs of competing (conventional) methods, even without considering the effect of residue taxes (I, IV, V). There are also factors that cannot easily be determined with any monetary value, like the savings of non-renewable natural resources and landscape, as FA compensate for natural stone materials. For example, gravel pits are normally situated in important groundwater areas, and the excavation of these pits involves grave risks to the groundwater. Recycling of FA and FA-mixes in soil construction would reduce the use of stone materials by about 20-30 % of the total annual amount needed for conventional soil construction at present. In individual cases the savings of stone materials could be even larger, 50-70 %.

Another important question is the total environmental impact of the FA applications in the long term. With environmental dynamic modelling it has been possible to show that FA applications are really minor risks to the environment. The dynamic modelling is a mathematical method that calculates the transport of critical substances from a construction course to the environment, by combining the results of long-term leaching tests of FA materials and the data on the properties of the surrounding soil material. [VI]. Also many full-scale test structures that have utilised soil and water sampling and analyses for many years have proved that FA applications are environmentally safe [15].

## 2 LITERATURE REVIEW

The utilisation of coal fly ash (CFA) in soil construction applications has been studied in many countries in Europe, Asia and North America. Many of the road construction applications have been based on stabilised or self-cementing CFA of different strength levels, and on different granulated ashes. [7]. CFA has been applied in all parts of road structures, from the embankment to the pavement. For example, in Indiana in the United States they have developed highway embankment materials based on a mixture of CFA of Class F and bottom ash. [4]. The applications of the basecourses have mainly been

- a. stabilised, rigid CFA structures having high strength
- b. with or without activator stabilised half-rigid CFA structures
- c. stabilised old structural layers where reactive CFA have been used as binders or as components of a binder admixture

Bergeson and Barnes [35] reported that in rigid structures the unconfined compressive strength of the CFA basecourse was more than 5,6 MPa and in half-rigid structures the strength was 1,4 – 4,5 MPa.

Outside Finland there are only a few published studies on the soil construction utilisation of FA from the combustion of biofuels like peat and wood. However, these materials are equal and sometimes even better than CFA in their usage potential in soil construction applications. Another range of soil construction applications of relatively scarce research is the use of FA together with other industrial waste materials. There are some studies (unpublished studies of the European phosphate industry) on the upgrading of phospho-gypsum with FA, and several other studies on the use of FA mixed with desulphurization residues [8]. The use of steel melting slags in soil construction has been researched in the Ukraine [34]. However, mixtures of FA with different fibre sludges from the paper industry appear to have been studied only in Finland [15].

It has been proven that FA are adequate binder components for the stabilisation of soft soils. For this use FA have been studied and developed both in Japan [14] and in Finland [5] [III].

The properties of FA depend on the type of fuel and on the combustion technology. Therefore the properties of a certain FA may significantly differ from the properties of a FA from another source. In the United States the FA are being categorised into classes C and F. C-ashes are self-cementing and pozzolanic and contain more free lime (CaO) than F-ashes. The F-ashes are also pozzolanic and able to gain significant strength with the help of activators [9,10]. Based on the former categorisation most of the Finnish FA are F-ashes. The F-ashes primarily result from the burning of anthracite or bituminous coals, and the C-ashes from the burning of lignite or sub-bituminous coals. [4]. The Canadian Standards Association specification for FA (CSA A23.5) classifies FA according to the calcium content (CaO-content); low-calcium FA having less than 8 % CaO, medium class having 8-20 % CaO and high-calcium class having more than 20 % CaO. According to the former classification most of the Finnish FA falls in the low-calcium category. There are many studies on the factors affecting the reactivity of ashes. The reactivity is especially affected by the relative quantity of LOI (loss of ignition), CaO, SiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>, and evidently the specific surface of the FA [e.g. 2, 11]. The pozzolanic activity of F-ashes increases as the grain size decreases.



The properties of a FA begin to change immediately as it is mixed with water or with water and activator. In practice this means that the longer a FA batch mixed with water and/or activator is waiting for compaction the lower its final strength will become. The use of dry FA has generally not been possible because of the absence of separate dry storage facilities. Therefore, there have been studies on the geotechnical properties of FA that have been stored in open air as moisturised piles before construction. In most cases, these pile ashes have to be used with activators, especially when adequate freeze-thaw durability is required. Also, when dry FA is used in practical construction processes there will be a delay before spreading and compaction of the material layers, after the FA material is moisturised into its optimum water content and mixed with activator(s). This delay has to be considered when performing laboratory tests. The studies indicate [12] that after mixing in the laboratory, a delay of 0,5 hours gives relatively correct results although the delay in practice might be much longer, as much as several hours during the same day. The studies of SGT (the geotechnical R&D unit of SCC Viatek Ltd in Finland) [15] have confirmed the former, and that more accurate results can be achieved with a delay from 1 to 2 hours after mixing in the laboratory.

The improvement of FA properties with binders or activators has been a widely studied topic. The most general activators have been different types of lime, cement, gypsum, desulphurisation residue (later FGD), slag and reactive dry FA. There are many studies that indicate that a small addition of lime can significantly improve the strength and durability of FA materials [2,6,12]. Majumbar, in a study conducted in India, indicated that lime addition up to 10 % could improve the strength, after which there is no further improvement [2].

The quality of a finished FA structure will be affected by the properties of the FA itself, the delay after mixing (see above), the water content, the activator(s), and also other factors. These other factors include the effectiveness of mixing, the precision of component proportions in mixing and especially the level of compacted density obtained in the mix. The strength of a well-compacted material layer can be many times higher than the strength of a poorly compacted material layer [2]. In addition, a poorly compacted material layer might not have the required durability properties.

Structures based on FA or mixes with FA have very good long-term cementing properties [12, 35]. In Berg and Bergeson's study [12] the strengths of four different lime-stabilised FA sharply increased during the first 3 months after stabilisation, after which the strength development continued more slowly for at least a year, and probably for much longer. The pozzolanic reactions probably continue as long as there is free lime and water available in the stabilised material [12]. Several studies have also shown that the long-term cementing property is the reason for the self-healing mechanism of a FA layer [7,12]. In some cases the strength development of the FA structure was adequate, and the structure was performing similar to a stabilised base of crushed aggregate, despite cracking [12].

The durability of stabilised FA against weather and external load have been studied with several types of methodology. It has been found that it is not sufficient to determine the strength by using the most general unconfined compression (UCS) test only. It is also necessary to test the stability of material properties in dry, wet and saturated conditions. The stability of material properties can be determined as the change in the compression strength and as the loss of mass. The studies indicate that most of the FA materials are relatively stable at different moisture conditions [12]. The frost susceptibility, and especially the freeze-thaw tests are more demanding of most of the FA materials. In frost susceptibility tests, the worst performing FA mate



rial lost all of its strength or proved to be too frost susceptible. There exist several standardised methods for freeze-thaw tests. Some of the standardised tests measure the loss of mass during the freeze-thaw cycles, for example until the loss of mass is 50 % [12]. The durability is determined on the basis of the number of freeze-thaw cycles. Other tests are performed with a constant quantity of freeze-thaw cycles, and the durability is determined on the basis of the loss of material strength during the test. Poor durability can usually be seen even at the start of the test. These tests have proven to be very important for materials that will be used in arctic climates with freezing soil in the winter. The freeze-thaw behaviour of a material cannot be forecasted on the basis of unconfined compression strength, although the standard ASTM C 593 test requires freeze-thaw durable material to have a minimum strength value (UCS) of 2,8 MPa. The studies of SGT [e.g. 15] have repeatedly shown that there are materials with lower strength and adequate freeze-thaw behaviour. Mixtures of fiber sludge with FA, which have strength much lower than 2,8 MPa, are especially durable against the strains of freeze-thaw cycles.

Usually different durability tests have been conducted as separate tests on a certain construction material. SGT has also studied the effects of combined durability in its laboratory. These studies have shown that the results of combined durability tests may clearly differ from the results of separate tests [15].

The environmental acceptability of FA applications has been widely studied in different countries. One extensive laboratory study has been done in the United States [33]. This study involved ashes from 20 different power plants. The ashes were tested with different types of leaching tests that simulated different conditions. The study concluded that according to the leaching behaviour none of the ashes can cause any harm to the environment. FA filling on a large construction area in Maryland also proved the environmental safety of FA. The average thickness of the fill was 5 meters and the total amount of FA was about 15 million tonnes. The environmental control at the site was multi-faceted for over 15 years. The results showed that the discrete FA filling did not affect the quality of the deep ground water. The substances of the leachates that were released from the fill have been bound into the soil or upper ground water in the close vicinity of the filling site [13]. Several test constructions based on FA and FA-mixes in Finland [e.g. 15] support the results of the research mentioned above, and conclude that properly processed and used FA materials are environmentally safe. Perhaps an important contributing factor limiting the use of FA is the lack of knowledge about the uses of FA in construction among professionals and environmental authorities. Educational programmes, demonstration projects, and technology transfer programmes would certainly help in that regard. However, the largest constraint to more extensive utilisation of FA might be the drawbacks of environmental legislation in different countries.

### 3 RESEARCH PHILOSOPHY AND METHODOLOGY

#### 3.1 NRC-structures

NRC ("New Recycled construction"; abbreviation for "New construction based on recycled materials") -technology aims at technically, economically and environmentally competitive solutions. Conventional road structures are based on natural stone materials and have to be made relatively thick in order to obtain adequate bearing capacity and frost resistance of the structures.

The use of FA mixes will make it possible to obtain properties that can be used to totally change the type and behaviour of a road structure. *Figure 3-1* describes the differences between conventional structures and NRC structures based on FA mixtures:


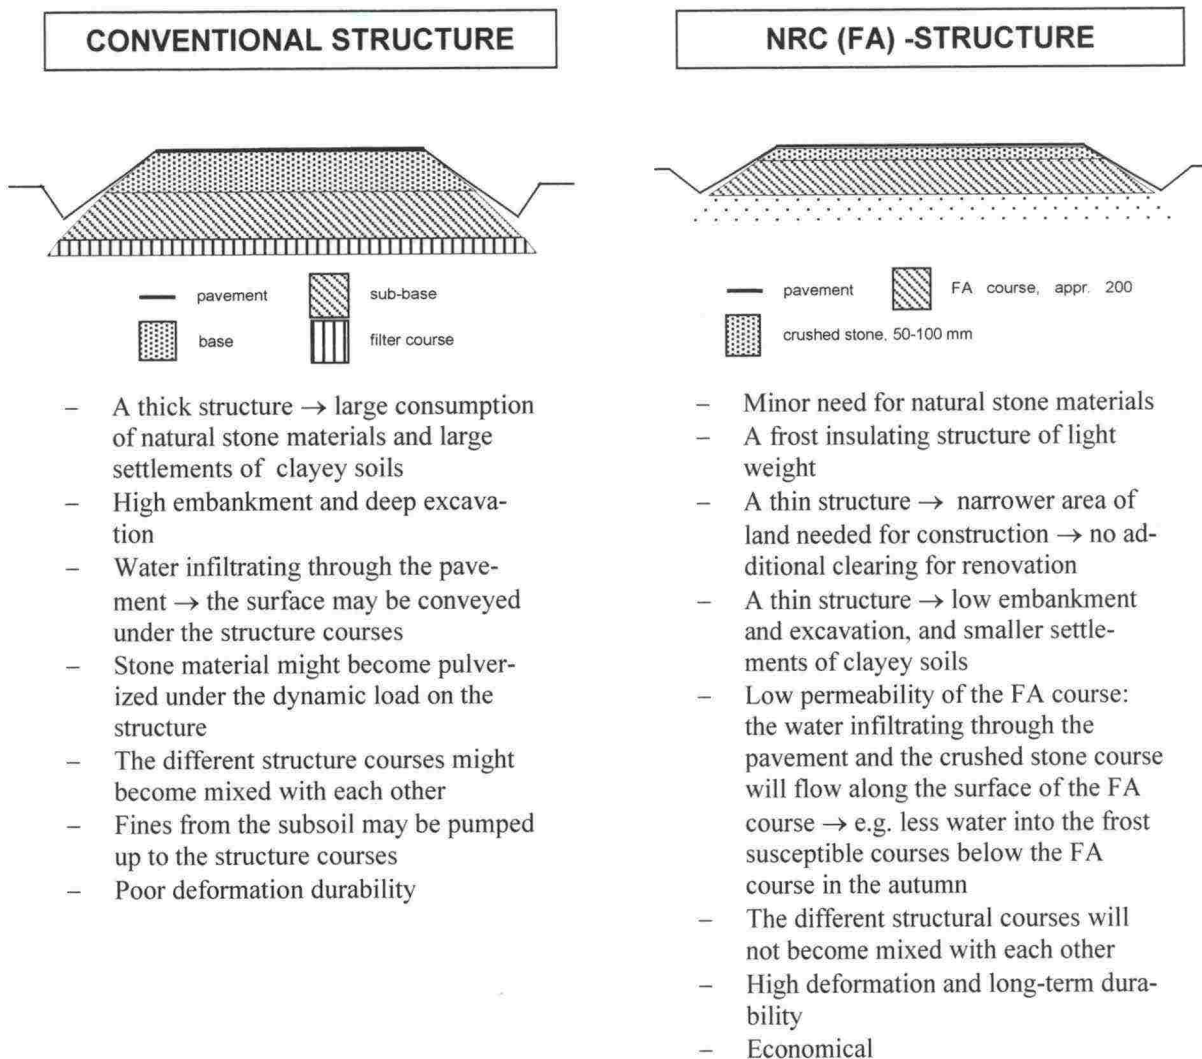


Figure 3-1: Differences between the conventional structures and the NRC (FA) -structures


### 3.2 Upgrading material properties

#### 3.2.1 Proportion of components in the material mixes

The requirements for the properties of a FA-mix depend on the requirements that have been specified for the structure; its bearing capacity, differential settlement etc. The combination of the mix properties can be modified relatively freely. Examples are given in *Figure 3-2*; by varying the proportion of the FA and the fibre sludge in the material mix properties like strength, deformation, durability and permeability can be changed. With an increasing proportion of fibre sludge the material decreases in ultimate strength and in modulus, but exhibits an increasing ultimate strain. With a sufficient proportion of fibre sludge the material becomes elasto-plastic, for example the material with 20 % of fibre sludge in *Figure 3-2b*. The former indicates that required properties for an application may be obtainable by changing the proportion of mixture components. For example, in order to obtain high bearing capacity (e.g. for highways), the amount of fibre sludge has to be relatively small. In case the road has to be frost resistant, and resistant against deformation caused by consolidation settlements (e.g. secondary roads), the amount of fibre sludge should be relatively large.

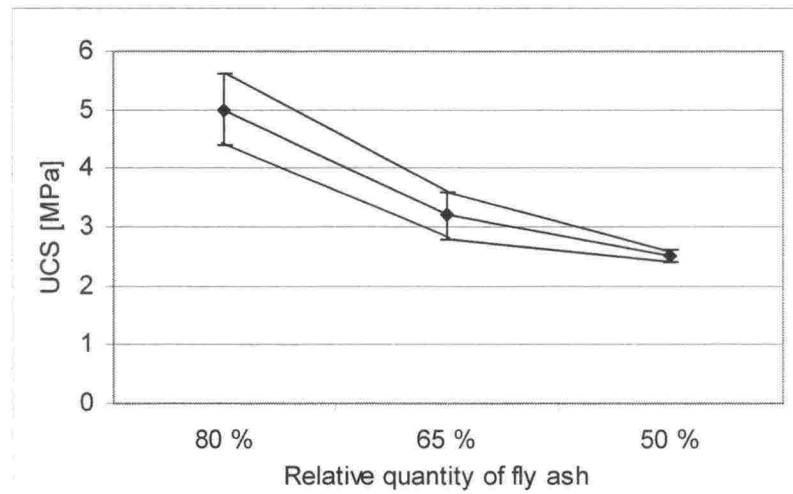

3-2 a.

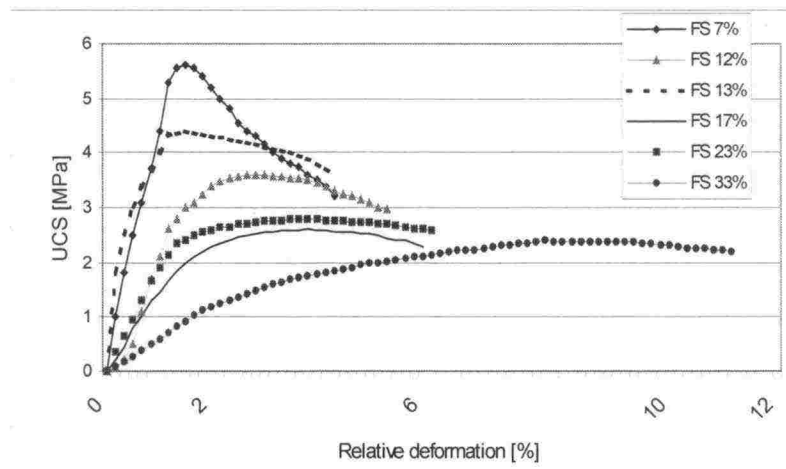


3-2 b.

Figure 3-2: Modification of the properties of a FA-mix, i.e. a mix of FA and fibre sludge:  
 a) strength modified by changing the relative quantity of FA,  
 b) strength-strain modified by changing the relative quantity of the fibre sludge (FS). Strength development of test pieces for 28 days before testing [15]




### 3.2.2 Stabilisation

In addition to the variation in component proportions the properties of FA mixes can be improved and modified with different binders or stabilisers and with their proportion in the mixes. *Figure 3-3* shows an example of the stabilisation of a certain CFA with different binders, and the effect of the binder quantity on the stress-strain properties of the material:

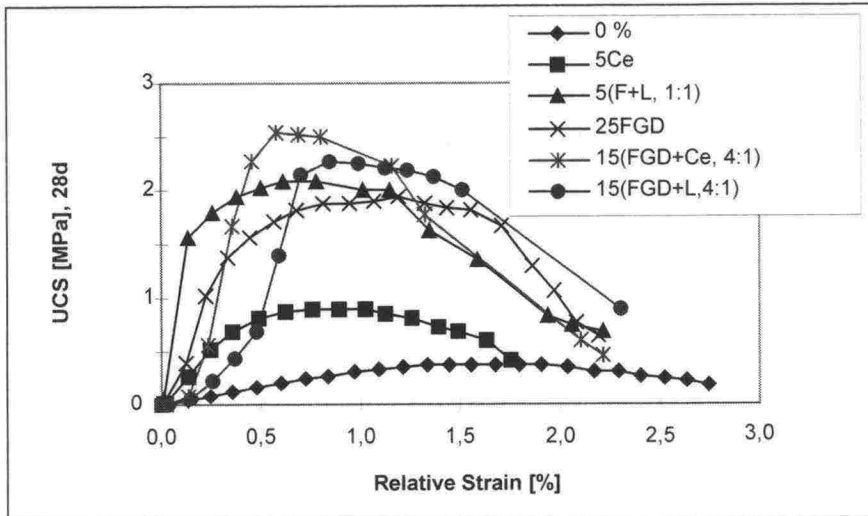

3-3 a.

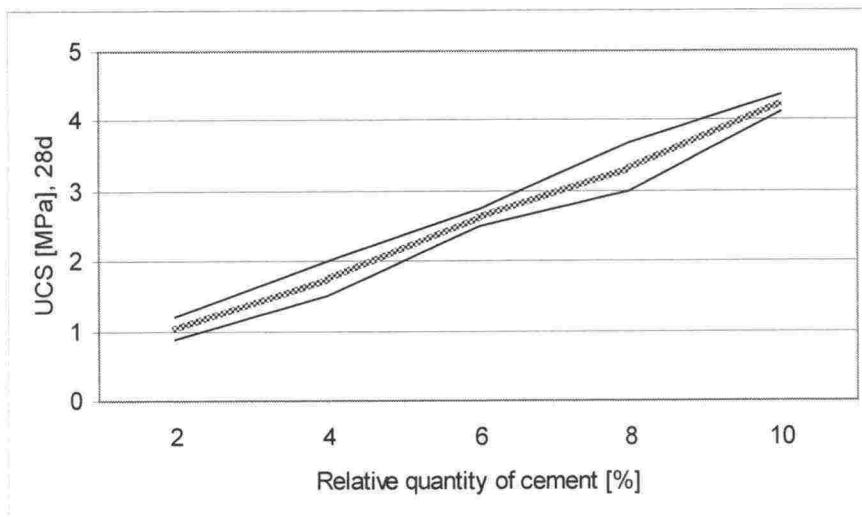

3-3 b.

Figure 3-3: Examples of the effect of; a) different binders on the stress-strain properties of a CFA [6], b) the quantity of cement on the strength of a CFA [15]

### 3.2.3 Storage

The FA properties vary considerably depending on the type and properties of fuel, on the combustion technology and on the storage system. Dry storage (e.g. a silo) does not have any negative effect on the FA properties. If the FA will be stored in an open-air deposit the pile-FA will be moisturised, which affects its properties. This can be clearly seen in *Figures 3-4 a. and b.*, which show the weakening of the self-cementing properties as the compression strength of a certain CFA changes. For the laboratory ageing the CFA was at first moisturised and stored for a given time, relative to the open-air storage time. After storage the CFA was mixed with an



activator when required. The test pieces were compacted to a Proctor density of  $D = 90-92\%$ . Figure 3-4a shows that the compression strength decreased during the first 28 days (1month) after moisturising, and Figure 3-4b shows that the cementing properties slowly became weaker as the open-air storage time became longer. Therefore, FA from dry storage (dry FA) has to be considered as an essentially different material than a pile-FA of the same origin.


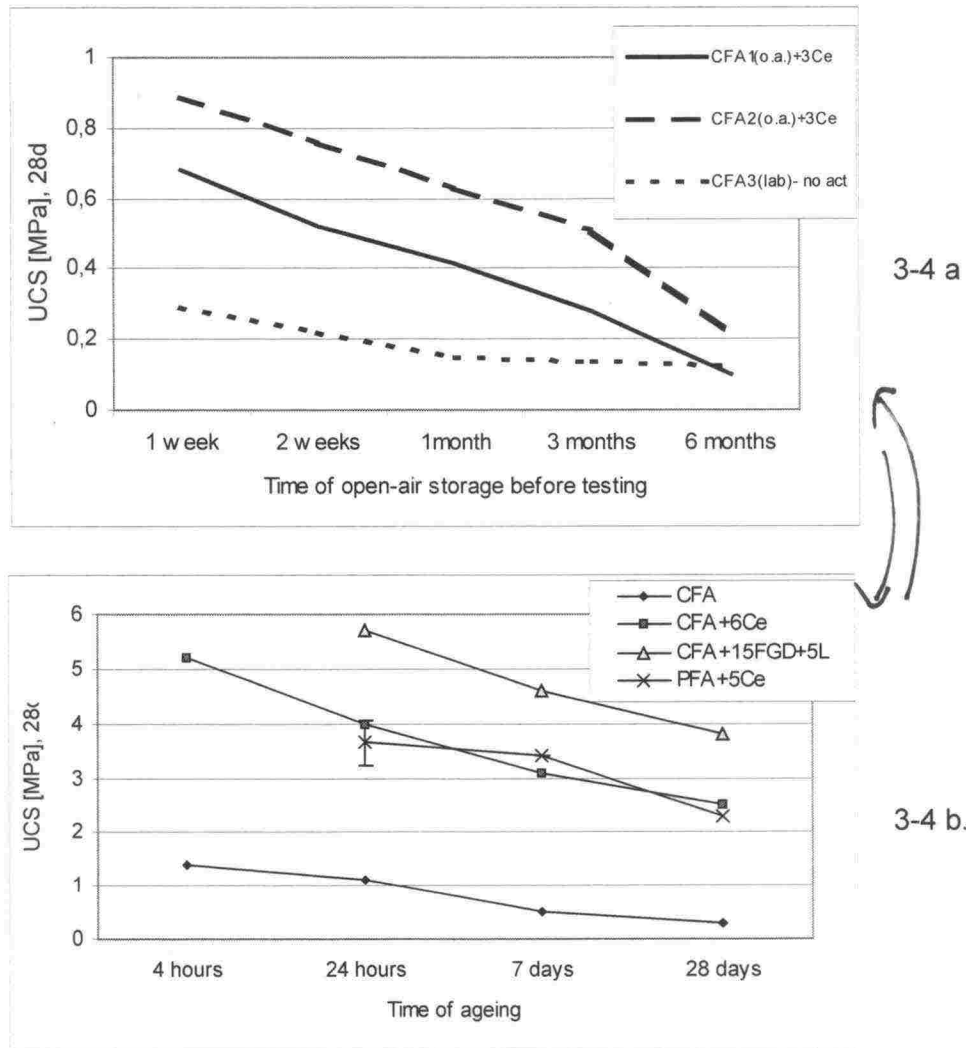


Figure 3-4: Effect of moisturising and storage on the stress-strain properties of some coal FA; a) Open-air storage from 4 days up to 28 days. All materials were laboratory-aged. b) Open-air storage from 7 days to 6 months. CFA1 and CFA2 were samples from actual open-air storages. CFA3 was a laboratory-aged sample. [15]


### 3.2.4 Mixing and compaction

The properties of a NRC-material that is finally used in construction can be significantly affected by the mixing technology, its effectiveness and its dosage accuracy in the manufacturing of the material. The work methods during the actual construction process, especially the compaction method, might also have an important effect on the final outcome. Figure 3-5a shows the differences in the properties of a gypsum-ash mixture after a conventional batch mixer (CON) and a counterstroke or impact mixer (IM); see also Figure 5-11. The high-speed reverse motion of the drums of the impact mixer cause the material particles to heavily strike on each other and,

consequently, the microstructure of the material to break. This can be seen in the SEM-photos of Figure 3-6. Figure 3-5b gives the results of a study on the effect of the relative compaction on the strength development of a CFA and a cement-stabilised CFA.

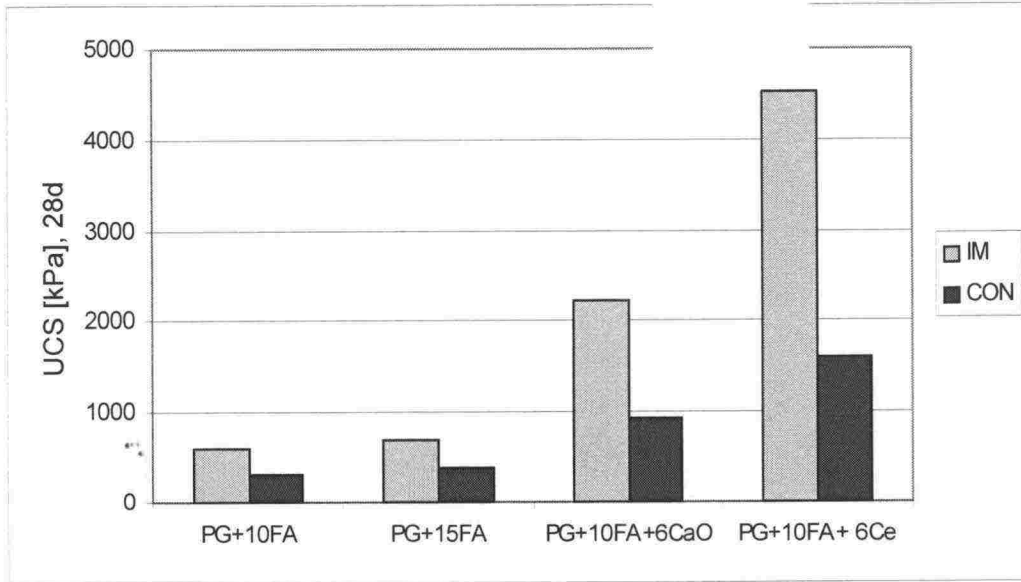

3-5 a.

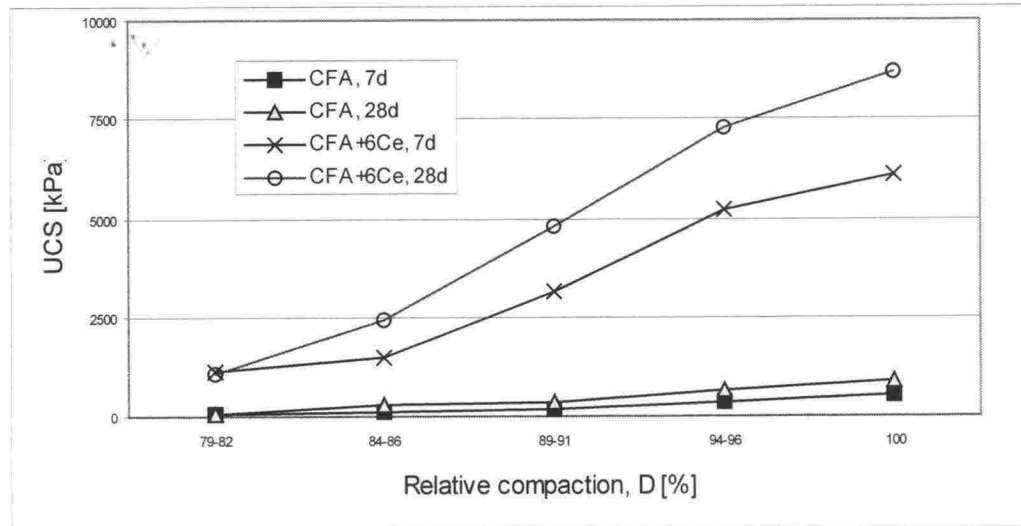

3-5 b.

Figure 3-5: a) differences in the properties of a gypsum-ash mix after it has been mixed with a conventional (CON) and with an impact mixer (IM) and b) the effect of the relative compaction on the strength development of a CFA and a cement-stabilised CFA [15]

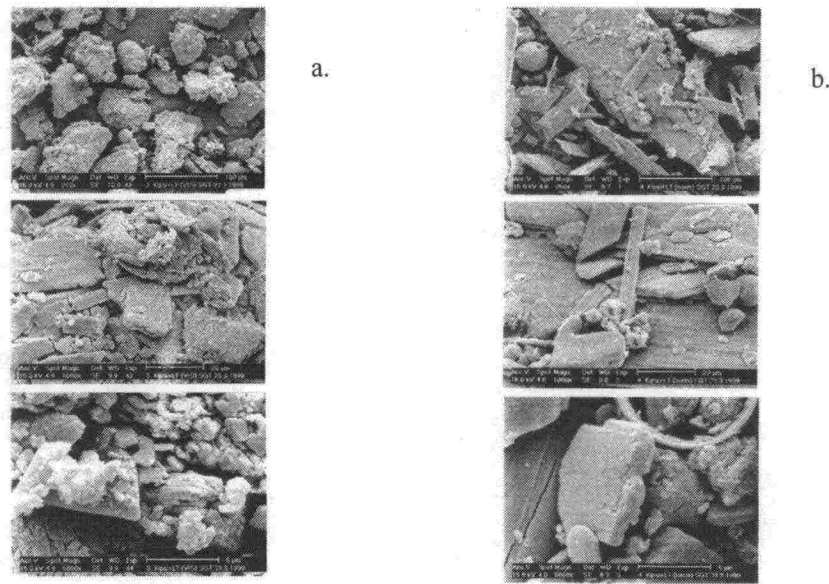


Figure 3-6: SEM-photos of gypsum-ash mixes by a) the impact mixer (IM) and b) the conventional batch mixer (CON)

### 3.3 Criteria and acceptability tests on materials

#### 3.3.1 Criteria on materials

##### Geotechnical requirements

The geotechnical requirements that a NRC-material has to meet depend on the requirements set on the structure where the material will be used, and on the final design of the structure. The requirements for the structure include criteria on its bearing capacity, differential settlement, durability and life time. For this reason it is beneficial to optimise the material and the structure simultaneously.

Concerning NRC-structures for road and field applications there should be established geotechnical criteria for at least the following factors:

- Strength and rigidity
- Frost resistance and frost susceptibility
- Effect of saturation on the strength
- Freeze-thaw durability

Additional criteria could be the following:

- Bulk density
- Thermal conductivity
- Compressibility
- Dynamic load resistance
- Water permeability
- Resistance against acid infiltration or any other chemical load

Table 3-1 below gives several criteria that have been suggested in the published papers [I ... V] and in reports [e.g. 5, 6, 15, 16].

Table 3-1: Suggested geotechnical criteria

Geotechnical Classification of NRC- materials		Unconfined compression strength [MPa], minimum	Frost susceptibility (segregation potential) $SP_0$ [mm <sup>2</sup> /Kh]	
			NRC in general	Fibre-ashes
A	Very strong	4,5	0,2	0,5
B	Strong	1,5	0,2	0,5
C	Fair	0,5	0,5	0,7
D	Weak	<0,5	0,5	1,2
E	No strength development	-	-	-
<b>Assessment of the durability of NRC-materials</b>				
Tests for the properties		Maximum decrease of the unconfined compression strength after the test [%]	Other recommendations	
Freeze-thaw durability		40	Test pieces are solid and unbroken after test	
Water retention capacity		30		
Frost heave		30	-	
Infiltration of water		20	No visible erosion	
Combined test		The result after the most severe test + 5%		

### Environmental acceptability

A NRC-construction has to be environmentally sound; i.e. construction utilising recycled materials should not cause pollution of groundwater or soil. This is also strictly stated in the national legislation on waste and environmental protection [17,18]. One of the major problems in Finland is a missing set of criteria on the environmental acceptability of recycled materials for soil construction. The leaching and transport of different elements and substances from FA mixtures have been tested widely and for a long time, and both factors have been studied at the laboratory level and on different field test sites. The long-term impact can also be studied with dynamic transport models (see Section 6.3).

### 3.3.2 Testing of materials

It has been found useful to carry out the development of a new FA mixture according to a step by step procedure suggested in Figure 3-7.

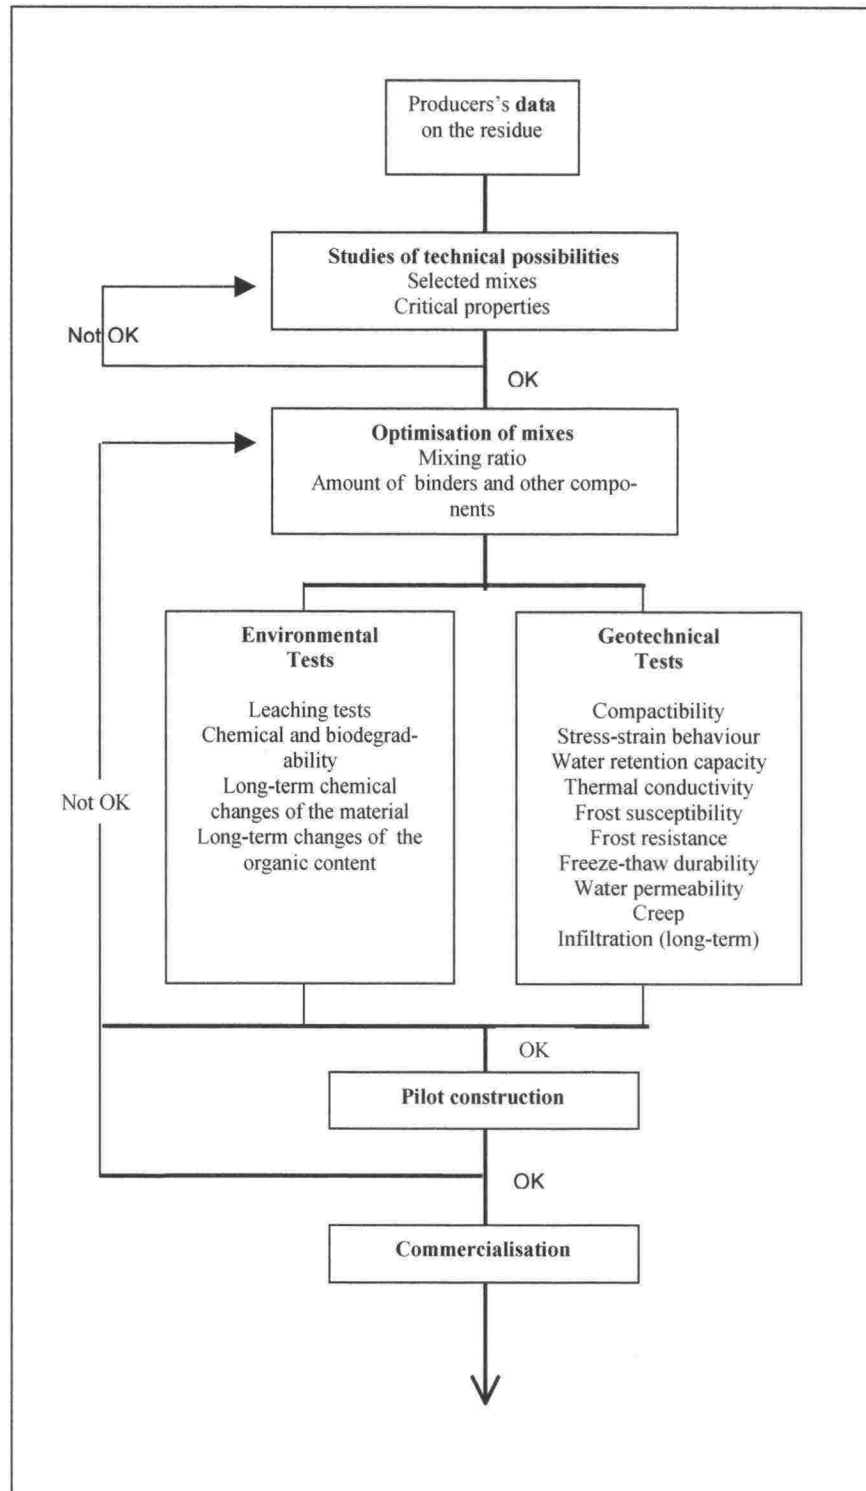


Figure 3-7: Development process of a recycled soil construction material (based on industrial residues) [15] [V]

At the first stage of the development procedure, basic geotechnical properties and the total content of a wide range of inorganic elements of the FA will be determined. The results will be used to make a preliminary assessment on the potential technical and environmental risks and the possibilities for risk management in connection with the FA.



The outcome of the first stage will be used to choose alternative mixtures, i.e. binders and other components, for the second stage of optimisation (optimisation of mixes). The optimisation aims at the determination of a mixture that meets the basic acceptance criteria and is an iterative process. At first, screening tests will be conducted on the selected mixes to determine certain critical geotechnical properties (e.g. stress-strain and freeze-thaw properties). The choices for the final and more detailed optimisation will be made on the basis of the results from the screening tests.

The third stage will involve final tests on one or a few of the best alternatives for their geotechnical and environmental properties and durability. The material mixes that do not meet the criteria can be improved e.g. by increasing the proportion of a binder and tested again - or rejected (e.g. in case there are several alternatives at this stage).

Finally, it is preferable that the best alternatives are tested in full scale (at pilot test sites) after the laboratory tests. Though these full-scale tests are expensive and of long duration, this is a necessary stage, particularly as there exist no officially established acceptance criteria for the NRC-materials and structures and/or national decrees that guide the use of industrial residues in soil construction.

Following is a concise survey of the test methods that the author recommends for the tests of *Figure 3-7*:

### **Compactibility**

The compactibility of the NRC-material will be determined by using the modified Proctor test while simultaneously determining the maximum bulk density (dry),  $\gamma_{d,max}$ , and the optimum water content,  $w_{opt}$ , of the material. The resultant relative compaction  $D$  [%] =  $(\gamma_d/\gamma_{d,max}) * 100$ .

### **Stress-strain behaviour (UCS)**

A cylindrical test piece is subjected to a steadily increasing axial load until failure occurs (standard unconfined compression test, see *Figure 3-8a*). The axial load is the only force or stress applied. The rate of the load is 1 - 2 mm/min. If there is not any noticeable failure, the maximum value of the compressive strength is taken when the deformation (change of height) is 10 %.

### **Water retention capacity**

The water retention capacity is determined by immersing the test piece in water for 7 days, after the test piece has been stabilised for at least 21 days. The condition of the test piece will be assessed during the immersion. After this the strength (UCS) of the test piece will be determined.

### **Thermal conductivity**

Thermal conductivity is determined according to ASTM D 5334-92 (Standard Test Method for Determination of Thermal Conductivity of Soil and Soft Rock by Thermal Needle Probe Procedure).

### **Frost susceptibility**

The test piece will be compacted in a plastic cylinder and the test will start after 28 days stabilisation and after the test piece has been saturated with water. The frost susceptibility will be tested with special test equipment that allows the upper side of the test piece to become frozen (- 3°C) and the under side to remain thawed (+ 1°C) and absorb water on a capillary carpet, see *Figure 3-8b*. At the start during water saturation the load on the test piece is around 20 kPa. The load on the test piece can

be varied during the test, but normally it is around 3 kPa. The frost susceptibility will be determined by measuring the settlements or frost heave of the test piece over a certain time period. Segregation potential,  $SPo$  [ $mm^2/h$ ], can be calculated on the basis of the frost heave.

**Frost resistance** will be determined by assessing the condition (eg. softening and lenses) and by determining the strength (UCS) of the test piece after the frost susceptibility test.

#### **Freeze-thaw durability**

Freeze-thaw tests are applications of a suggested test method of the Technical Research Centre of Finland (VTT: "Tien rakennekerroksissa käytettävän hydraulisesti sidotun materiaalin pakkas-sulamiskestävyyskokeen suoritus"): The test piece that has been stabilised for 28 days will be placed in a container on a capillary carpet. Water will be absorbed by the test piece through this capillary carpet. After 4 hours the test piece will be placed in a freezer, the temperature of which will be decreased from room temperature to freezing ( $-18\text{ }^\circ\text{C}$ ). The test piece will remain at this temperature for 8 – 16 hours. The test piece will then be rotated by  $180^\circ$  and placed on the capillary carpet for thawing, after which the former stages will be repeated. These cycles will be repeated 12 times. The condition of the test piece will be controlled at all times during the test. After the test is completed, the strength (UCS) of the test piece will be determined

#### **Water permeability**

The permeability of a NRC-material is a measure of its capacity to allow a fluid (normally water) to filtrate or to flow through it.

The **rigid wall permeability** test with constant pressure can be carried out after the test pieces (inside plastic moulds) have been stabilised for at least 28 days. After this water will flow through the test pieces for the infiltration phase. The filtrates will be collected and weighed at certain time intervals. Darcy's coefficient of permeability ( $k$ ) will be calculated.

**Flexible wall permeability test with constant head** is carried out according to the recommendations of the Environment Centre of Finland<sup>1</sup>. A test piece inside a rubber membrane will be subject to an all round confining pressure in a test cell. Water will be conducted through the test piece from a front container to a back container, and the water level differences of the containers will be measured. Water flows upward inside the test piece when there is higher pressure in the front water container than in the back container, see *Figure 3-8c*.

#### **Infiltration (long-term acid permeability test)**

A constant flow of acidified water ( $pH = 4 \dots 4,5$ ) will be conducted through test pieces that have been stabilised for 28 days. Time for infiltration is 3 months (90 days). The leachate will be collected after infiltration for 30, 60 and 90 days. Water samples can be analysed and the results can be compared with column test results (in case environmental testing is necessary).

Changes of the strength characteristics of the test pieces will be determined with a unconfined compressive strength test after the infiltration, and the results will be compared with the results on stabilised test pieces without infiltration.

<sup>1</sup> Tekes' National Programme on Environmental Construction / Geotechnics 1994-1999. TEKES = Technology Development Centre)

### Creep test

The creep test provides information about the effect of pre-loading on the strength of the material by combining oedometer and long-term loading of the test pieces. Mixed materials are put inside plastic bags and placed into the moulds of  $\square$  68 mm. The moulds must be greased to allow free movement for the test pieces. Pieces are compressed with loads of 20, 40, 60 or 80 kPa for 180 days after which the unconfined compressive strengths will be determined.

### Leaching tests

Leaching tests will determine potential environmental harm of soils stabilised with different binders after varying stabilisation times. Normally, the leaching test for stabilised NRC-material is the column test (Dutch standard NEN 7343, see *Figure 3-8d*). In a few cases the material density will become so high that it can be tested according to the diffusion test, e.g. the Dutch standard NEN 7345.

### Biodegradability

Biodegradability can be tested according to the OECD Method 301F (OECD Guideline 1992). This is discussed in Chapter 4.5.3.

### Other environmental tests

Testing for chemical degradability, and the long-term chemical changes or changes of the organic content do not have any specified methodology. These properties have not been studied in the projects that have been referred to in this Doctoral Thesis.



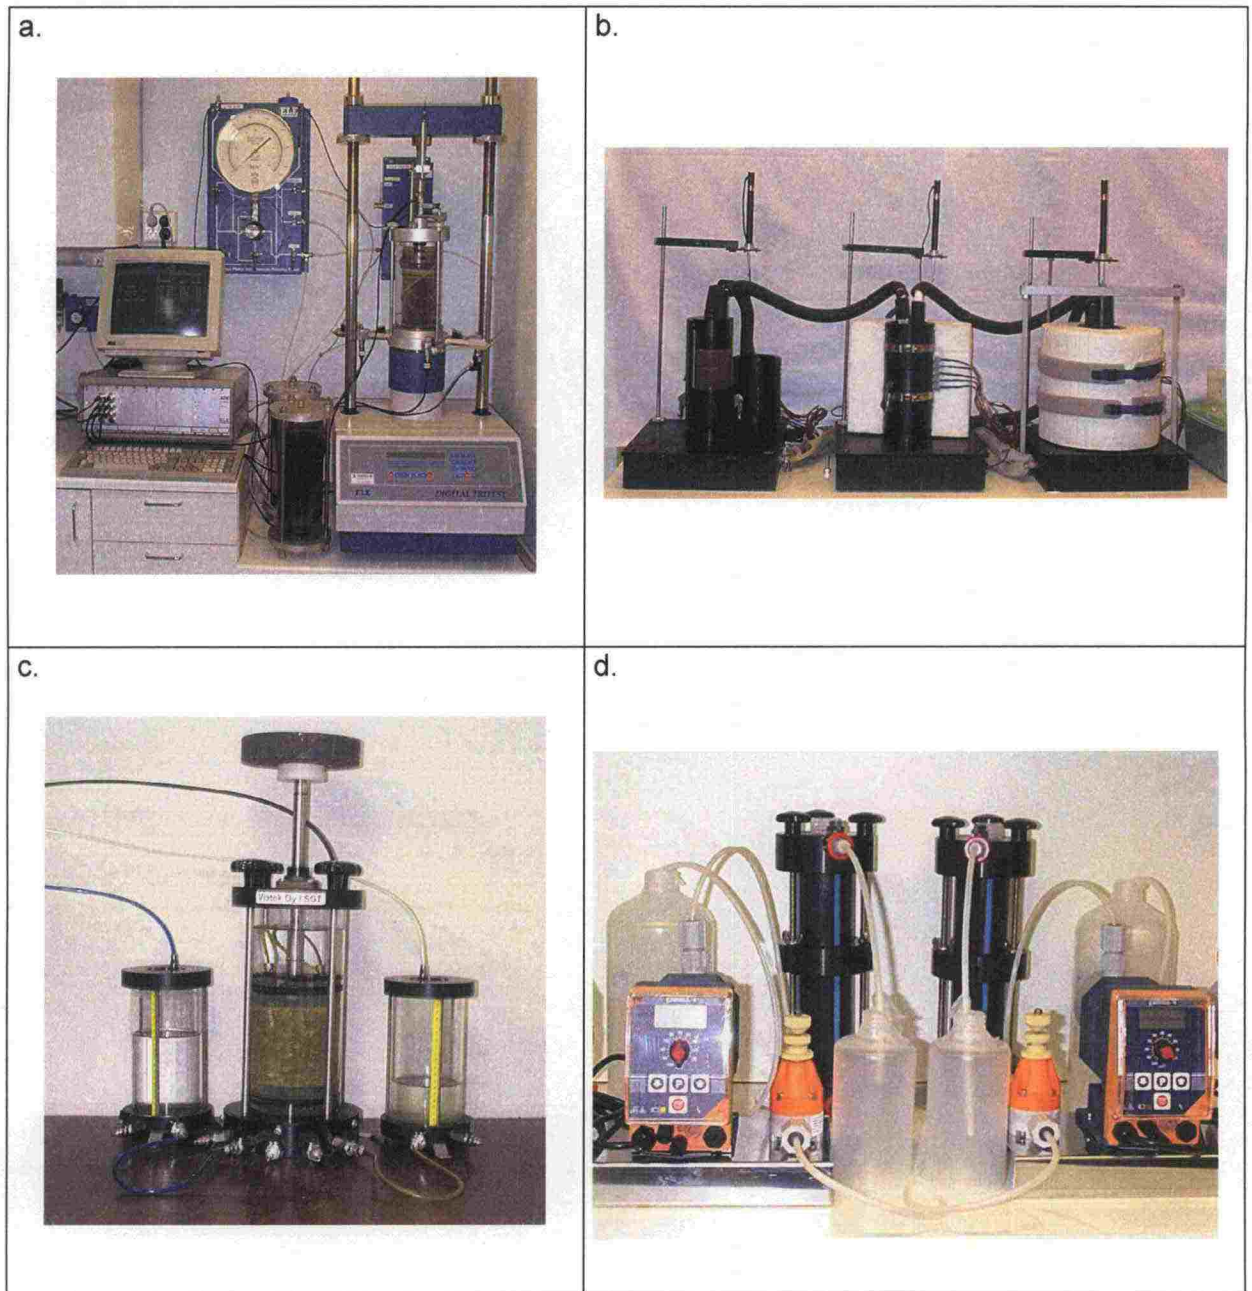


Figure 3-8: Equipment used for testing; a) Standard unconfined compression test, b) Frost susceptibility test; c) Flexible wall permeability test; d) Column test

## 4 MATERIALS AND APPLICATIONS

### 4.1 Fly Ashes (FA)

Out of the total annual production of FA in Finland half is CFA and half is from the incineration of fuels like peat (PFA), wood (WFA) and miscellaneous material (MFA). The miscellaneous materials include different types of sludge like fibre sludge (FS) from paper manufacturing, or sludge from the wastewater treatment processes of a paper mill.

A major part of the FA is not yet being utilised efficiently. However, soil construction is a field of high-volume applications that could easily and effectively recycle all available FA in Finland. CFA applications in soil construction have been developed and widely studied in the world, and for a long time. However, studies on FA based on other fuels are relatively scarce.

The studies and research for this doctoral thesis mainly concentrate on FA produced in Finland. The quality and properties of FA depend significantly on the type and properties of the fuel and on the incineration process itself. Also FA from individual power plants might vary from batch to batch. *Table 4-1* shows the variation in inorganic substances of the main FA categories in Finland.

*Table 4-1: Inorganic substances of the main FA categories in Finland, mg/kg (Helenius 1992, Walsh 1997, Isännäinen 1997,SGT 1996-1998, Finncao 1998, Mäkelä et al 1999, SGT 1990-2000)*

Inorganic substance / element		FA [mg/kg] based on different fuels			
		Coal	Peat	Wood	Misc.*)
Arsenic	As	19...57	2...284	...26	<10...120
Boron	B	...475	8...230	130...160	90...180
Barium	Ba	78...1600	55...790	115...1340	80...1700
Beryllium	Be	3...17	1...3	2	1...4
Cadmium	Cd	<0,5...16	0,5...19	0,8...11	<1...303
Cobalt	Co	21...49	13-33	7...23	6...30
Chromium	Cr	18...300	37...212	40...85	30...120
Copper	Cu	41...144	55...180	58...230	37...200
Quicksilver	Hg	0,1...1,1	0,01...0,6	0,2	<1
Manganese	Mn	430...792	-	-	-
Molybdenum	Mo	7...40	0,9...19	<5...14	<5...10
Nickel	Ni	23...1197	32...700	32...68	40...80
Lead	Pb	27...177	16...970	20...103	20...300
Antimony	Sb	0,2...15	...20	2...15	<13...130
Selenium	Se	2...6	2...7	...1,4	1...4
Vanadium	V	70...360	68...356	32...100	16...190
Zinc	Zn	38...1030	<20...900	300...1900	200...3200
Uranium	U	...12	-		

\*) Miscellaneous fuel like peat/wood, peat/wood/sludge, peat/sludge, wood/sludge, coal/peat, coal/wood

*Table 4-2* contains data on the most important chemical and geotechnical properties of FA. In general Finnish FA are F-ashes according to the classification in the United States, i.e. pozzolanic but only slightly self-cementing. In regard to the lime content (CaO) which might be larger than 20 %, some of the PFA, WFA and MFA could be classified as C-ashes [21]. The self-cementing behaviour varies significantly between different FA categories as can be seen in the data given in *Table 4-2*.



Since the pozzolan reactions immediately start after water addition it is clear that the cementing properties of a pile-FA are weaker the longer the storage time. This can be noted in *Figure 4-2*. Loss of Ignition (LoI), content of CaO, and the specific surface quite clearly correlate with the cementing behaviour of a FA [2,3].

*Table 4-1* shows that PFA, WFA or MFA do not contain more environmentally harmful inorganic substances than CFA, and often even less.

*Table 4-2* shows that in regard to pozzolanic reactions all types of FA have high contents of SiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>. Best self-cementing results, as high as 8-10 MPa after 28 days, have been obtained with PFA, WFA and MFA. In these cases the content of CaO was also high.

The optimum water content ( $w_o$ ) also varies significantly. It is evident that the high content of CaO of PFA, WFA and MFA increases the optimum water content.

Table 4-2: Chemical and geotechnical properties of selected FA in Finland [6, 15, 22,23,24,25,26]. Figures given in parentheses are the mean values of the obtained data in case a range of data is given. Only one figure is the mean value of several measurements or test results

Fly ash	LOI	CaO	Fe <sub>2</sub> O <sub>3</sub>	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	MgO	C <sub>q</sub> <sup>*)</sup>	Grain size, dry FA, d <sub>50</sub>	Self-cementitious <sup>**)</sup> Dry FA	Pile-FA, ageing 28d	Bulk density (dry)	Water content, optimum/w <sub>o</sub>
	%	%	%	%	%	%	-	mm	kPa	kPa	kg/m <sup>3</sup>	%
CFA-A	5,6... 14,7 (9,0)	3,47... 9,4 (5,7)	7,7... 13,6 (8,8)	41,9... 53,4 (48,7)	16,6... 27,4 (22,9)	2,01... 5,9 (3,5)	0,54... 0,75 (0,66)	0,01...0,02	640...1310 (884) D = 100 % 380 D = 90 %	110 D = 90 %	720...850 (804) max dry density 1220...1310 (1278)	22...27 (25)
CFA-B	1,5...3,4 (2,6)	3...3,9 (3,3)	6,1... 17,5 (9,6)	42,5	16,4... 22,7 (20,2)	n/a	0,58...0,6 (0,6)	0,015... 0,035	310...1660 (1030) D = 100 % 620 D = 90 %	200 D = 90 %	740...1090 (900) max dry density 1290...1580 (1482)	13...26 (18)
CFA-C	6,1... 17,5 (10,0)	0,2...4,8 (2,3)	4,1... 17,0 (9,8)	42,9... 67,5 (54)	17,7... 25 (21,8)	0,5...3,3 (1,6)	0,33... 0,66 (0,49)	0,015... 0,04	330...1360 (692) D = 100 % 190 D = 90 %	180 D = 90 %	630...920 (804) max dry density 1180...1360 (1292)	21...29 (24)
CFA	1,5... 17,5 (7,2)	0,2...9,4 (3,6)	4,1... 17,5 (9,4)	41,9... 67,5 (48,4)	16,4... 27,4 (20,8)	0,5...5,9 (2,6)	0,33... 0,75 (0,6)	0,01...0,04	310...1660 (869)	163	630...1090 (836)	13...29 (22)
Fly ash	LOI	CaO	Fe <sub>2</sub> O <sub>3</sub>	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	MgO	C <sub>q</sub> <sup>*)</sup>	Grain size, dry FA, d <sub>50</sub>	Self-cementitious <sup>**)</sup> Dry FA	Pile-FA; ageing 28d	Bulk density (dry)	Water content/ ω <sub>o</sub>
	%	%	%	%	%	%	-	mm	kPa	kPa	kg/m <sup>3</sup>	%
PFA	1...15	5...30	0...20	3...57	2...29	1...25	0,48	n/a	300...>9000	n/a	590...1500	20...79
WFA	5...34	40	3	30	7	5	1,7...1,8	n/a	1600...>8000	n/a	1000...1300	30...45
MFA	1...8	n/a	n/a	n/a	n/a	n/a	n/a	n/a	300...>10000	n/a	800...1600	18...57

$$*) C_q = \text{coefficient of quality} = \frac{CaO + Al_2O_3 + MgO}{SiO_2} \quad [3]$$

\*\*\*) Self-cementitious is determined by the unconfined compression strength of a test piece after 28 days cementation.

The strength development of a FA is less the larger the LoI value (i.e. the non-combustible part of the FA) and the smaller the percentage of CaO in the FA. *Figure 4-1* shows that even a very small (0,5-1,0 %) addition of active lime significantly improves the cementation. The figure shows, however, that there are differences between FA from different sources. Additionally, it has been shown that the larger the specific surface of a FA the better its strength development [2].

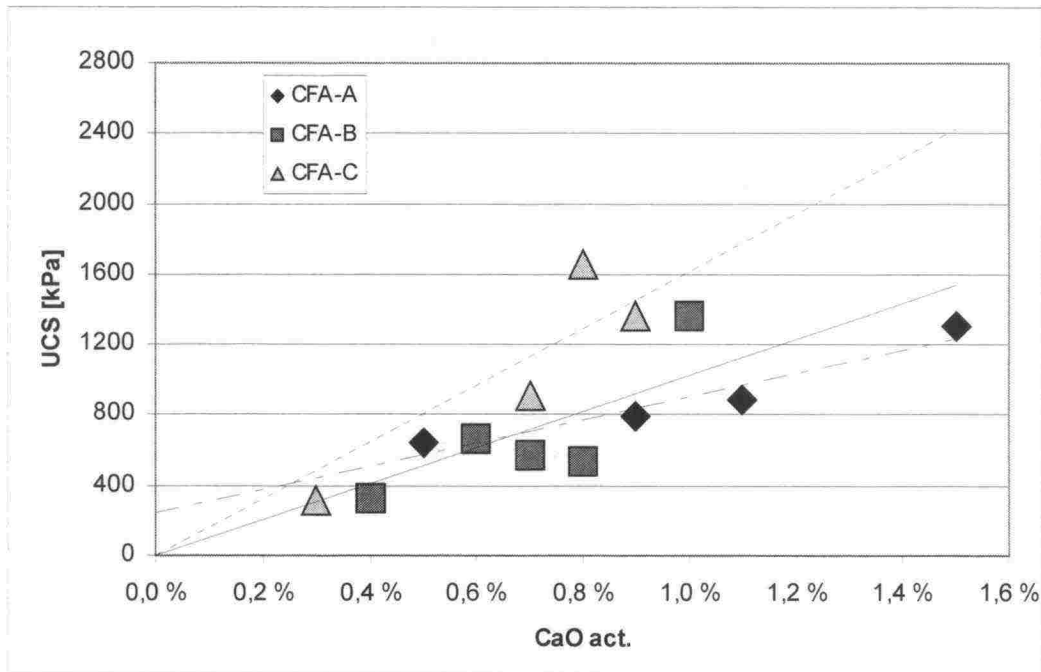


Figure 4-1: Unconfined compression strength as a function of the content of active CaO. The test was on CFA from three separate power stations [6]

The strength development of a FA will depend considerably on following factors as well:

- Binder or activator (quality, properties, quantity)
- Water content
- Compaction
- Homogeneity of the mixture
- Efficiency of mixing

The effect of the water content on the strength development and on the compaction of the FA is significant. Most importantly, the farther the water content of the FA is from the optimum water content the lower will be the resultant final strength. The following figures show test results on some FA: for the effects of water content, *Figure 4-2*, and compaction, *Figure 4-3*, on the strength. By using the tests showing the effect of different water contents it is possible to determine the tolerances for changes in water content in practice. Likewise, it is possible to determine the minimum relative compaction, D [%], by varying the relative compaction in the laboratory tests. Similarly, *Figure 4-3* shows the strength might fall significantly when relative compaction is less than 90-91 %. Therefore, the targeted relative compaction is 91-92 % for most of the FA structures.

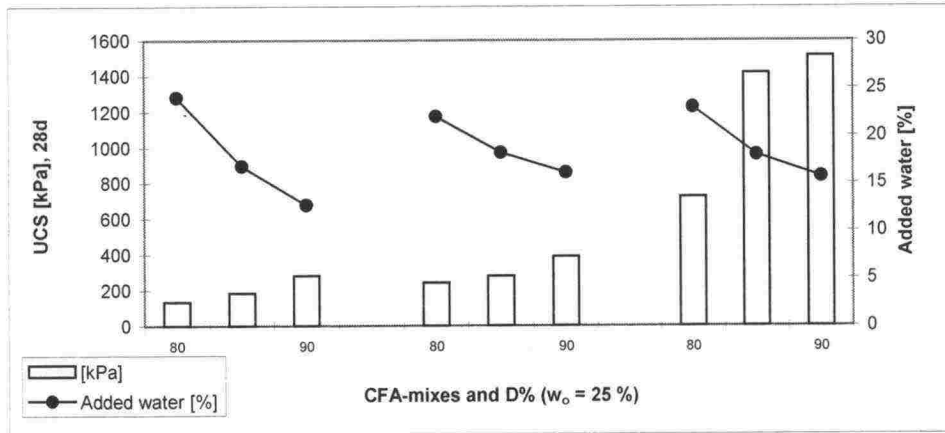


Figure 4-2: The effects of water content on the strength of some CFA-mixes (examples)

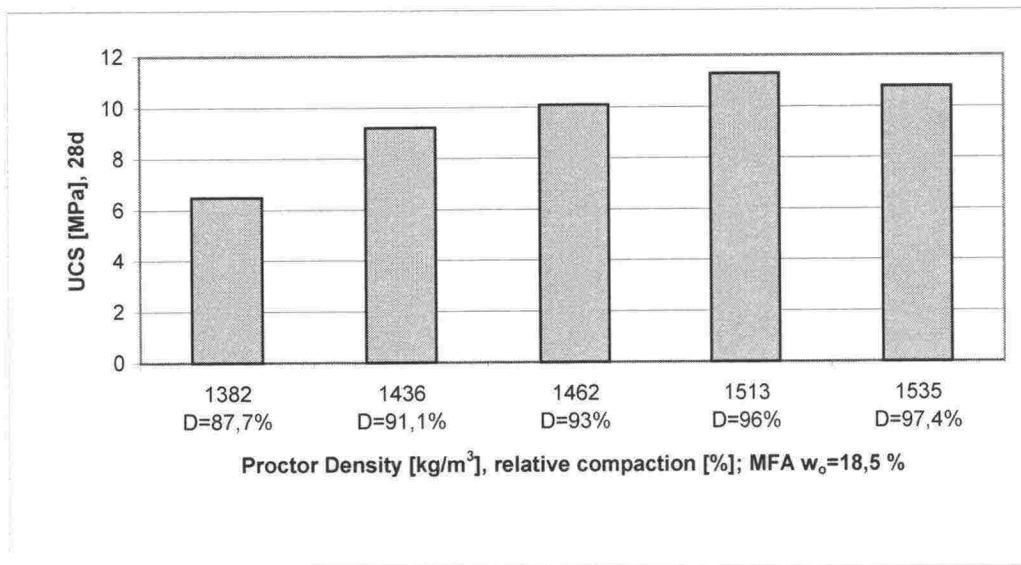



Figure 4-3: The effects of compaction on the strength of a MFA (example)



## 4.2 Improvement of FA properties with binders

Binders can be used to significantly improve the geotechnical and environmental properties of FA. Even a very small addition of binder as an activator for a dry FA may activate and accelerate the cementation reactions in the FA. Even 1 – 2 % of activator might multiply the strength of a FA material. To obtain sufficient strength of the material, the required binder quantity is considerably larger in the cases of pile-FA or other originally weakly cementing ashes [15].

There exist several binders or activators that can be used with FA. The most important binders are different types of lime and cement, as well as industrial residues like slag (especially the blast furnace slag), gypsum, reactive ashes and FGD (flue gas desulphurisation residues). Lime has proved to be a very efficient activator, and cement is very versatile. The use of industrial residues is reasonable because of the environmental and economic benefits, that can be obtained, and because it is also technically feasible. *Figure 4-4* shows the effect of cement quantity on the strength of three FA. The figure indicates that the strength of these three types of FA will be improved in an almost linear amount with an increasing amount of cement.

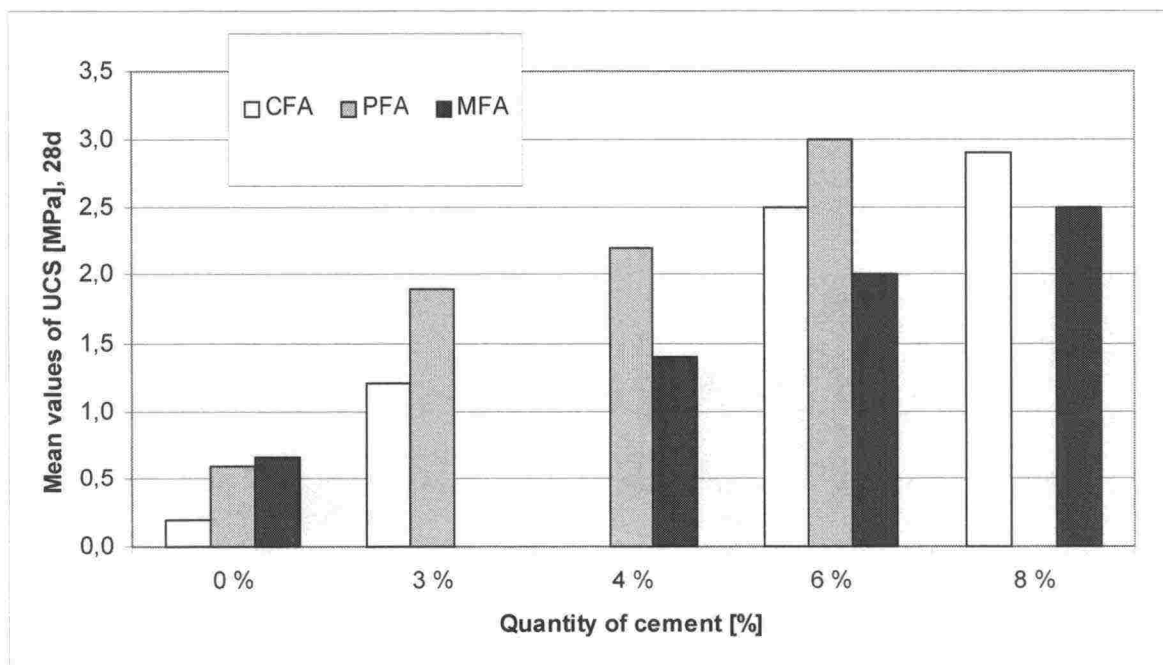

*Figure 4-4: Effect of the quantity of cement on the unconfined compression strength of three different types of FA (examples of certain individual cases) [15]*

It is obvious that the effects of binders and binder mixes are different for different FAs. *Figure 4-5* compares the effect of certain binders (all 6 % of dry weight) on different categories of FA samples of the different categories after 28 days of stabilisation.

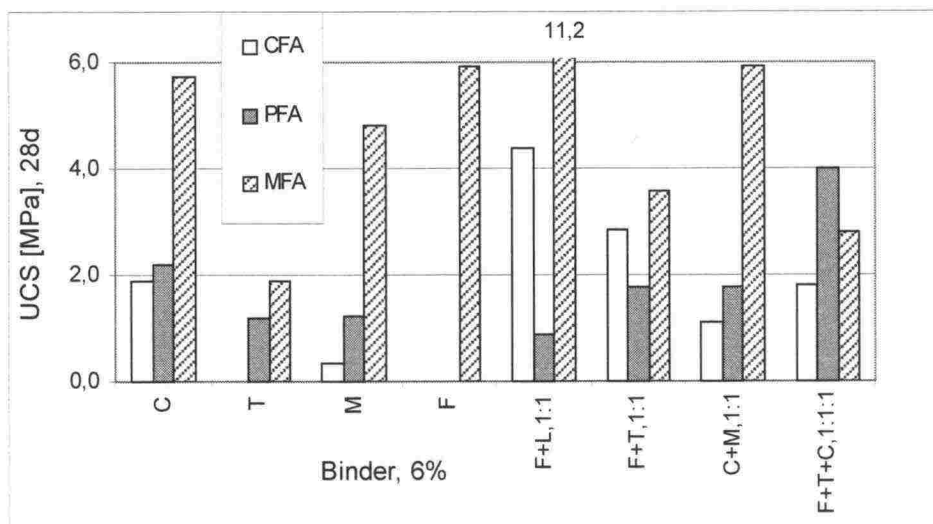
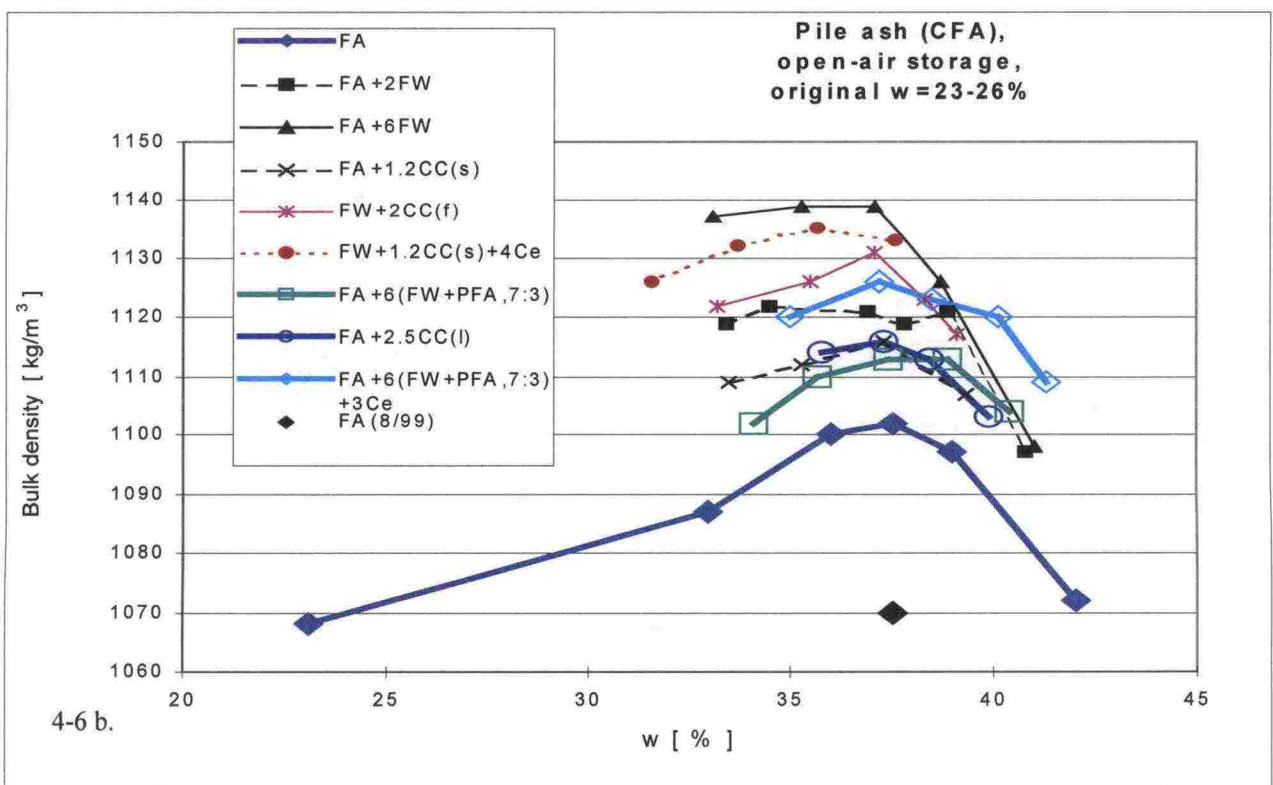
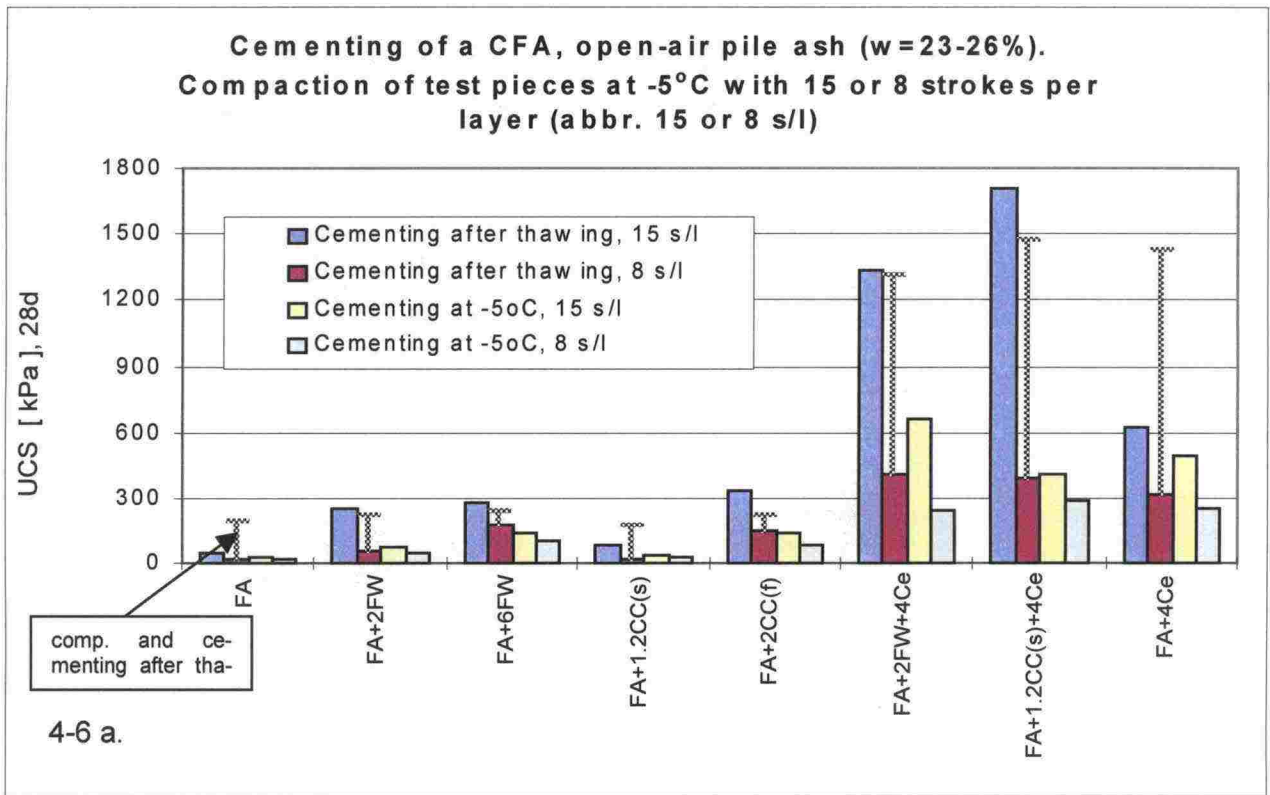


Figure 4-5: Effect of different binders (6%) on the strength of different FA (stabilisation for 28 days). C=cement, L=lime (CaO), T=hydrated lime, M=blast-furnace slag., F=Finnstabi®; mean values of several cases) [15]

Each binder has its characteristic reactivity and stabilisation time. The results of Figure 4-5 would be different with different binder quantities and times of stabilisation. The figure indicates that it is worthwhile to test the different binder alternatives because of their significantly different effects. The studies indicate that MFA-types of FA seem to have relatively good strength development with all types of binders.

The winter-construction properties of FA can be improved with help of calcium chloride,  $\text{CaCl}_2$  (CC). SGT studies have been conducted on the improvement of FA with salt products like CC-flakes or -solution and the filterwaste (FW). FW is a by-product of the production process of CC, and it consists of free lime, gypsum and 20-30 % calcium chloride. Figure 4-6a shows that the compaction and strength development of FA at  $-5^\circ\text{C}$  will be clearly more effective with an addition of only 2 % FW or 1,2 % CC-solution than without any CC. The actual cementing will start only after the FA structure has thawed, though the compaction has taken place during the frost period. Figure 4-6b shows the improvement of the compaction results of a certain FA (not frozen) when mixed with different salt products. The salt products also decrease the frost heave of frost susceptible NRC-materials. Figure 4-6c shows results from 3-cyclic frost heave tests on heavily frost susceptible materials that have been treated with the salt products. The results indicate that the frost heave is considerably decreased. The most effective additive was 2 % of CC-flakes. A study concluded that frost susceptible FA can be improved with a small addition of CC [20]. However, this finding has to be checked with additional research.



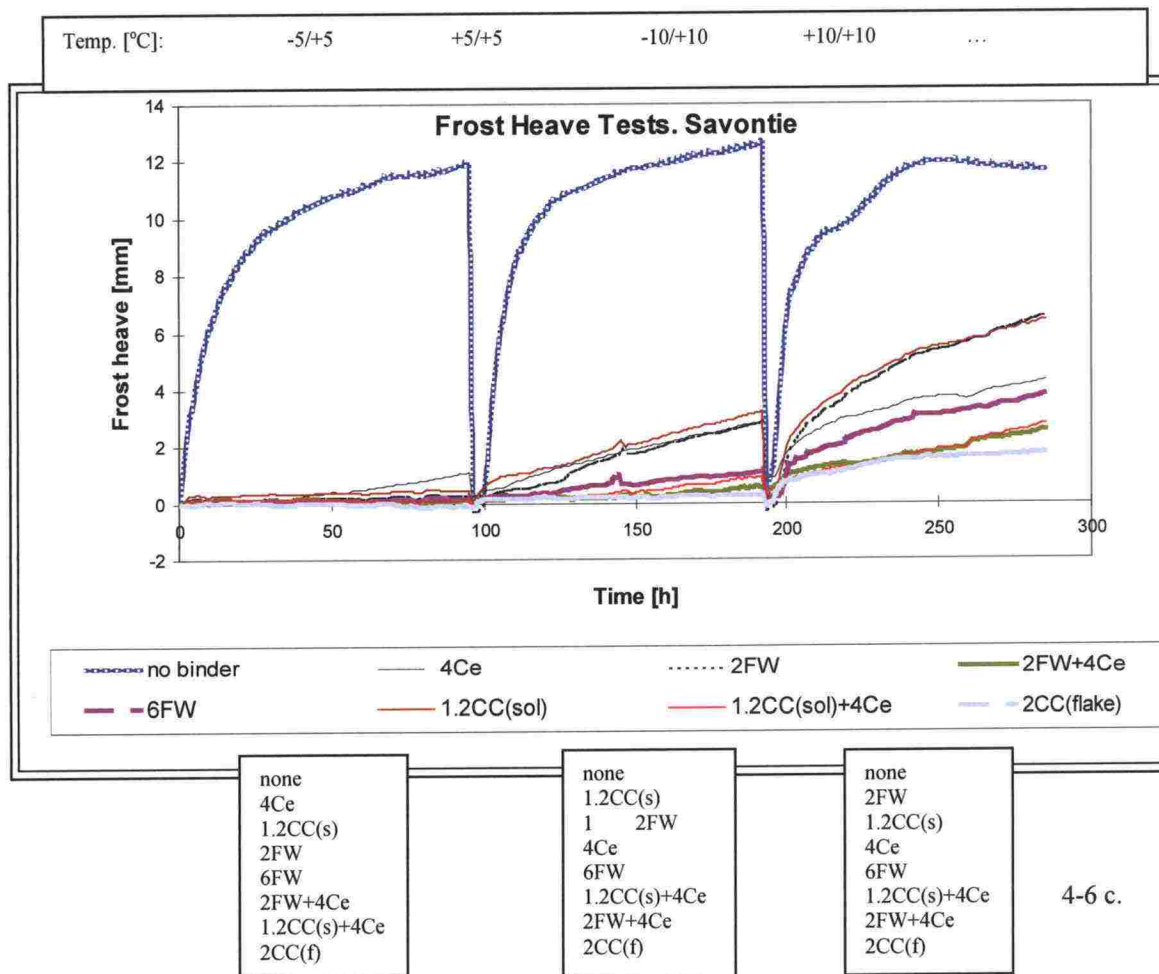


Figure 4-6: Improvement of FA and soil properties with calcium chloride salt (CC) and filterwaste (FW); a) Cementing behaviour of CFA; b) Bulk density of CFA ; c) Frost heave behaviour of crushed stone. CC as solution (s) or as flakes (f) [20]

Binders can also be used to improve the environmental behaviour of FA. Figure 4-7 shows the effect of different binders on the solubility of heavy metals from a stabilised FA. For example, the figure indicates that the blast furnace slag significantly reduces the leaching of several heavy metals. This test was made in 1991 on a coal ash using the EP Tox Test [37] that is designed to simulate leaching under natural disposal conditions. The leaching medium was diluted acetic acid.



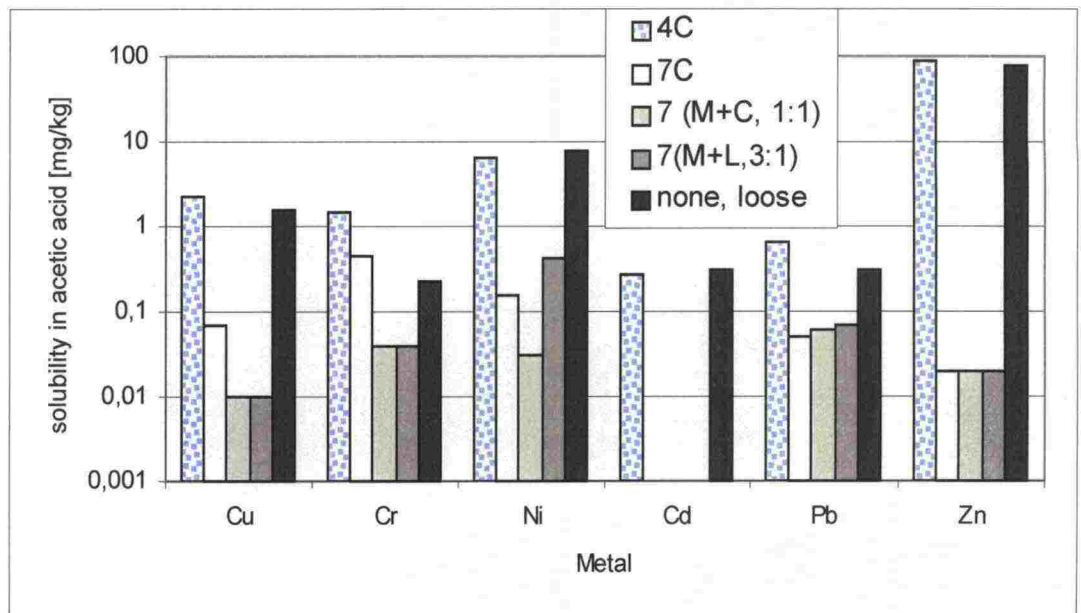


Figure 4-7: Effect of certain binders on the leaching of heavy metals from a FA. C=cement. M=blast furnace slag, L=lime. [15]

### 4.3 FA mixtures with other industrial residues

The mixing of FA with other industrial residues yields interesting possibilities for developing totally new types of materials and applications for road construction as well as for other areas of soil construction. The research for this doctoral thesis concentrated on the following NRC material mixtures:

- Fibre sludge (FS) + FA = Fibre-ash
- Phospho-gypsum (PG) + FA = Gypsum-ash
- Stainless steel slag (S) + FA = Slag-ash



Figure 4-8: Fibre-sludge or "fibre-clay" consists of organic fibres, kaolin and water.

### 4.3.1 Fibre-ash

The concept of fibre sludge involves pulp or wood based primary sludge and deinking sludge from the paper industry. Principally the fibre sludge consists of organic fibres, kaolin (clay) and water. This is why it is frequently called 'fibre-clay', see *Figure 4-8*. *Table 4-3* characterises the Finnish fibre sludge types.

*Table 4-3: Characteristics of Finnish fibre sludge [15]*

	Mill Nr	w [%]	LoI [%]	Permeability, k [m/s] at D = 93-95 %
Deinking sludge	1	84...190	55...72	$1,2 \cdot 10^{-9} \dots 9 \cdot 10^{-9}$
	2	138...233	52...59	$1 \cdot 10^{-9} \dots 3 \cdot 10^{-9}$
	3	83...95	58...61	$1,5 \cdot 10^{-7} \dots 2 \cdot 10^{-8}$
	4	95	56	$1 \cdot 10^{-8}$
Pulp based sludge	5	176...213	70...81	$1 \cdot 10^{-8} \dots 1 \cdot 10^{-9}$
	6	123...153	56...58	$3 \cdot 10^{-9}$
	7	130	51	$5 \cdot 10^{-10}$
	8	204	69	$2,5 \cdot 10^{-9}$
Wood based sludge	9	120...180	55...67	$5 \cdot 10^{-8} \dots 5 \cdot 10^{-9}$
	10	116...150	53...65	$1 \cdot 10^{-8} \dots 3 \cdot 10^{-10}$
	11	147...154	59	$2,5 \cdot 10^{-9}$
Pulp or wood based sludge	12	181...240	92	$2 \cdot 10^{-8}$

To date fibre sludges have been reused or recycled relatively little in soil construction. Certain fibre sludges are being developed as construction materials for impermeable barrier structures of waste deposits or landfills, because of their relatively low water permeability. Fibre sludges cannot be used alone in road construction because of their rather low resistance to weather and physical load. On the other hand, a mixture of FA and fibre sludge, i.e. fibre-ash, might result in a NRC-material having quite new combinations of properties [II]:

- a. resistant against large deformations, i.e. "unbreakable structures"
- b. good frost insulation capacity
- c. good water retention capacity
- d. light weight
- e. relatively good bearing capacity
- f. workable and easy to construct

The excellent deformation resistance is due to the constituents of the fibre sludge, i.e. clay and fibres. The fibres may act as reinforcement in the sludge matrix [1]. The more fibre sludge a mixture contains the larger can be the deformations of the fibre-ash structure, as shown in *Figure 4-9* and *Figure 3-2*:

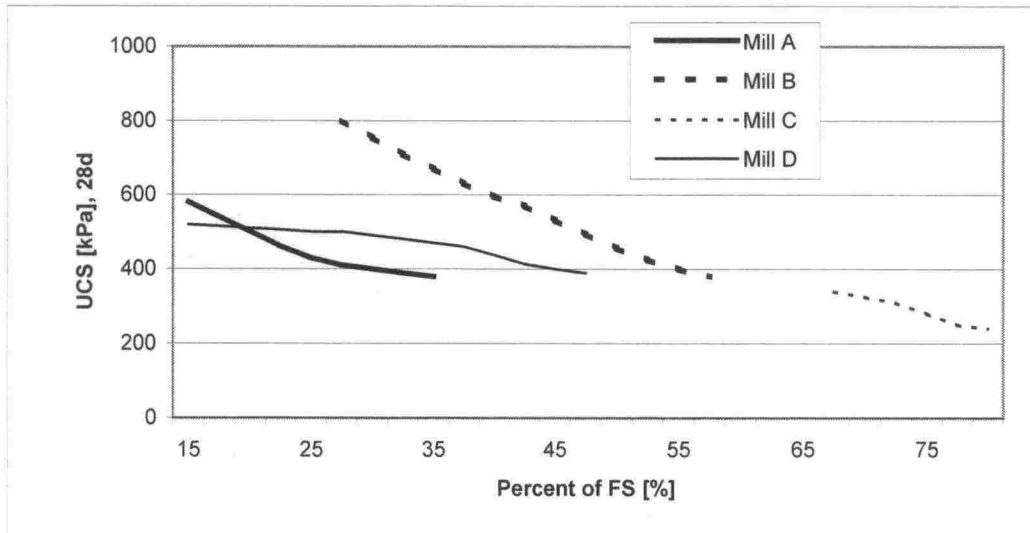


Figure 4-9: Effect of the percent of fibre sludge on the strength of fibre-ash mixtures [15]


Usually it is necessary to add binder to fibre-ash mixtures in order to obtain NRC-materials that adequately withstand frost and freeze-thaw cycles. The most usual binder has been cement. Changing the binder quantity can significantly modify the properties of a fibre-ash mixture, but for economical reasons the quantity should be optimised to a level that allows only adequate long-term strength properties to be achieved. The quantity and quality of the FA in the mixture will remarkably affect the required binder quantity. It has been found that the larger the ash quantity the smaller is the required binder quantity. The type of fibre sludge in the mixture also affects the quantity of FA and binder. Studies indicate that the amount of de-inking sludge should not be higher than 70 % and the amount of other fibre sludge types not higher than 50 %. Additionally the studies have shown that even a small amount like 10 – 20 % of fibre sludge will significantly improve the deformation resistance of a fibre-ash [15].

Table 4-5 gives data on the properties of some fibre-ash mixtures that have been stabilised with cement.


### 4.3.2 Gypsum-ash

Studies have been performed using phospho-gypsum or processgypsum (abbr. G or PG), a calcium sulphate dihydrate ( $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$ ) that is a residue from the manufacturing process of phosphoric acid. Some of the phospho-gypsums are being used by the construction industry for building materials but the main part is being dumped in deposits. Phospho-gypsum often contains small residual amounts of phosphoric acid and sulfuric acid and also some trace concentrations of other minerals [15, 19].

Thus phospho-gypsum alone cannot be recycled in road construction. However, mixtures of phospho-gypsum, FA and binders can yield materials that have adequate strength properties for road construction. The best types of binders for gypsum-ash mixtures are cement and lime, which can be seen from the test results shown in Figure 4-10a. The test results show the effect of binder type and quantity of PFA on the strength of gypsum-ash.

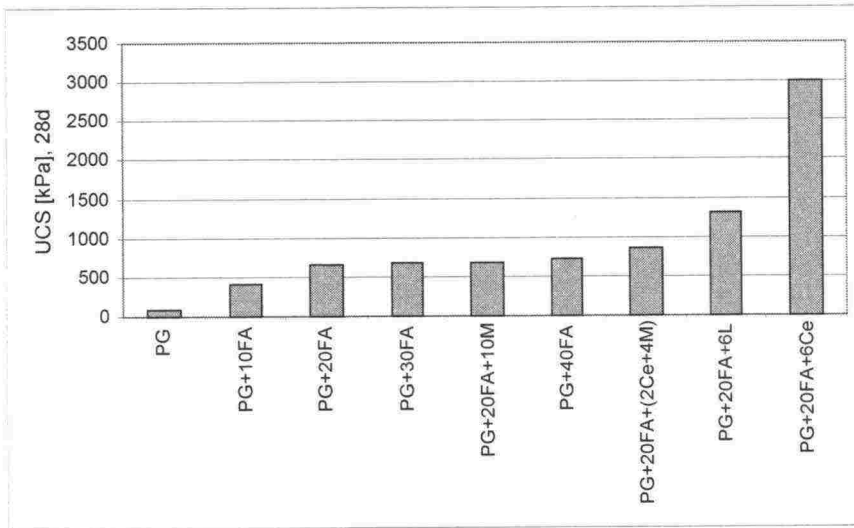

4-10 a.

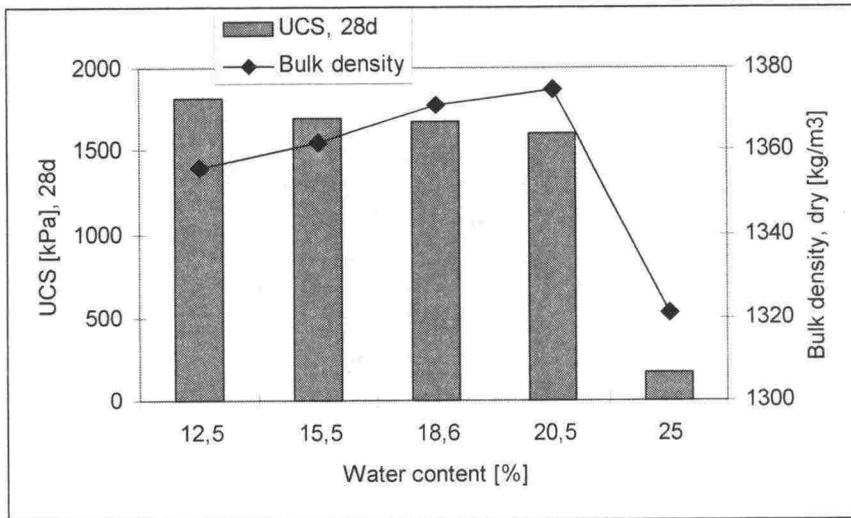

4-10 b.

Figure 4-10: a) Compression strength of gypsum-ashes as function of binder type and quantity of PFA ; b) Effect of water content on the bulk density and strength of test pieces of (PG+PFA, 9:1)+5(M+Ce, 7:3) [15]

The effect of water content on the strength of test pieces of gypsum-ash materials was tested with a mixture (PG+PFA, 9:1)+5(M+Ce, 7:3) that also has been used in full-scale test construction. Figure 4-10b shows that the maximum strength could be obtained with a water content that was significantly smaller than the optimum water content ( $w_o$ , which would yield the maximum bulk density). The results indicate that mixtures of gypsum-ashes have to be tested at different water contents, not only at the maximum bulk density.

Table 4-5 presents data on the geotechnical properties of some gypsum-ash mixtures.

### 4.3.3. Slag-ash

Stainless steel slag (hereafter referred to as slag) is produced in huge quantities as a residue of stainless steel production. Until now there have not been any feasible recycling applications utilising the stainless steel slag. In Finland the slag is deposited as piles in lagoons close to the sea.



For this doctoral thesis the author has studied the slag produced in Finland. The chemical composition of slag is given in *Table 4-4* and the grain size distribution in *Figure 4-11*.

The water content of slag is relatively high (30...60 % depending on the grain size distribution) because it is deposited in lagoons after the stainless steel production process. For recycling purposes the slag has to be drained, for example in piles that incorporate drainage pipes, to achieve a lower water content. After one month of drainage in the piles the water content of the slag is typically found to be around 15...25 % [15,27].

*Table 4-4: Chemical composition of a stainless steel slag [27]*

Constituent	% of weight
CaO	38,9
SiO <sub>2</sub>	24,6
MgO	10,7
Fe <sub>2</sub> O <sub>3</sub>	8,9
Cr <sub>2</sub> O <sub>3</sub>	5,7
Al <sub>2</sub> O <sub>3</sub>	5,0
TiO <sub>2</sub>	1,2
MnO <sub>2</sub>	0,9
NiO	0,7
C	0,6
S	0,1
MoO <sub>3</sub>	0,09
Cr <sup>6+</sup>	0,0005

The slag alone cannot be recycled in any soil construction application. For example, the slag is not a cementing material as such, it is susceptible to large amounts of frost heaving and it contains relatively large quantities of soluble heavy metals. However, the technical and environmental properties of slag can be significantly improved with dry FA and binders [15]. From a geotechnical and environmental standpoint it has been shown that the best binder is a mixture of blast furnace slag with cement (MC, 1:1).

Various studies have shown that the best methods to improve the soil construction properties of slag are stabilisation with MC, dry FA or a mixture of these. *Figure 4-12* shows test results on the different alternatives after 28 days stabilisation. The strength development of the stabilised slag will be surprisingly high even after a month of stabilisation, as shown in *Figure 4-13*. After aging for about three months, the strength might still increase as much as an additional 50 % above the one-month strength. Thus, the properties of stabilised slag have proved to be quite promising. *Table 4-5* lists the results of geotechnical tests on some stabilised slag mixtures.

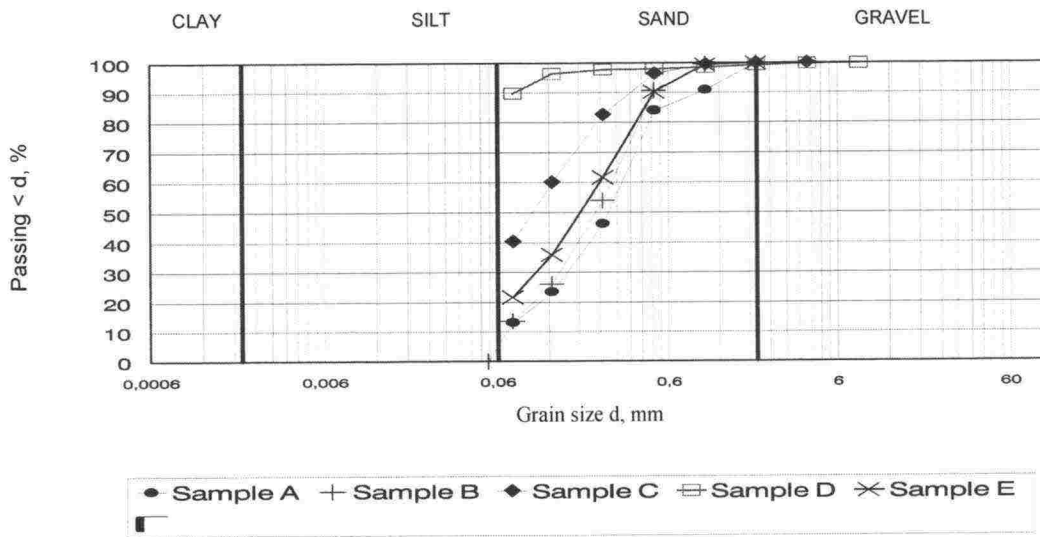


Figure 4-11: Grain size distribution of a stainless steel slag; 5 batches [15]

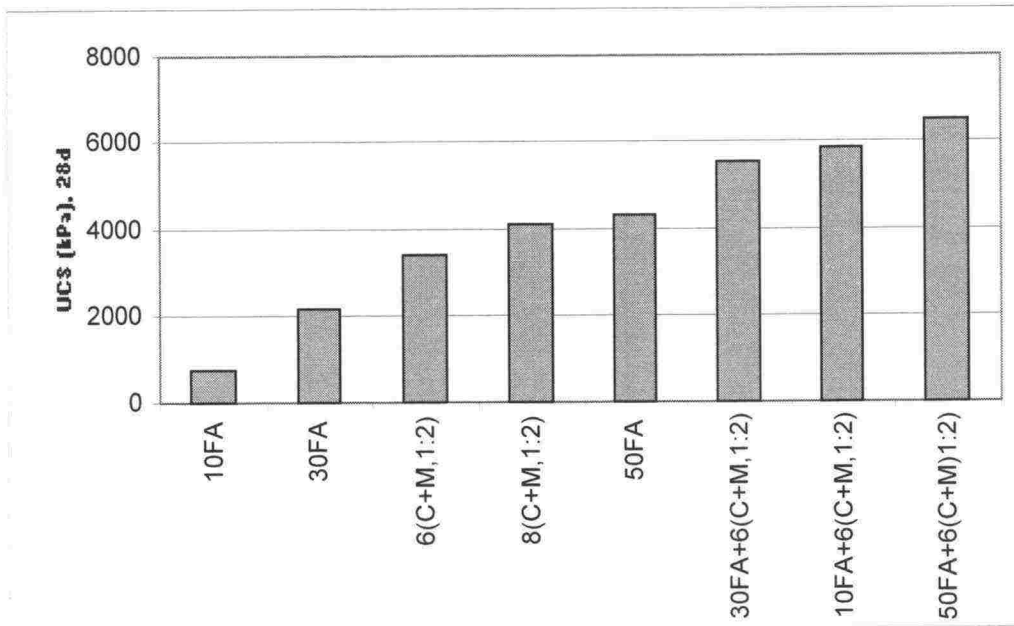


Figure 4-12: Improvement of slag with CM, FA and CM+FA. C=cement, M=blast furnace slag, FA=MFA [15]

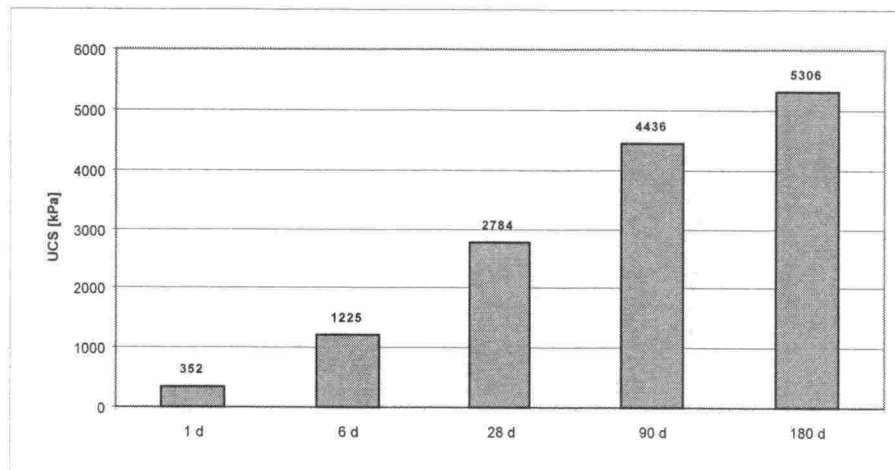


Figure 4-13: Strength development of a CM-stabilised slag (6% CM, 1:2) [15]

Table 4-5: Properties of stabilised fibre-ash, gypsum-ash and slag-ash [15]

NRC mixture	Geotechnical properties							
	Water content	Bulk density	UCS and deformation				Thermal conductivity	Segregation potential
			w <sub>o</sub> [%]	ρ [kg/m <sup>3</sup> ]	28d			
	σ <sub>u</sub> [kPa]	ε <sub>u</sub> [%]			σ <sub>u</sub> [kPa]	ε <sub>u</sub> [%]	λ [W/mK]	SP <sub>o</sub> [mm <sup>2</sup> /Kh]
(FS1+MFA 2:10) + 6Ce	51	895	600-700*	>10	n/a	n/a	n/a	≈1
(FS2+MFA, 45:55) + 7Ce	65	855	600*	>10	n/a	n/a	n/a	> 1
(FS3+WFA, 10:3) + 5Ce	56	810	300-400*	>10	n/a	n/a	n/a	>> 2
(FS4+CFA, 10:4) + 14(FGD+Ce, 2:1)	42	1060	760-770	5,5	n/a	n/a	0,58 <sup>+22°C</sup> 0,89 <sup>-10°C</sup>	0.6-0.8
(G + 10MFA) + 3(M+Ce, 7:3)	18,6	1370	614	3,5	1120	2,5	n/a	n/a
(G + 10MFA) + 4(M+Ce, 7:3)	18,6	n/a	942	3,5	1880	1,8	n/a	1,2
(G + 10MFA) + 5(M+Ce, 7:3)	18,6	1366	1092	n/a	2760	1,6	n/a	n/a
(G + 10MFA 10%) + 6(M+Ce, 7:3)	n/a	n/a	1642	2,5	3088	1,5	0,58 <sup>+22°C</sup> 1,41 <sup>-17°C</sup>	1,1
S + 10MFA	9,3	2200	726	2,3	n/a	n/a	n/a	n/a
S + 10MFA+ 6Ce	9,3	2158	6484	2,2	n/a	n/a	n/a	n/a
(S + 10MFA) + 2(M+Ce, 2:1)	8,9	n/a	1219	1,7	n/a	n/a	n/a	0,02-0,12
(S + 10MFA) + 3,5(M+Ce, 2:1)	8,9	n/a	1843	1,6	n/a	n/a	n/a	< 0,1
(S + 10MFA) + 5(M+Ce, 2:1)	8,9	n/a	2982	1,3	n/a	n/a	n/a	< 0,1
(S + 10MFA) + 6(M+Ce, 2:1)	9,3	n/a	5852	1,3	n/a	n/a	n/a	n/a
S + 30MFA	8,9	2160	2158	1,6	n/a	n/a	n/a	0,1-0,12
S + 30MFA + 6Ce	8,9	n/a	8215	1,0	n/a	n/a	n/a	n/a
S + 30MFA + 6(M+Ce, 2:1)	8,55	2070	5526	1,3	n/a	n/a	n/a	n/a
S + 30MFA + 6M	8,9	n/a	4613	1,4	n/a	n/a	n/a	n/a
S + 50MFA	11	2100	4291	1,3	n/a	n/a	n/a	n/a
<b>Note:</b>								
FS1	Pulp-based sludge							
FS2	De-inking sludge							
FS3	De-inking sludge							
FS4	Wood-based sludge							
*)	UCS at ε=10%							

#### 4.4 FA as binder

Dry and reactive FA can often be used as a component in binder mixtures. In the international project EuroSoilStab different FA types have been studied for the stabilisation of peat, gytja and clay [5] [III]. In addition, it has been proven that it is feasible to use FA for the renovation of old gravel roads structural courses [15].

##### 4.4.1 Stabilisation of soft soil

During the EuroSoilStab project there have been studies on the use of four different FA types for the stabilisation of soft soil. The properties of the FA are given in *Table 4-6*.

*Table 4-6: FA in EuroSoilStab studies [5]*


CFA from	Content [%]										Specific weight [kg/m <sup>3</sup> ]	Specific surface [m <sup>2</sup> /kg]
	CaO	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	MgO	K <sub>2</sub> O	Na <sub>2</sub> O	MnO	PsO <sub>5</sub>	LoI		
Finland	5,8	43,8	22,2	8,4	2,8	2,2	1,2	0,09	0,68	11,3	2390	459
Sweden	22,3	25,1	16,3	5,0	13,4	1,1	0,64	0,14	0,80	8,6	2740	339

*Figures 4-14...4-16* compare the effects of different CFA based binder mixes on different peat, gytja and clay materials. *Figure 4-14* shows that the effect of binders is different on the clay materials from different depths as the properties of clay are different. At this site, the clay from a deeper soil layer cannot be stabilised as effectively as the clay from the upper layer. This is often the opposite. *Figure 4-17* shows the results of a study on the effect of CFA quantity on soft soils [5].


The FA-based binders are not appropriate for all types of soft soils. The studies indicate that soft soils that can be cement-stabilised and yield good results also benefit from the use of FA based binders. For peat stabilisation, the largest economical benefits can be obtained by using mixtures that require relatively large quantities of binder. *Table 4-7* presents information about the properties of two different peat types that have been stabilised with a FA mixture [5].

The test results indicate that cement or a portion of lime can be compensated with FA in cases where the soil can be stabilised with FA. In general, however, with an equal amount of binder the strength of the FA-stabilised soil will be a little lower than the strength of the cement- or lime stabilised soil. Because of the lower price of FA, it is generally economical to increase its amount in the mixture. An increase in the amount of FA is technically advantageous, as can be seen in *Figure 4-17*, which shows an increase in strength with increasing amount of FA.



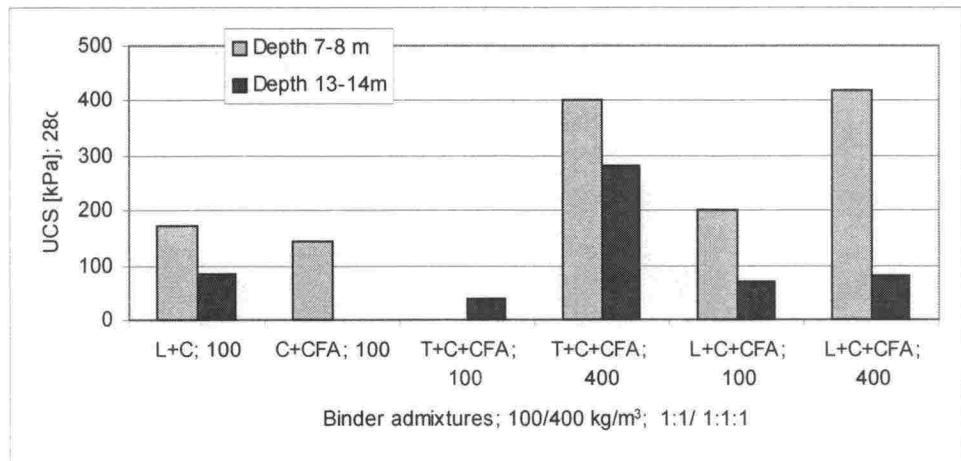

a.

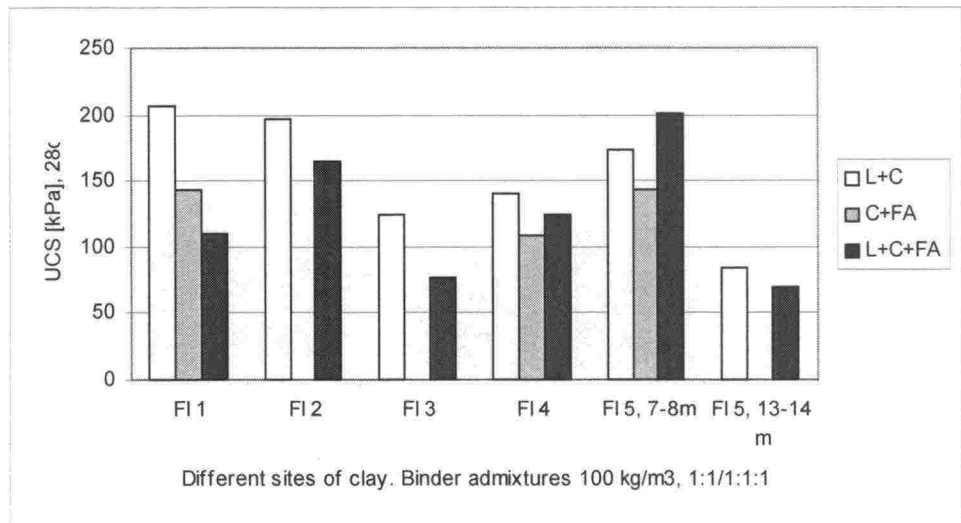

b.

Figure 4-14: Comparison of the effect of different CFA-based binders on clay a) clay from one site at two depths, b) clay from different sites [5]

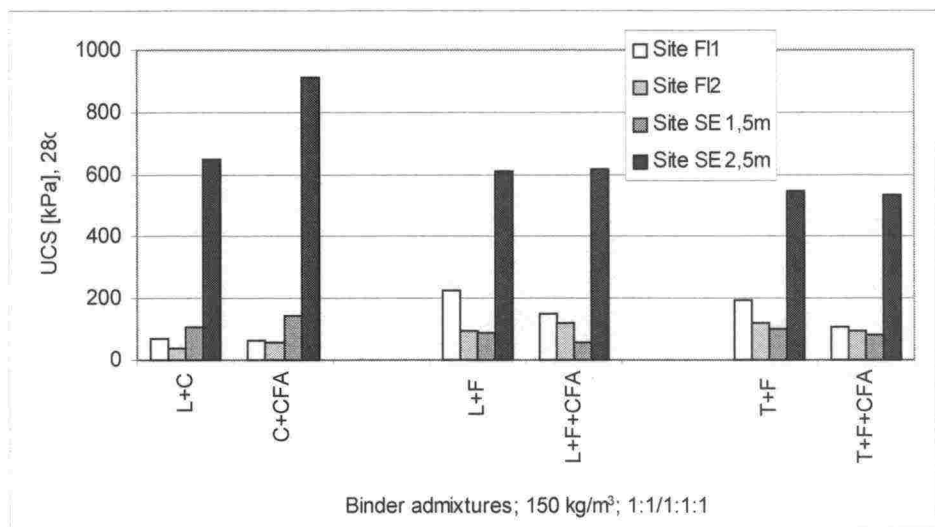


Figure 4-15: Comparison of the effect of different CFA-based binders on gytja [5]



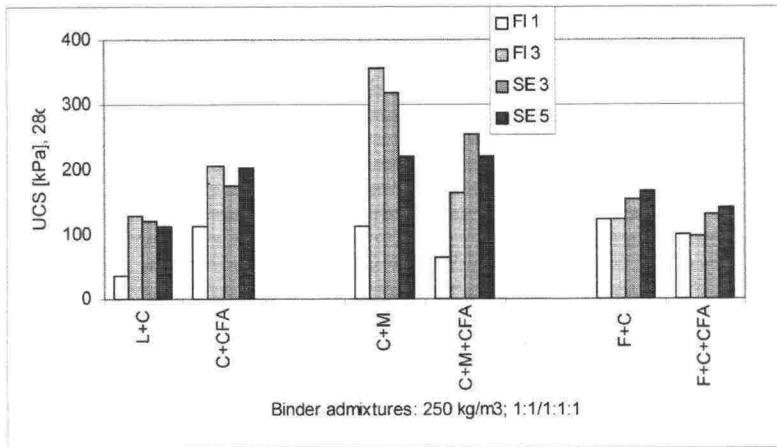


Figure 4-16: Comparison of the effect of different CFA-based binders on peat [5]

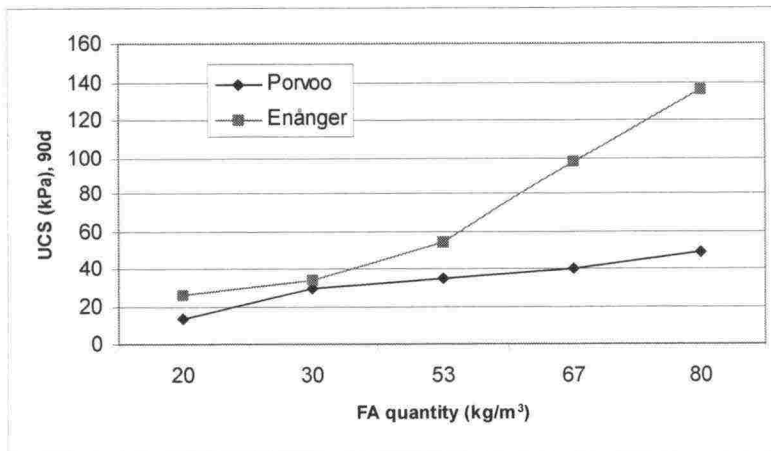

a) gyttja

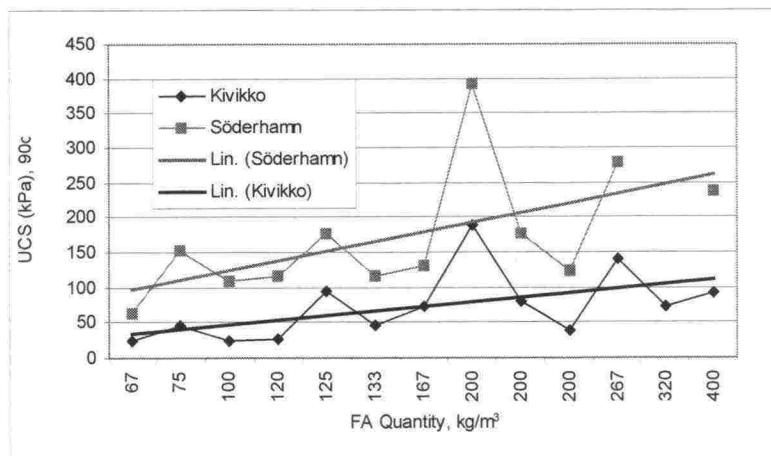

b) peat


Figure 4-17 Effect of CFA quantity on the strength of soft soils, a) gyttja and b) peat (Lin. = linear regression) [5]

Table 4-7: Properties of two peats stabilised with CFA mixtures [5]

Source of peat	Binder mixture / quantity (kg/m <sup>3</sup> ) / stabilisation time (d)	Bulk density $\rho$ [kg/m <sup>3</sup> ]	Unconfined compression test		Water permeability
			$\sigma$ [kPa]	$\epsilon$ [%]	Rigid wall test k [m/s]
Finland	Ce+FA/250/28	1001-1010	97,0	3,7	6,15E-08
	Ce+FA/250/90		94,3	3,6	7,20E-08
Sweden	Ce+FA/250/28	1023	143,9	3,5	n/a
	Ce+FA/250/90		177,3	3,0	n/a

#### 4.4.2 Stabilisation of old road structures

The studies on the stabilisation of old road structures concentrated on badly frost-damaged sites that are a part of the low-volume road network in Finland. The damaged road sites have relatively thin structural courses that partly have been mixed with the subsoil. Because of frost heave and freezing-thawing cycles repeating each year, the courses of this type of road structure usually soften and weaken with time, as the fines of the subsoil will be pumped into the structural course, and the structural course sinks into the subsoil. Stabilisation of the structural course should effectively prevent this kind of damage of the road.

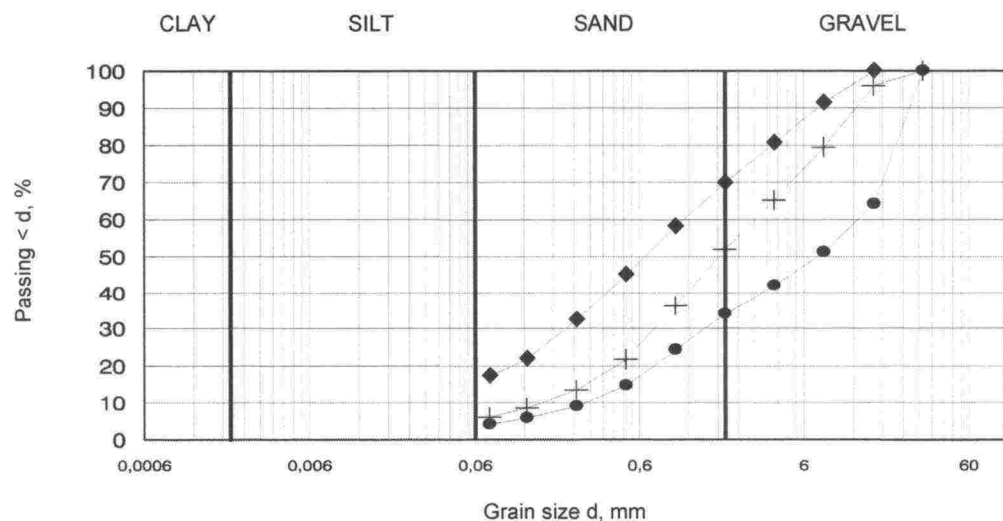

6 = below > 5m / ⊥ = below 0-5m / ! = above the stab. course

Figure 4-18: Grain size distribution of materials of an old road structure examined for NRC-stabilisation [15]

The NRC-materials for stabilisation should have a grain size distribution similar to moraine deposits, as the suitability of a NRC-binder mixture depends on the amount of fines in the moraine deposit, which has to be stabilised. For this doctoral thesis, NRC-stabilisation of old road structures have been studied only on materials having grain size distribution such as in Figure 4-18 [15].

Figure 4-19 shows results that have been obtained with FA-based binders used in the stabilisation process. The best binder components for FA were cement, blast furnace slag (M) and gypsum. Figure 4-19 shows the effect of binder quantity on the strength and Figure 4-21 shows the effect of stabilisation time. Table 4-8 gives information about the geotechnical properties of the old NRC-stabilised structures when using FA-based binders [15]

The test results have shown that the feasibility of FA-based binder mixes for moraine-type materials also depends on the properties of moraine itself, e.g. on its grain size distribution. In the best cases it is possible to obtain quite high strengths (5-7 MPa / 28d) with relatively small binder quantities (5-7 %). Also the strength development of FA-stabilised soils is significant during a longer time period. Figure 4-21 shows that the strength may double or more between the 1<sup>st</sup> and 3<sup>rd</sup> months of stabilisation.

Primarily, the FA-based stabilisation of old road structures is used to improve the bearing capacity. FA-based stabilisation is not used to improve the frost susceptibility, although Table 4-8 indicates that the thermal conductivity of FA-stabilised structures might be a little smaller than the thermal conductivity of crushed stone in general,  $\lambda$  (crushed stone) > 0,89 W/Km.

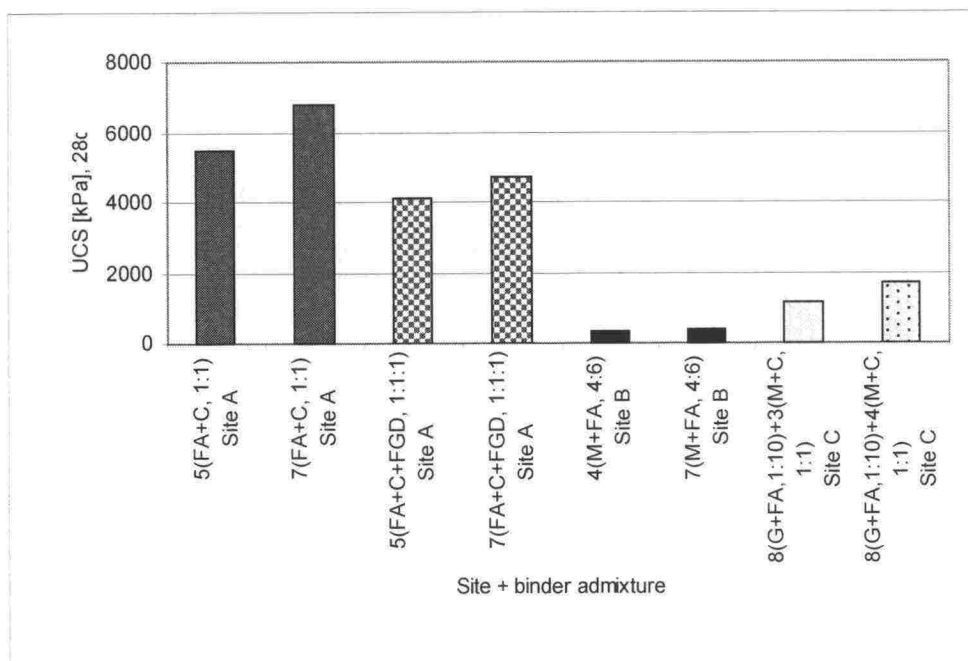


Figure 4-19: Strength of three different soil materials after stabilisation with FA-based binders: CFA for sites A and B and PFA for site C [15]



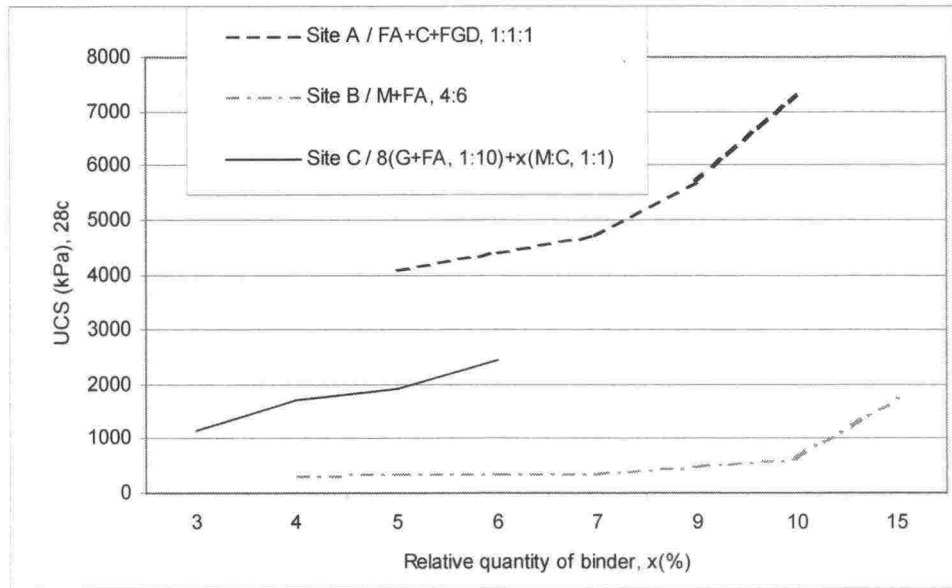


Figure 4-20: Effect of binder quantity on the strength [15]

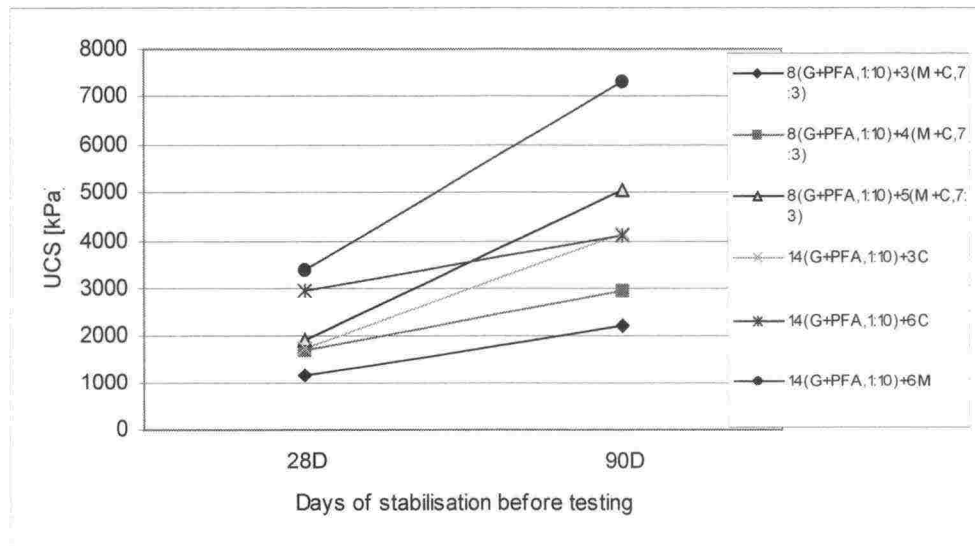


Figure 4-21: Effect of stabilisation time on the strength of grushed stone stabilised with mixes of gypsum (G), fly ash from peat combustion (PFA), blast furnace slag (M) and cement (C) [15]

Table 4-8: Geotechnical properties of old NRC-renovated (stabilised) road structures [15]

Stabilised structure material	Binder	Water content	Bulk density	UCS and deformation, 28d		Thermal conductivity
		w <sub>o</sub> [%]	ρ [kg/m <sup>3</sup> ]	σ [kPa]	ε [%]	λ [W/Km]
CS A	15(CFA+M, 6:4)	6,2	2080	1700	1,2	n/a
CS A1	15(CFA+M, 6:4)	7,0	2180	400-1200	n/a	n/a
CS B	7 (CFA+FGD+Ce, 1:1:1)	5,5	2260	4400-4700	1,0...1,4	n/a
CS C	14(G+10PFA) + 6(M+Ce, 7:3)	7,1	2070	3367	2,0	0,72 (+22°C); 1,23 (-17°C)
CS C	8( G+10PFA) + 6(M+Ce, 7:3)	6,9	2075	3292	1,3	n/a
CS C	8(G+10PFA) + 4(M+C, 7:3)	6,7	2080	1708	1,6	n/a

**Note**

- CS A, A1 Crushed stone structure from site A; A = laboratory tests, A1 = tests on samples from the full-scale test structure
- CS B Crushed stone structure from site B; laboratory tests
- CS C Crushed stone structure from site C; laboratory tests

**4.5 Long-term stability of materials**

The principles and methodologies described in Chapter 3 have been used to study the long-term durability of the materials. All materials have been tested for the following factors that are essential for road construction materials; water retention capacity, frost susceptibility, frost resistance and freeze-thaw durability. A few materials have also been tested to study the effects of infiltrating water or acid water. Additionally, materials containing fibre sludge have been tested to determine their biodegradability. Dynamic load durability has been studied only in test structures at full-scale test sites.

**4.5.1 Water resistance, frost resistance and freeze-thaw durability**

Different FA mixtures have been tested for water resistance, frost resistance and freeze-thaw durability, and the results have been compared with the strength of corresponding mixtures that have been stored at normal room temperature (18-21°C) without external fatigue load. *Figure 4-22* presents the results for FA, *Figure 4-23* the results for fibre-ashes, *Figure 4-24* the results for gypsum-ashes and *Figure 4-25* the results for slag-ashes [5,15].

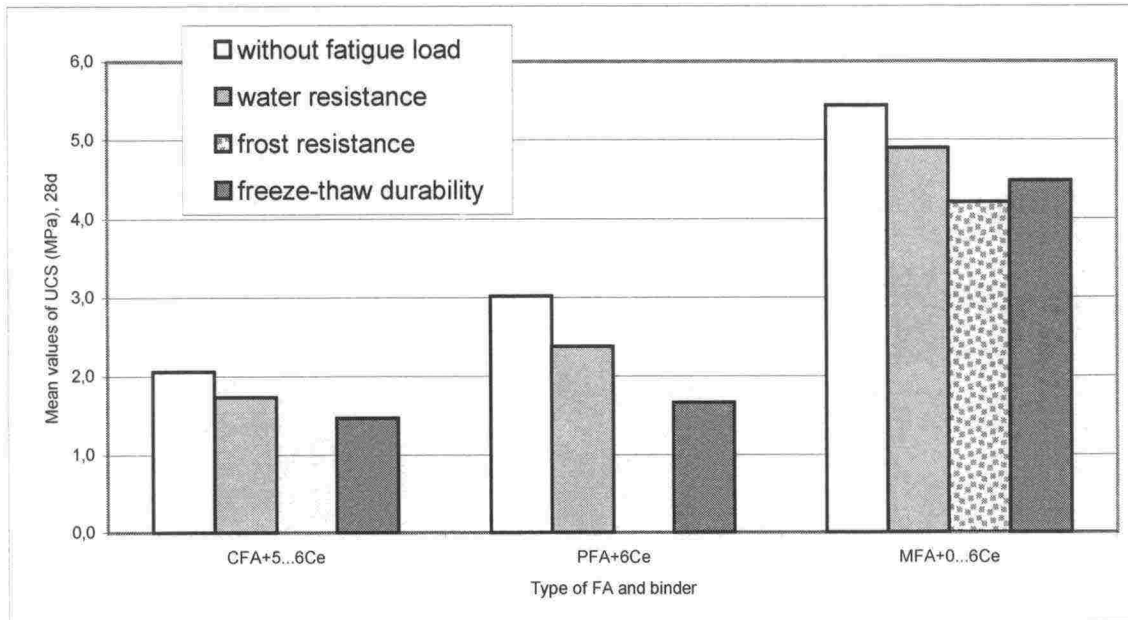


Figure 4-22: Water resistance, frost resistance and freeze-thaw durability of different FA-types. Mean values of test results. [5,15]

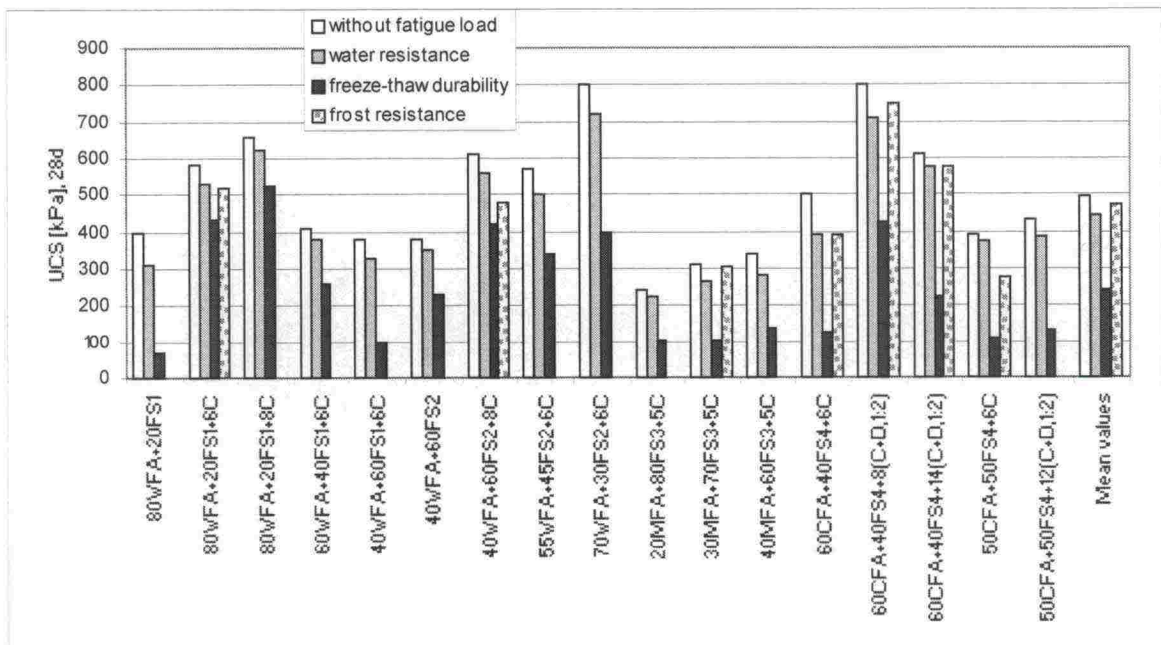


Figure 4-23: Water resistance, frost resistance and freeze-thaw durability of different fibre-ashes: FS = fibre sludge, WFA/MFA/CFA = different types of fly ash, C = cement, D = desulphurisation residue [15]

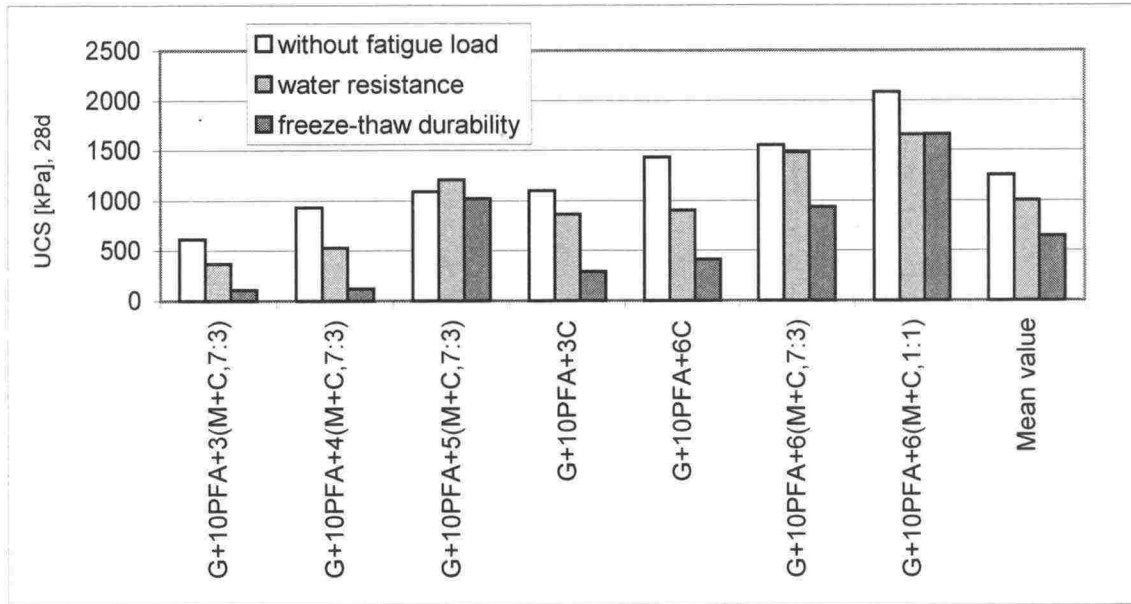


Figure 4-24: Water resistance, frost resistance and freeze-thaw durability of different gypsum-ashes: G = phospho-gypsum, PFA = fly ash from peat combustion, C = cement, M = blast furnace slag [15]

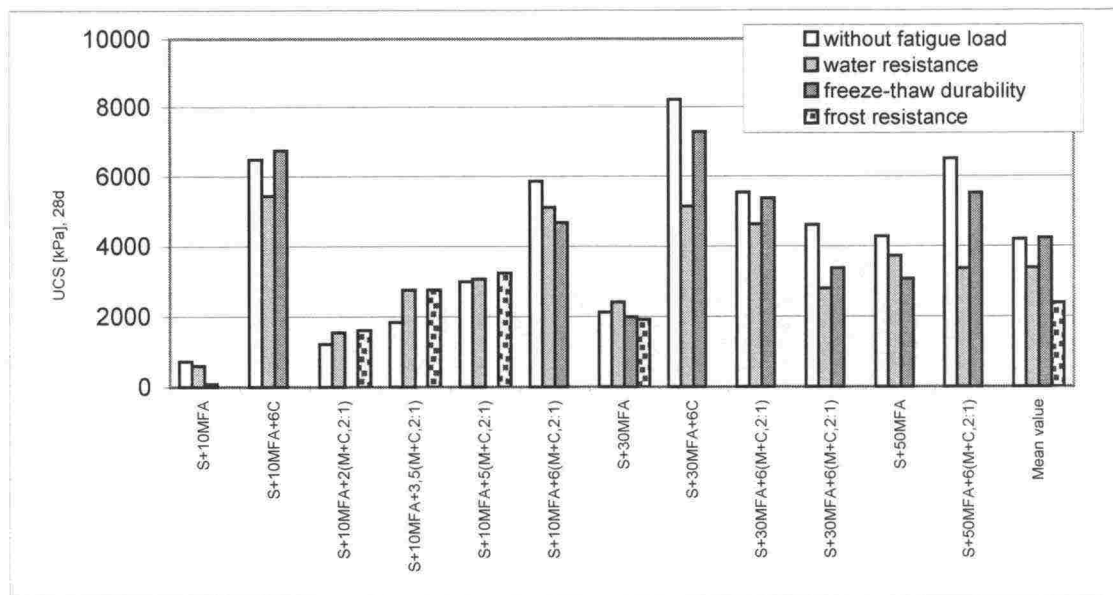


Figure 4-25: Water resistance, frost resistance and freeze-thaw durability of different slag-ashes [15]

The fatigue tests on NRC-materials are important for the determination of their suitability in geotechnical applications. According to Figures 4-22 ... 4-25 the UCS of a material does not correlate well with the material's frost resistance or freeze-thaw durability. A material having a high UCS value might have inadequate freeze-thaw properties, and vice versa.

In general fatigue tests result in decreasing strength of the material with increased number of cycles; a slight decrease in the water retention test, slightly more in the frost susceptibility test and the largest decrease in the freeze-thaw test. The stabi



lised FA presented in *Figure 4-22* have exhibited quite good durability when subjected to different fatigue loads, and their strength decrease has been moderate. Many of the SGT's studies [15] have shown that moist pile-FA requires binder to obtain adequate freeze-thaw durability. When using dry FA the need for binder is less and in some cases no binder is required.

Fibre-ash mixes based on pile-FA always require some binder in order to obtain adequate freeze-thaw durability as shown in *Figure 4-23*. For example, UCS of the material mix 80WFA+20FS1 was 400 kPa, as the material was not subjected to any fatigue load, while its UCS was only 80 kPa after the freeze-thaw test. Increasing the relative amount of ash in fibre-ash mixtures will increase the material's strength (UCS). *Figure 4-23* also indicates, that fibre-ash materials from different producers may clearly differ from each other in strength, despite the use of same binder and equivalent component proportions in the mixtures. For example, the mixtures 60WFA+40FS1+6C, 55WFA+45FS2+6C and 60CFA+40FS4+6C all had 6 % cement as binder, but the UCS varied between 410 kPa and 570 kPa after no fatigue load, and even more, between 120 kPa and 330 kPa, after the freeze-thaw test. Additionally, the same figure indicates, that the larger the share of fibre sludge in the mixture, the more binder will be needed, in order to achieve adequate freeze-thaw durability for a fibre-ash material. For example, 6 % cement for the mixture 40WFA+60FS1 was not sufficient, as the UCS decreased from 380 kPa to 200 kPa (about 50 %) during the freeze-thaw test. On the other hand, 8 % cement for the same mixture was sufficient, as the UCS decreased only about 30 %, from 610 kPa to 420 kPa during the freeze-thaw test. Finally, the results shown in *Figure 4-23* indicate, that it might be feasible to compensate part of cement with some suitable industrial residue. For example, as 6 % cement in the mixture 60CFA+40FS4+6C was compensated with 8 % of a binder mixture C+D (one part of cement with 2 parts of flue gas desulphurisation residue), the UCS (after no fatigue load) improved from 500 kPa to 800 kPa, and the UCS (after freeze-thaw test) from 120 kPa to 420 kPa.

When using dry FA the need for binder is often non-existent or clearly smaller than when using FA alone. The fatigue durability of fibre-ash materials essentially depends on the quality and proportion of the components (FA and FS) and on the quality and quantity of the binder. Therefore, to obtain adequate geotechnical properties for fibre-ashes, the mix optimisation is significantly more demanding than in the cases of pure FA materials. As shown in *Figure 4-23* there is a poor correlation between the UCS and the freeze-thaw durability of fibre-ashes. This fact emphasizes the importance of freeze-thaw tests on fibre-ash mixtures.

Gypsum-ash mixtures, when mixed with pile-FA, require binder to obtain adequate freeze-thaw durability. In addition, with gypsum-ash mixtures a dry FA may decrease the need for a binder or even eliminate the need for a binder. *Figure 4-24* shows that adequate freeze-thaw durability can be achieved with the right choice of binder, and with a binder quantity that exceeds a threshold value. In these cases the best binder was a mixture of blast-furnace slag (M) with cement (C) in a proportion of 1:1. The threshold quantity of the binder in that case was 3-5 %, since with 3 % of binder the freeze-thaw durability was far too low, but with 5 % it was excellent. Slag-ash mixtures have exhibited excellent durability values. *Figure 4-25* indicates that the durability of these materials will be very good even with 10 % of FA and 2 % of binder (MC, 2:1), or with only 30 % of FA. This indicates that there is no need for binders when using an adequate quantity of FA.

### 4.5.2 Frost susceptibility

Frost susceptibility can be determined by utilising segregation potential, a parameter that has been determined for each material (shown in *Table 4-9*). The table also presents existing guidelines for frost susceptibility [5,15,28].

*Table 4-9* refers to studies that have been conducted using pre-moisturised or imitated pile-FA, and dry FA. It has been observed that the segregation potential  $SP_o$  is smaller in materials based on dry FA than in pile-FA materials. There is also correlation between  $SP_o$  and frost resistance [15]. It can also be observed that if the  $SP_o < 0,2$  the frost resistance of the material will be very good, and if the  $SP_o \geq 0,5$  the frost resistance of FA materials (except fibre-ashes) can be critical. In the case of fibre-ashes the critical limit can be as high as  $SP_o = 1,0$ . As a rule, the higher the  $SP_o$  the weaker the frost resistance of a material.  $SP_o$  can be decreased (improved) with the use of binders. In fibre-ashes the  $SP_o$  can be improved by increasing the quantity of FA and binder. The  $SP_o$  of gypsum-ashes can be improved by increasing the quantity of binder. The  $SP_o$  of slag-ashes will be very small even when small quantities of binder and FA are utilised.

*Table 4-9: Frost susceptibility (segregation potential) of different materials*

Materials tested		Segregation potential, $SP_o$ [mm <sup>2</sup> /Kh]	Evaluation
FA	FA + 15 %D + 3...5 % BI	< 0,1	not susceptible
	FA + 3...7% BI	0,1 – 0,6	slightly susceptible
Fibre-ashes	FS + 20...40%FA + 3...9 %BI	0,11 – 0,59	slightly susceptible
	FA + 20...100% FS + 6...14%BI	0,5 – 2,0	slightly susceptible / susceptible
Gypsum ashes	G +10%FA + 4...6%BI	1,0-1,2	slightly susceptible / susceptible
Slag – ashes	S +10...50%FA + 6% BI	< 0,1	not susceptible
Abbreviations		Guidelines [28]	
FA	Fly ash (CFA, MFA, PFA)	< 0,18	not susceptible
BI	Binder (cement, lime and their mixes)	0,18 – 0,72	slightly susceptible
D	Desulphurisation residue	0,72 – 3,6	susceptible
		> 3,6	strongly susceptible

### 4.5.3 Biodegradability

Fibre-ashes contain organic material, i.e. fibres. No previous studies were found dealing with the biodegradability of these mixes, e.g. for road applications. Full-scale test structures yield information about this aspect, but there is a need for laboratory testing as well.

The biodegradability of fibre sludge has been studied utilising OECD Method 301F (OECD Guideline 1992). Method 301F is a Manometric Respirometry Test that is being applied in the laboratory of Envitop Oy in Oulu. Degradation is followed by the determination of BOD (Biological Oxygen Demand) as a portion of the COD (Chemical Oxygen Demand). Thus, biodegradation is expressed as BOD/COD (%). The acceptable level for characterising readily biodegradable material (rapid biodegradation in an aquatic environment under aerobic conditions) is 60 % in 28 days. Values less than 60 % indicate that the materials cannot be considered readily biodegradable. In general, the biodegradability of fibre sludge or its mixes with FA has been less than 60%, i.e. typically 18 ... 58 %. (Envitop Oy, Oulu).

### 4.6 Environmental impacts

The environmental impact of FA and FA mixes in soil structures can probably be best determined by the release of environmentally harmful and soluble constituents from the material into the soil and groundwater over long periods of time. For this doctoral thesis environmental impacts have been determined from tests using the methodology described in Chapter 3, i.e. the leaching tests performed according to the Dutch standards NEN 7343 (column test). Table 4-10 presents the test results on the materials [5,15].

Table 4-10: Results of column test (NEN 7343) on FA materials. [5,15]

Materials	Constituent [mg/kg (L/S10)]											
	As	Cd	Co	Cr	Cu	Mo	Ni	Pb	Sb	Se	V	Zn
CFA1						<b>3,96</b>						
CFA2	0,015	0	0,355	0,553	0,04	<b>4,895</b>	0,03	0,151	0,021	<b>1,125</b>	0,355	<b>1,549</b>
PFA1	0,021	0,008	0,001	0,113	0,001	<b>4,96</b>	0,002	0,001	0,006	<b>0,183</b>	1,28	0,08
PFA2	0,04	0,004			0,01		0,11					0,76
PFA3	<b>0,159</b>			0,185		<b>0,362</b>	0,016	0,005			1,095	
		<0,00			<0,00							
MFA1	0,11	0,006	0,003	0,102	0,22	<b>0,407</b>	0,01	0,022	0,002	<b>0,5</b>	0,02	0,84
MFA2	<b>0,24</b>	<b>0,02</b>	0,02	1,446	0,214	<b>1,952</b>	0,059	0,048	0,021	<b>4,927</b>	0,058	0,60
WFA1+3Ce	<b>0,145</b>	<b>0,025</b>	0,02	1,182	0,236	<b>4,358</b>	0,06	0,093	0,021	<b>5,0</b>	0,216	0,447
Slag (without ash)	0,002	<b>0,029</b>	<0,00	<b>3,2-8,9</b>	0,04-0,1	<b>23-43</b>	0,02-0,1	0,08	0,002	0,05	0,003	0,03
Slag-ash (30 % MFA)	<0,02	0,010	<b>0,01</b>	0,63	<0,02	<b>5,66</b>	<0,04	0,08	<0,02	<0,5	<0,02	0,33
Fibre-ash	0,06	0,001	0,016	0,005	0,002	0,001	0,28	0,001	0,001	0,008	0,026	0,007
<b>Guide values [31]</b>												
Group 1	0,14	0,011	1,1	2,0	1,1	0,31	1,2	1,0	0,12	0,06	2,2	1,5
Group 2	0,85	0,015	2,5	5,1	2,0	0,50	2,1	1,8	0,40	0,098	10	2,7
Group 1: Recycled material layers have to be covered (e.g. with crushed stone) to prevent the transport of material particles into the environment, or any human or animal to come into direct contact with the material. Figures exceeding these values are marked with bold letters												
Group 2: Water infiltration through the recycled material layer must be prevented by asphalt or other impermeable pavement. Figures exceeding these values are marked with bold letters + underlines. In this case a specific risk analysis is required.												

Table 4-10 includes the guide values that have been suggested by the Finnish Environment Centre [31]. Many of the suggested guide values are stricter than the Dutch guide values on which the suggested ones are based. The guide values for molybdenum (Mo) and selenium (Se) are extremely strict in comparison with the practise in other countries. In general, according to several international sources, the leaching of Mo and Se from ashes is not considered an environmental risk. However, when comparing the leaching of materials in Table 4-10 with the suggested guide values it can be noted that the leaching of Mo and Se will usually exceed the guide values, except in the case of fibre-ash. The environmental impact of FA and FA-mixes will be discussed in greater detail in section 5.5.



## 5 FULL-SCALE TESTS ON NRC-STRUCTURES

### 5.1 Different types of NRC-structures

NRC-constructions differ from conventional constructions both in materials and in structures. The differences in materials and material properties were described in Chapter 3. Figures 5-1... 5-3 show the basic types and the principles of implementation for one type of NRC-solid structure (Figure 5-1), the stabilisation of old road structures (Figure 5-2) and the mass-column stabilisation (Figure 5-3) based on recycled materials.

Dozens of former structure types based on different industrial residue mixes have been tested in full scale in Finland, mainly in co-operation with SGT and the Finnish Road Administration (FinnRa). Most of the test structures involve different applications of fly ashes. Laboratory tests on fly ash mixtures for mass – column stabilisation have given promising results but, until now, all full-scale tests have been carried out with other types of industrial residues. Therefore, a more detailed discussion on mass – column stabilised structures will be excluded and Chapter 5 will concentrate on the experience and test results of NRC-solid structures and the stabilisation of old road structures.

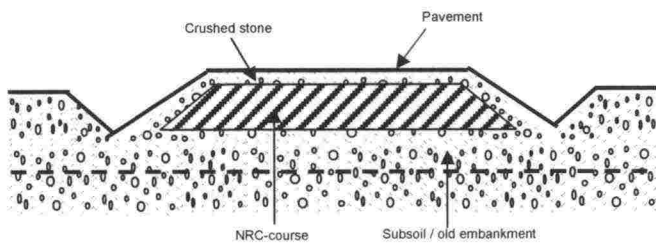


Figure 5-1: The basic type of NRC-solid structure

#### Principles of Implementation

1. Removal of the old pavement and, probably, its subsequent reuse in the new structure
2. Planing of the surface to support the road edges
3. Compaction of the subsoil/old embankment
4. Production of the NRC material course ( $\approx 200$  mm): mixing, transport, spreading and compaction
5. Spreading and compaction of the crushed stone layer (50-100 mm)
6. Paving


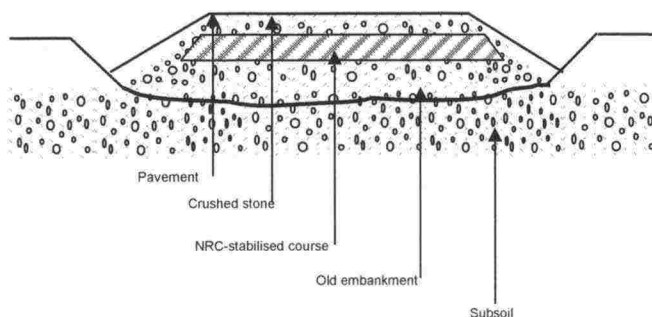


Figure 5-2: The basic type of renovation by NRC-stabilisation

#### Principles of Implementation

1. Removal of the old pavement / surface and, probably, its subsequent reuse in the renovated structure
2. Stabilisation of the old course with a NRC - binder mixture (200-250 mm)
3. Compaction after stabilisation
4. Spreading and compaction of a crushed stone course (50-100 mm)
5. Paving



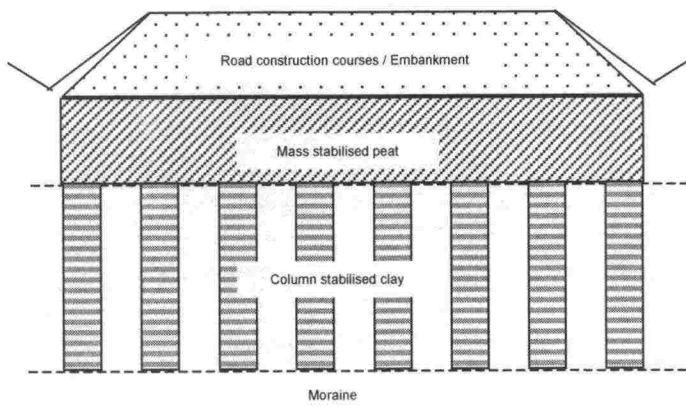

### Principles of Implementation

1. Removal of trees, stumps, stones etc. (at a new construction site) or removal of an old embankment (at an existing construction site)
2. Column stabilisation
3. Mass stabilisation
4. Construction of the embankment and other upper structures

Figure 5-3: The basic type of mass-column stabilisation

## 5.2 Test sites

Table 5-1 describes the structures, materials, time of construction and equipment tested for NRC-construction at 18 full-scale test sites that consisted of 32 different test structures [I, II, VI, V]. The NRC- materials that have been used in the test structures include different types of FA from the incineration of coal, peat, wood and miscellaneous fuel, different types of fibre sludge and one type of gypsum. The test structure types are different NRC-solid structures (23 FA – structures, 6 fibre-ash structures, 1 gypsum-ash structure) and NRC-stabilisation for the renovation of old roads at three sites. Mixtures of stainless steel slag and FA have not yet been constructed nor tested at full scale in spite of promising laboratory test results.

Table 5-1: Full-scale test sites for recycled construction [15]

TEST	SITE	YEAR	STRUC-TURE	MATERIALS	TESTED EQUIP-MENT	
FA (solid)	Pirkkala, Savontie	1992	A	MFA + 4(M + Ce, 1:2)	II	
	Luopioinen, Rajalantie	1996	A	MFA + 4(M + Ce, 7:3)	II	
	Sipoo, Knuters (I-III)		1997	A	CFA	I
				A	CFA + 25FGD	I
				A	CFA + 5Ce	I
	Koria		1998	A	MFA1 + 3Ce	I
				A	CFA + 6T	I
				A	MFA2	I
	Jämsä		1998	A	MFA1 + 4Ce	III
				A	MFA2 + 6,2Ce	III
	Laitila		1998	A	CFA + 3T	I
				A	MFA + 5T	I
	Juankoski, Vehkalahti		1999	A	MFA + 6Ce	I
				A	PFA1 + 6Ce	I
				A	PFA2 + 9Ce	I
	Mustasaari		1999	A	CFA + 6Ce	III
				A	CFA + 2CC + 4,5Ce	III
	Tornio		1999	A	MFA + 4Ce	III
A				MFA	III	
Inkoo		2000	A	CFA + 15FGD + 5L	IV	
Oulu		2000	A	PFA1 + 6,5Ce	IV	
			A	PFA2 + 7Ce	IV	
FA as Binder	Laitila	1998	B	Binder 15(CFA + M, 4:6)	V	
	Maaninka	1999	B	Binder [8(FG+10FA)+4(M+Ce, 7:3)	VI	
						Inkoo
Fibre-Ash	Luopioinen, Rajalantie	1996	A	FS + 40MFA + 5Ce	VII	
			A	FS + 20MFA + 9Ce	VII	
	Jämsä	1998	A	(FS1 + MFA1, 10:3) + 7Ce	III	
			A	(FS2 + MFA2, 45:55) + 7Ce	III	
				A	(FS3 + MFA3, 2:10) + 6,2Ce	III
Inkoo		2000	A	(CFA + FS, 10:4) + 14(FGD + Ce, 2:1)	IV	
Gypsum-Ash	Maaninka	1999	A	PG + 10PFA + 4(M + Ce, 7:3)	VI	

**Note**


<p><b>TYPE OF STRUCTURE</b></p> <p>See Figure 5-1 and 5-2  A = Solid NRC-structure  B = Renovation of old road structures by NRC stabilisation</p>	<p><b>TYPE OF EQUIPMENT</b></p> <p>I = Stationary mixing plant  II = Concrete mixer  III = "Sami"-mixer  IV = "Maamyra"  V = Milling mixer  VI = Stack mixer  VII = Screening scoop</p>	<p>Test sections in Luopioinen and Tornio have asphalt pavement. Other test sections have been covered with crushed stone.</p> <p>Abbreviations of materials: see List of Symbols</p>
--	---	---

### 5.3 Tests on recycled structures

The NRC-structures have been tested to ascertain their geotechnical behaviour and environmental impacts. The studies have involved measurements using instruments that have been installed at the test sites, tests on material samples and direct measurements of the structures.

The properties of NRC-materials have been measured as accurately as possible during construction, especially the following properties; water content; compactibility; binder quantity; proportion of components in the mixture; and the density of the final structural layer. These measurements are very important for assessing quality management during construction. They also have significance when assessing the quality of the NRC-structure and when investigating the reasons for a structure that achieved a lower quality level than originally targeted.

The test structures have been equipped with geotechnical instruments that electrically measure frost heaves, settlements, temperature and water content. Frost heaves and settlements are determined with potentiometers that have been wire-anchored below the maximum frost penetration depth. Measurements of temperature are made with thermo-elements (poles) at different depths of the structure and the sub-base. Water contents in the structure are determined with a calibrated moisture gauge measuring dielectricity. The geotechnical instruments have been installed in the test structures in a similar manner as shown in *Figure 5-4*.

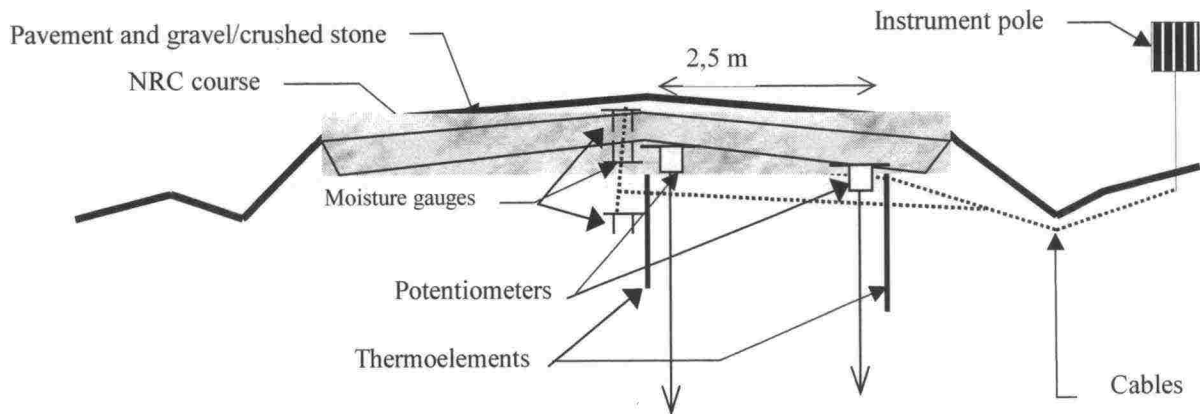

*Figure 5-4: Geotechnical instruments in the test structures*

Almost all test structures have also been equipped with groundwater pipes. The groundwater pipes have been installed a few meters off to the sides of the test structures, below the depth of groundwater flow, in order to observe the groundwater quality. Additionally, the test sites in Sipoo have been installed with lysimeters under the test structures for CFA and CFA + 25 FGD and, for comparison, under the reference structure. The lysimeters are used to determine water quality that is infiltrating through the structures. A schema of the groundwater measuring system is shown in *Figure 5-5*.

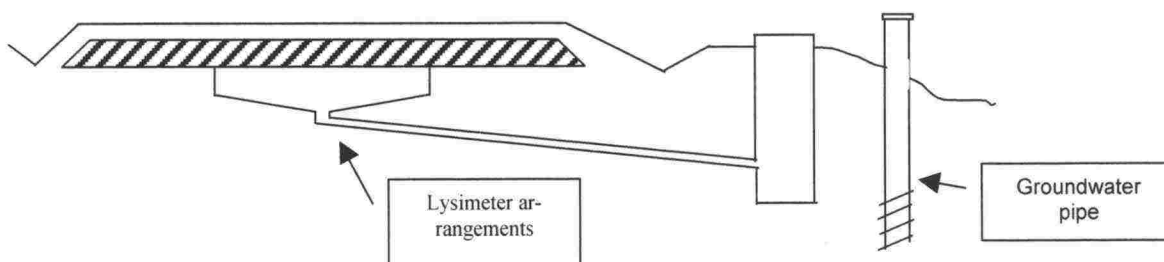


Figure 5-5: A lysimeter and a groundwater pipe. The principle of test arrangements in Sipoo

In addition to the measurements with geotechnical instruments, follow-up tests at the test sites included measurements of bearing capacity, damage observations, and studies and sampling of test pits at certain intervals. The tests on test pit samples have yielded significant additional information about the long-term behaviour and durability of materials and structures.

#### 5.4 Storage, equipment and work methods

The quality of a NRC-structure will be significantly affected by the storage of materials and by the equipment and work methods used in the construction process. In NRC-construction the following factors are the most important ones that affect the quality of the construction:

1. Storage of materials
2. Mixing of the recycled material mass
3. Mixing in the stabilisation of the old structure for renovation
4. Compaction of the NRC-structure that is preceded by properly finished subbase and edge supports.

##### Storage

The storage method has a particularly significant effect on the quality of FA. The best recycling properties can be obtained when a FA has been stored dry. The longer a moisturised material is stored the greater the amount of its reactivity that will be lost. This has been shown in the laboratory tests (see Chapter 3). At present, power stations have very little dry storage space for FA in Finland. The fact that the major part of the FA is produced during the cold winter season is an additional problem, as the FA should be stored dry for successful NRC-constructions during the warmer season (late spring – summer – early autumn). Therefore, large dry storage facilities with capacities of 10 000 m<sup>3</sup> to 100 000 m<sup>3</sup> are a most important precondition for the implementation of extensive recycling of FA in soil construction applications. Steel silos are expensive solutions, but there also exist less expensive alternatives in the world, though less known and implemented. The storage of FA is a problem because it loses its fluidity when stored (it loses its fluid powder structure and becomes compact when stored).

The full-scale research projects that have been referred to in this doctoral thesis have primarily dealt with FA that have been stored in open-air piles for differing time periods. This is because of the shortage of dry FA. Only a few test structures have been constructed with dry FA that have been transported directly from power station's production or silo to the construction site (e.g. the NRC-stabilisation sites for



the renovation of old roads). Otherwise the FA have been transported slightly pre-moisturised in truck platforms to open-air piles at temporary storage sites. The FA piles have been formed without compaction i.e. as loose as possible in order to avoid any strength development during the storage. The water content of the FA in piles would depend on wind and rain conditions. Therefore the piles have to be moisturised or covered. The length of storage varied with the capacity of the FA producer and the size of the construction project.

Storage of other residues, like fibre sludge and phospho-gypsum did not involve as many problems as the FA, because these materials inherently have high water contents. Also wetting and drying conditions do not have much effect on the properties of these materials during short-term storage.

### **Mixing of the NRC-mass**

The efficiency of the mixing equipment largely affects the quality of materials such as fibre-ash and the gypsum-ash. Other factors that significantly control the quality of NRC-materials are the precision of the component proportions and the binder quantity. Different mixing equipment have been tested during the projects involved with test construction. The equipment, as well as their weaknesses and strengths, have been described in *Figures 5-6... 5-11*.


The tests on the equipment have shown that the development of special mixing equipment for NRC-materials is a formidable challenge for the equipment manufacturers. The mixing equipment has to be economical and have a high production capacity in addition to producing high mixing quality. A stationary mixing plant will be justified only in cases where the manufacture (mixing) of NRC-material masses will take place close to the storage point. Otherwise the mixing equipment should be easily movable from one construction site to another.

### **Mixing in the stabilisation of old road structures for renovation**

The following equipment has been tested at the test sites: the Spring Harrow together with farming tractors, the Road Scraper and a special Milling Mixer for stabilisation. "Maamyra" could also be used in the stabilisation of road courses, but this has not been sufficiently tested to date.

The Spring Harrow was used in order to find a cost effective mixing method. This equipment has clear deficiencies although the properties obtained for the test structures were fairly good. A road course that will be stabilised must be well loosened with a Road Scraper before mixing. There will be dust problems before mixing because the binder has to be spread on the surface beforehand. Stabilisation will be relatively slow because the Spring Harrow must be run over the length of the construction several times to achieve a moderate outcome. Additionally it is not possible to mix the binder into the total depth of the layer (e.g. 20 cm). The maximum depth of stabilisation was 10 – 15 cm.

Also mixing results were relatively poor with the Road Scraper. The Milling Mixer operated efficiently throughout the total depth of the course, and had a fairly high production capacity. The Milling Mixer will be economical for large construction projects.

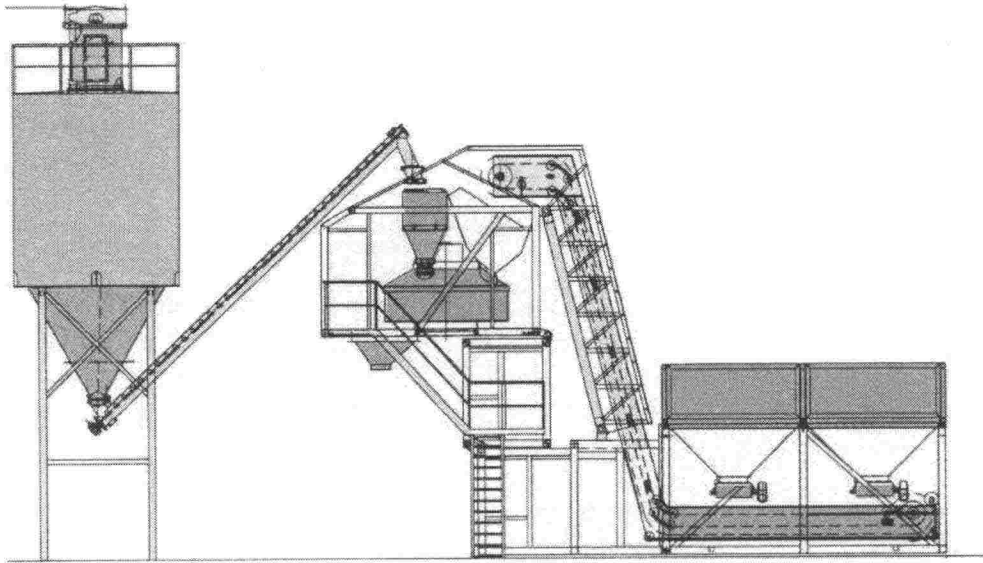

**MATERIALS AT  
 THE TEST SITE**

Stabilised FA  
 FA + FGD


**STRENGTHS**

Precise proportioning  
 High production capacity

**WEAKNESSES**

Expensive: high transfer and construction costs  
 Incompatible with fibre materials  
 Immobile

*Figure 5-6: Stationary Mixing Plant*

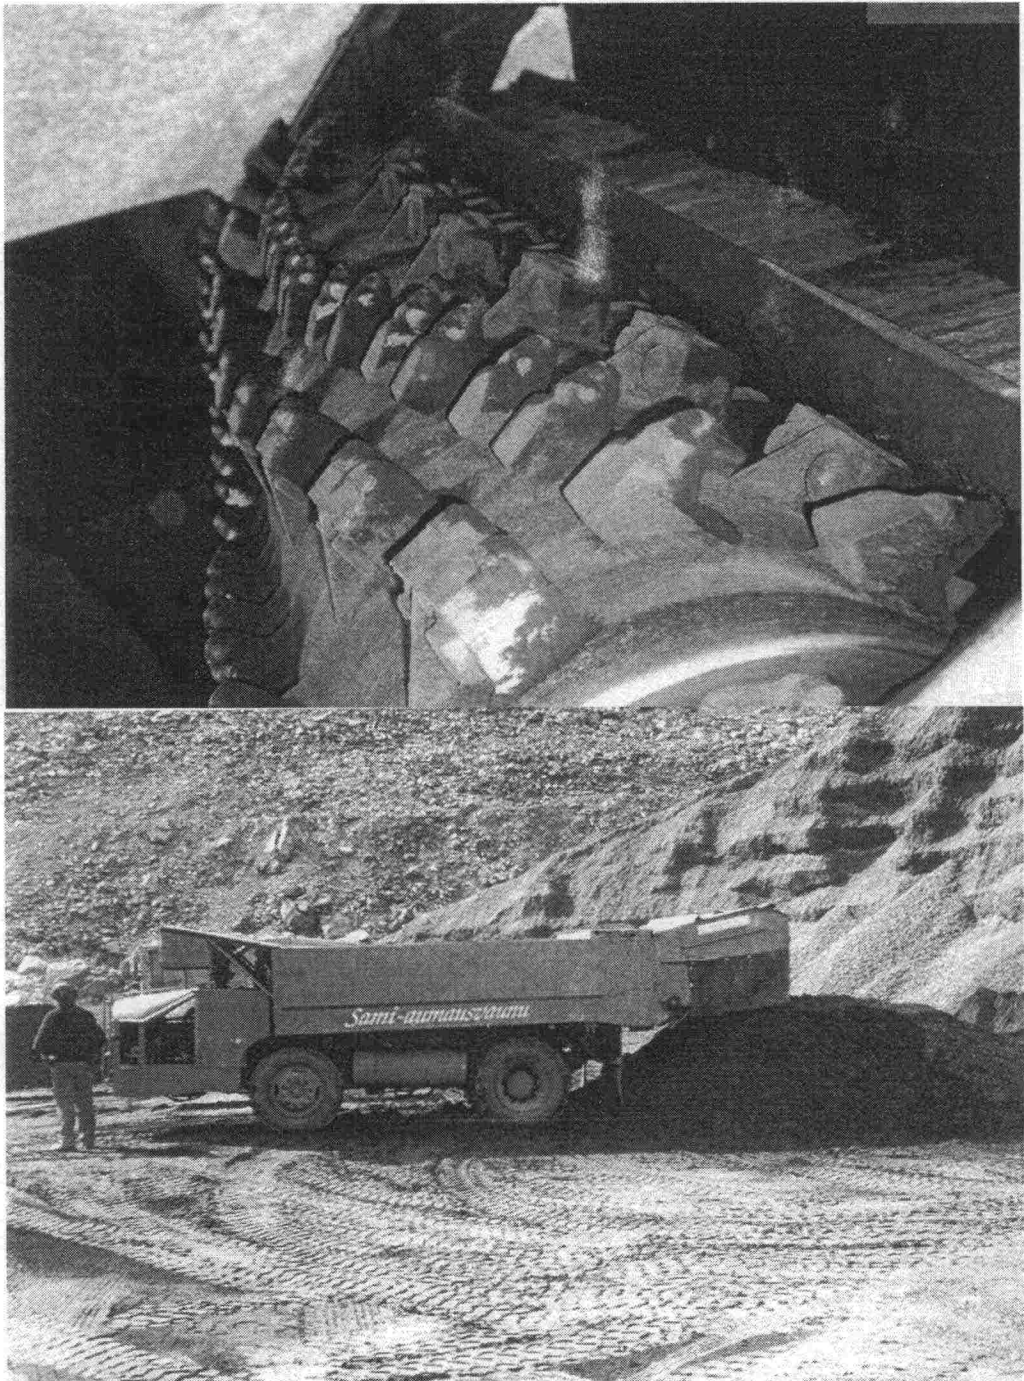

**MATERIALS AT  
THE TEST SITE**

- Fibre-ash
- Stabilised FA

**STRENGTHS**



- Low costs
- Moderate production capacity
- Fair mixing results with fibre sludge

**WEAKNESSES**

- Inaccurate proportioning
- Dust problem

Figure 5-7: "SAMI"-Mixer



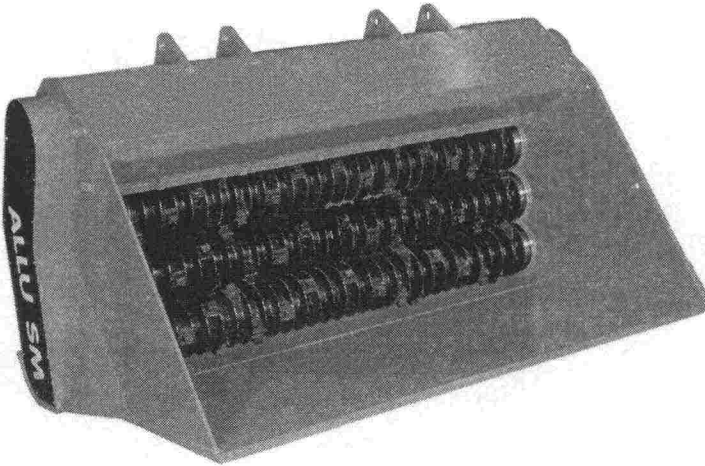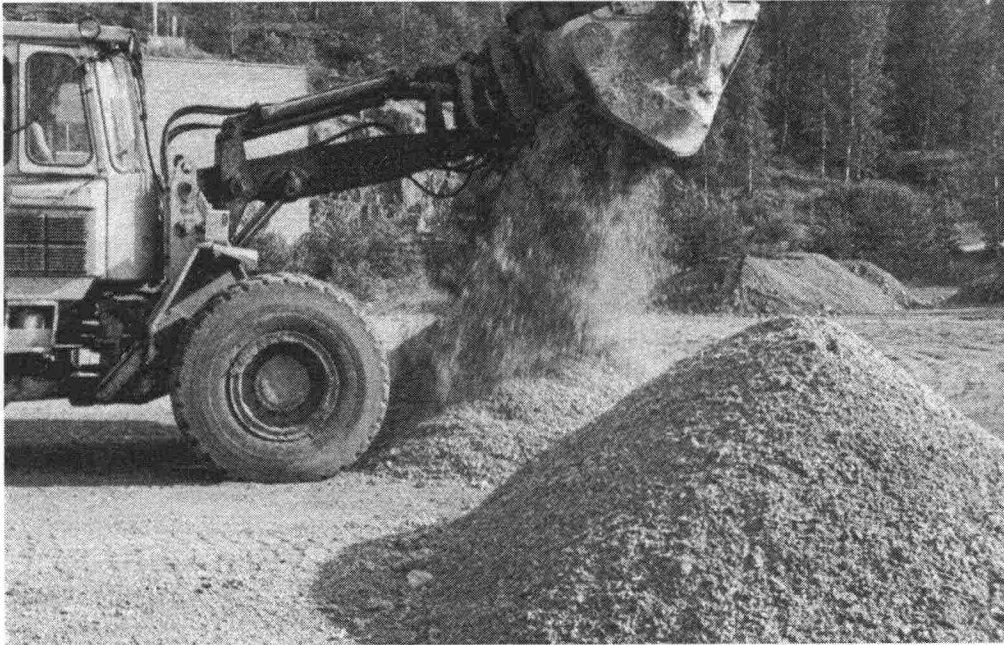

**MATERIALS AT THE  
TEST SITE**

- Fibre-ash

**STRENGTHS**

- Low costs
- Moderate production capacity
- Mobile

**WEAKNESSES**

- Inaccurate proportioning
- Dust problem
- Poor results with fibre sludge

Figure 5-8: Screening Scoop





**MATERIALS AT  
THE TEST SITE**

- Gypsum-ash


**STRENGTHS**

- High production capacity
- Cost effective in large construction projects

**WEAKNESSES**

- No tests with fibre sludge or other than gypsum-ash
- Moisturising
- Dust problem

*Figure 5-9: Stack Mixer*

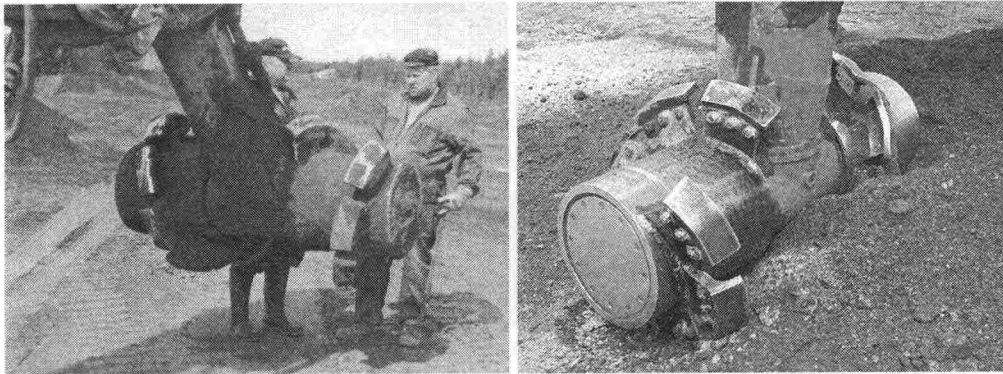

**MATERIALS AT THE  
 TEST SITE**

- Fibre-ash
- Stabilised FA

**STRENGTHS**


- Good mixing results with fibre sludge
- Mobile

**WEAKNESSES**

- Small production capacity
- Dust problem
- Inaccurate proportioning

*Figure 5-10: "Maamyrä"*



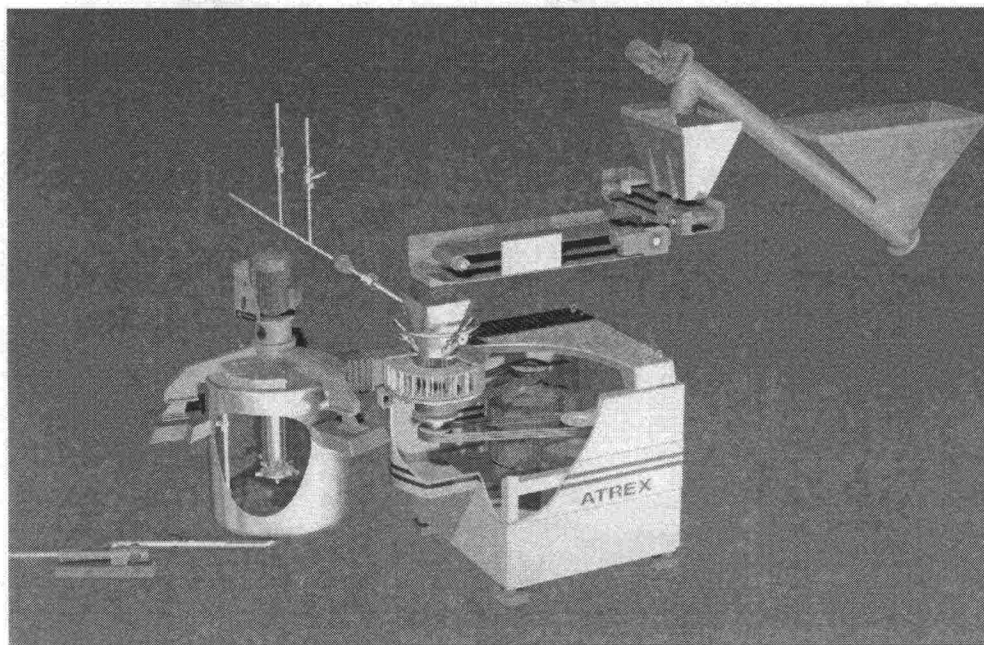

**MATERIALS AT THE TEST SITE**

- Tests in laboratory with
- Gypsum-ash
- Fibre-ash

**STRENGTHS**

- Very good results in laboratory tests
- Accurate proportioning

**WEAKNESSES**

- Low production capacity
- Energy intensive
- Expensive

*Figure 5-11: Impact Mixer (prototype)*

**Compaction of the NRC-structures**

Various aspects of the compaction of FA courses have been studied, i.e. in relation to the water content, thickness of the course, and the compaction equipment and methods, during the "Tuhkat Hyötykäyttöön" – project [6]. The studies have shown that a layer having a depth of at least 20 cm can be compacted to 92 % - 95 % of the maximum Proctor density value. This can be achieved if the water content of the FA is within certain ranges around the optimum water content, and if the compaction is performed with proper equipment and work methods. The FA course can be efficiently compacted with a 5 tonne Smooth Drum Vibratory Soil Compactor with a proper stroke length. Only the surface will remain loose and it must be compacted later, e.g. using a Rubber Roller or through a thin (approximately 5 cm) layer of crushed stone or gravel. This can be seen in *Figure 5-12*.

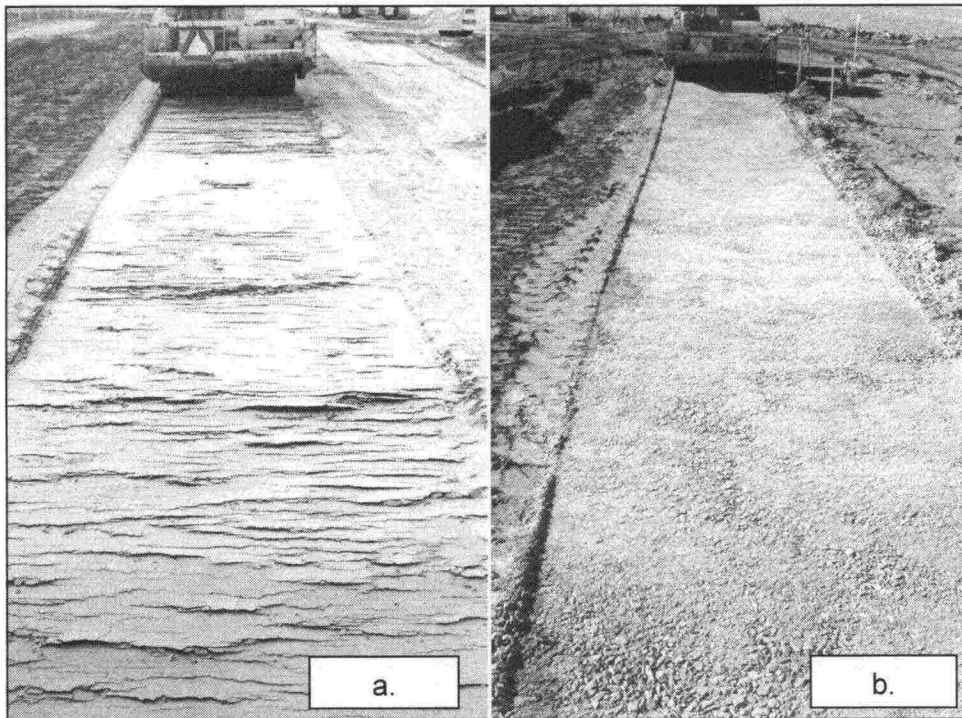


Figure 5-12: Testing of the FA compacting methods [6]; a) A Smooth Drum Vibratory Soil Compactor is compacting deep but leaving a scalelike surface which b) can be compacted through a thin course of crushed stone.

At the test sites the compaction was carried out after spreading and pre-compaction. The pre-compaction was done using a spreading machine, a truck or a Road Scraper running over the construction length for several passes.

The compaction of the sides of a NRC-structure requires special measures in order to prevent excess looseness and inadequate cementation. Figure 5-13 shows the principles of two simple but successful methods that have been tested at the full-scale test sites.

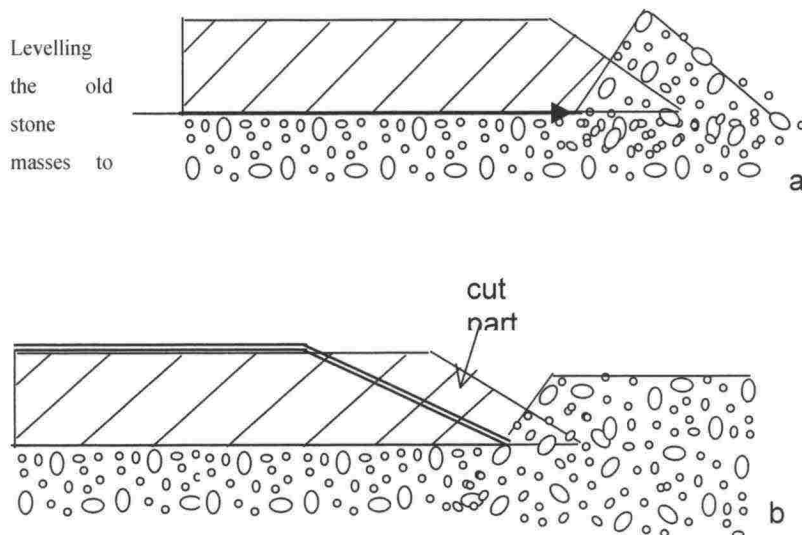


Figure 5-13: Principles to ascertain the compaction of the road side in NRC-construction; a) Side support; b) an extra wide structure where a part can be cut away.



## 5.5 Follow-up studies

### Homogeneity, compactibility and strength development

Follow-up studies at the test sites have been carried out for 0 – 8 years. *Table 5-2* summarises the results of tests and measurements during the construction and follow-up periods.

*Table 5-2* indicates the relatively wide variation of the water content in the material masses. As a rule the water content has been less than the optimum, which is safe in regard to the success of the compaction. At the site of Knuters it was possible to achieve very high precision with the help of the stationary mixing plant. However, the targeted relative compaction has been achieved at almost all of the test sites. At the MFA-section of Laitila considerably high water contents were measured that resulted in a low degree of compaction and softening during the thawing period of the first spring following the construction.

At the first fibre-ash site (Luopioinen) the mixing of FS with FA was not quite satisfactory with the use of a screening scoop. For this reason it was not possible to achieve the targeted relative compaction. Despite this the structures have been performing as expected, which indicates that the fibre-ash structures allow wider tolerances than only FA structures. At the site of Jämsä the fibre-ash structures were constructed using the "Sami"-mixer, and the better mixing quality resulted in a higher relative compaction.

In Maaninka, the gypsum-ash section where the subsoil is mainly silt was constructed in the early spring. During the construction a part of the road's subsoil was very wet and its bearing capacity was very low. Consequently, the compaction of the gypsum-ash layer above the soft and wet subsoil was not totally successful. However, the road has been performing quite well.

At most of the test sites samples have been taken by drilling or from a sampling pit at different time periods. The samples have been tested, e.g. for strength (UCS), that indicates the minimum strength achieved at the test section. The UCS results of FA and FA-mixes have to be considered with some reservations because these materials are often relatively brittle. In general the materials become more brittle as the strength develops with time. This can be seen in the results from Knuters: after 330 days the UCS of the samples taken from the sampling pits were larger than after 690 days. Penetrometer results measured in the sampling pits showed opposite results.

The results from samples of certain test sites showed significant strength development between the ages of 1 month and 12 months, for example the MFA-sections of Tornio and the CFA-sections of Mustasaari. The oldest site (8 years old) at Pirkkala shows that despite a thin structure and heavy (timber) truck traffic the strength of the FA structure of this gravel road has remained close to the target strength.

The targeted bearing capacity has been well achieved and the condition of the roads have remained essentially excellent at all of the FA sites and renovated FA-stabilised sites. The bearing capacity of fibre-ash and gypsum-ash structures has not become as high as the FA sites. However, the fibre-ash structures (with their excellent stress-strain properties) have been often observed to withstand the fatigue loads and settlements better (without breaking) than the structures utilising only FA.


Table 5-2: A selection of results of follow-up studies at the test sites

NRC	Site	Year of const.	Material mix	Water content [%]		Relative compaction (Proctor) [%]		UCS [MPa], 28 d		UCS from samples from the test site at a certain age of the structure [days / MPa]		Bearing capacity, mean, E <sub>2</sub> [MPa]		Noted condition during follow-up		
				optimum	Measured variation	Target	Measured variation/mean	Lab.	from materials mixed at site	I sampling	II sampling	Before constr.	After constr.	Year after constr.	Age of the structure [years]	
FA (solid)	Pirkkala	1992	MFA + 4(M + Ce, 1:2)	18,5	46-51	95	90-97	1,3	1,4-1,8	360/1,1-1,3	1800/0,9-1,5	30	90	1997	8	Good
	Luopioinen	1996	MFA + 4(M + Ce, 7:3)	17,5	19-23	90-95	79-82	2,48	n/a	280/0,27	n/a	69	118	1999	4	Good
	Sipoo, Knuters	1997	CFA	27	16-31		89-95/92	0,5	0,45	330/0,47	690/0,17	42	171			
				24-26	22-25	92	75-98/93	2,2	1,78	330/1,85	690/0,74	61	376	2000	3	Good
				33	24-36		91-97/96	1,2	1,07	330/1,13	690/0,48	90	167			
	Koria	1998	MFAI + 3Ce	19,5	15-23	94	92-94	4,1	2-3	360/1,7-3,4		44	140			
				28	23-28	92	92	8-9	3	360/1-2,9		47	113	2000	2	Good
				18,5	19-22	92	90	6,9	3	360/1,7-4,5		98	120			
	Jämsä	1998	MFAI + 4Ce	38,5	34-38	92	91-93	3,9	1,5-2	360/0,8-0,9		65	109	2000	2	Good
				46	30-42	93	91-94	2,3	1,5	360/0,6-0,8		55	102			
	Laitila	1998	CFA + 3T	23	20-25	92	91-92	2,2	2	360/2,7-3		55	170	2000	2	Good
				45	31-60	92	85-88	2,1	<1	360/0,4-0,6		45	105			
	Juankoski, V	1999	MFA + 6Ce	42	30-36	92		>7,3	2,5-6,9	360/3,9-5,3		75				Good
				36	31-36	92	90-92	1,3	0,8-1,2	360/1,1-1,4		44	n/a			Fair
			38	35-40			2	1,1-1,2	360/0,6-1,3		48				Good	
Mustasaari	1999	CFA + 6Ce	37	19-25	91	89-92	2,3	1,5	360/3,9-5,5		94	163	2000	1	Good	
			37	22-25	91	90-92	1,5	1,5	360/1,5-3,1		81	114				
Tornio	1999	MFA + 4Ce	31	20-24	91	88-89	4-5	2,5	360/7,7-8,5		76	132	2000	1	Good	
			31,5	20-24	92	91-93	3	2,5-3	360/4,7		118	221				
FA as Binder	Laitila	1998	Binder 15(CFA + M, 4:6)	6,2	4,2-6,6	95	91-95	1,7	0,4-0,6	360/0,2-1,2		56	82	2000	2	Good
	Luopioinen	1996	FS + 40MFA + 5Ce	40,9	40-46	90-95	85-86	0,7	n/a	30/0,45 <sup>1</sup>	360/0,11	94-134	46-69	1999	4	Good
			51,2	52-56		87-88	0,4	n/a	30/0,22 <sup>1</sup>	360/0,22	38-68	23-39				
Fibre-Ash	Jämsä	1998	(FS1 + MFAI, 10:3) + 7Ce	56	60-68	96	97-100 <sup>2</sup>	0,3-0,4	0,4	360/0,2-0,5		71	67			
			65	59-73	97	≈ 100 <sup>2</sup>	0,6	0,4	360/0,3-0,4		77	98	2000	2	Good	
			51	39-50	92	90-92	0,6-0,7	0,5-0,6	360/0,2-0,4		40	87				
Gypsum	Maaninka	1999	PG + 10PFA + 4(M + Ce, 7:3)	18	14-22	95	83-90	1	1-2	90/0,5-1,5	360/0,7-1,2	60	92	2000	1	Good

1) ε = 10 % ; 2) in relation to the maximum density, not the maximum dry density

**Freezing and frost heave**

Freezing of the test structures has been controlled with Thermolement Poles. As there are major variations in the annual thermal loads the freezing at a given NRC-test structure should be compared to the freezing of a conventional reference structure at the site. *Figure 5-14* shows the results of frost heave measurements at a test site (Luopioinen) and *Figure 5-15* the maximum frost depth at the same site from 1997 to 2000. The results were obtained from the fibre-ash sections (KT1 and KT2) and from the reference crushed stone section (MK). *Figure 5-14* shows that the frost heave has been on average 80 % (KT1) and 57 % (KT2) less than the frost heave of the reference structure (REF). Tests on other FA and fibre-ash structures of 200 mm thickness have shown similar results. Tests on gypsum-ash and slag-ash materials have not shown as low frost heave results as fibre-ash materials.

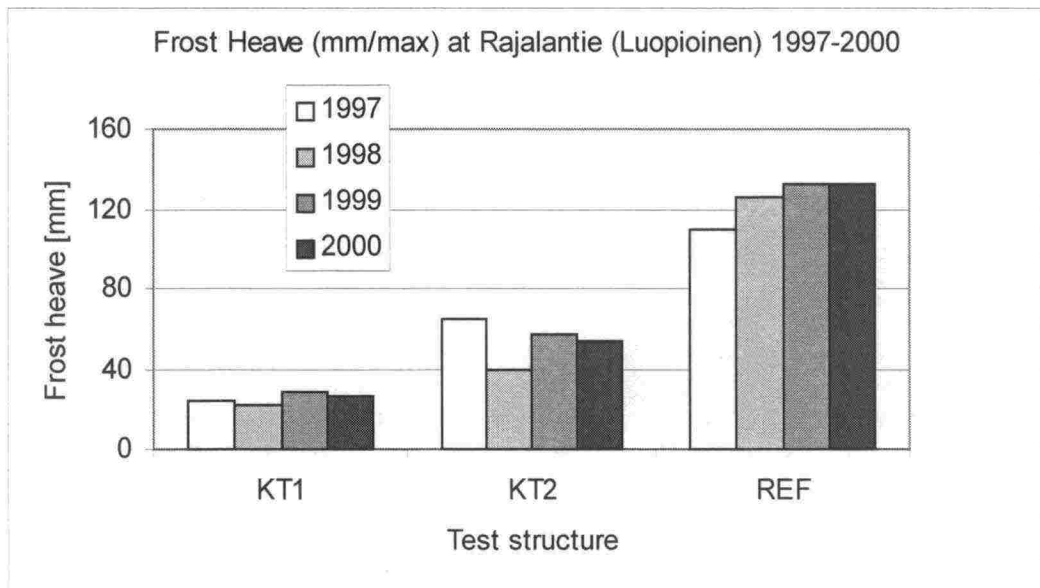

*Figure 5-14:* Frost heave at the Rajalantie test site in Luopioinen 1997 – 2000. KT1 = FS + 40MFA + 5Ce; KT2 = FS + 20MFA + 9Ce; REF = conventional crushed stone structure

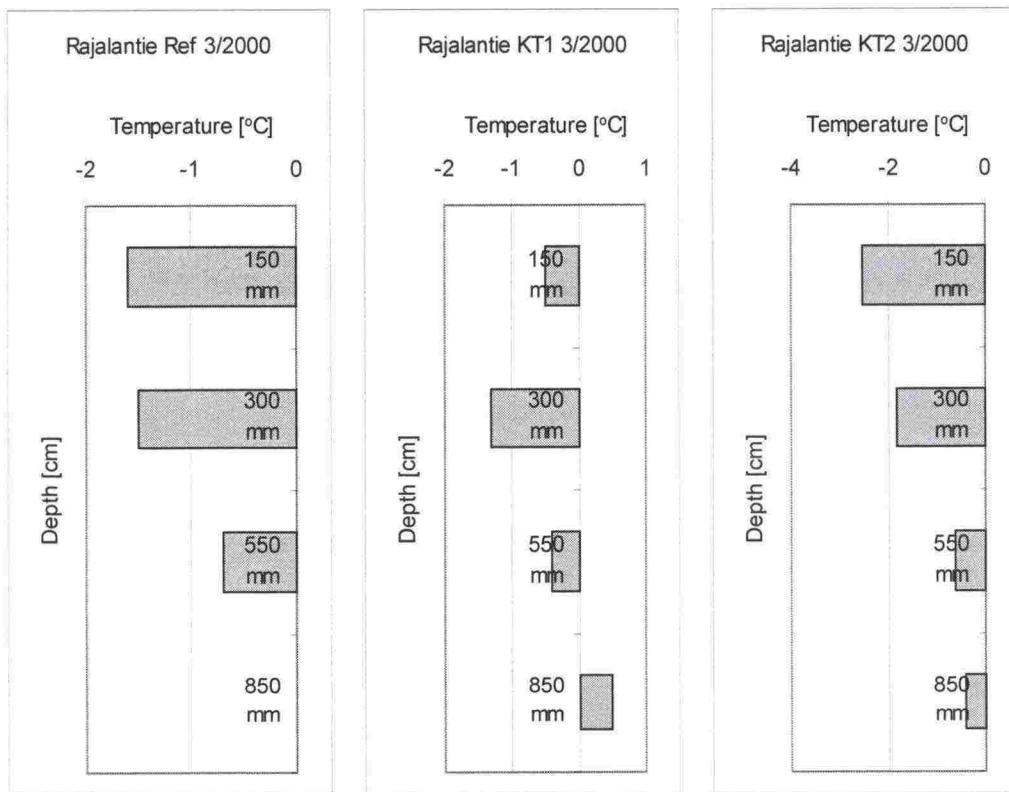


Figure 5-15: Frost depth at the Rajalantie test site in Luopioinen 1997 – 2000. KT1 = FS + 40MFA + 5Ce; KT2 = FS + 20MFA + 9Ce; REF = conventional crushed stone structure

### Temperature during cementation

When using FA or FA-mixes the prevailing temperature during and after construction has a significant effect on the start of cementation. The cementation will start only at temperatures above 4,0 °C. The pozzolanic reactions do not initiate at temperatures lower than + 4,0 °C and the strength of the FA-material will be very low. Also, at temperatures below 10 °C cementation will occur very slowly. This was evident at a test site in Inkoo in 2000 where the slow cementation of FA-materials kept the structures soft for a long time period and caused problems during the construction process. The mean temperature at the test site (+ 7 °C) was simulated during laboratory tests, and in comparison with tests at +20 °C the results were:

- the strength of CFA+15FGD+5CaO increased from 0,2 MPa to 0,4 MPa at 7 °C during the first 28 days and to 0,8 MPa during 60 days of cementation
- the corresponding strength development of this mixture was 3,6 MPa and 3,7 MPa at 20°C

For comparison, the same tests were made on a mixture of CFA+15FGD+5Ce. These tests indicate that the addition of cement tends to slightly improve the mix performance compared to lime at lower temperatures. The strength increased to 1,2 MPa, using cement, which is three times higher than with lime, during the first 28 days at 7 °C. Figure 5-16 shows the results of the laboratory tests performed on laboratory-remolded test specimens as well as the results that were obtained with 1 – 1,5 months old samples taken from the test structure by drilling. A part of the drilled samples were stored at 20°C temperature for 30 days before testing. This storage period indicated that the cementation reactions started properly and the test specimens achieved the appropriate 20°C strength (> 3MPa) very quickly.



## FA CEMENTING (START)

### Effect of Temperature

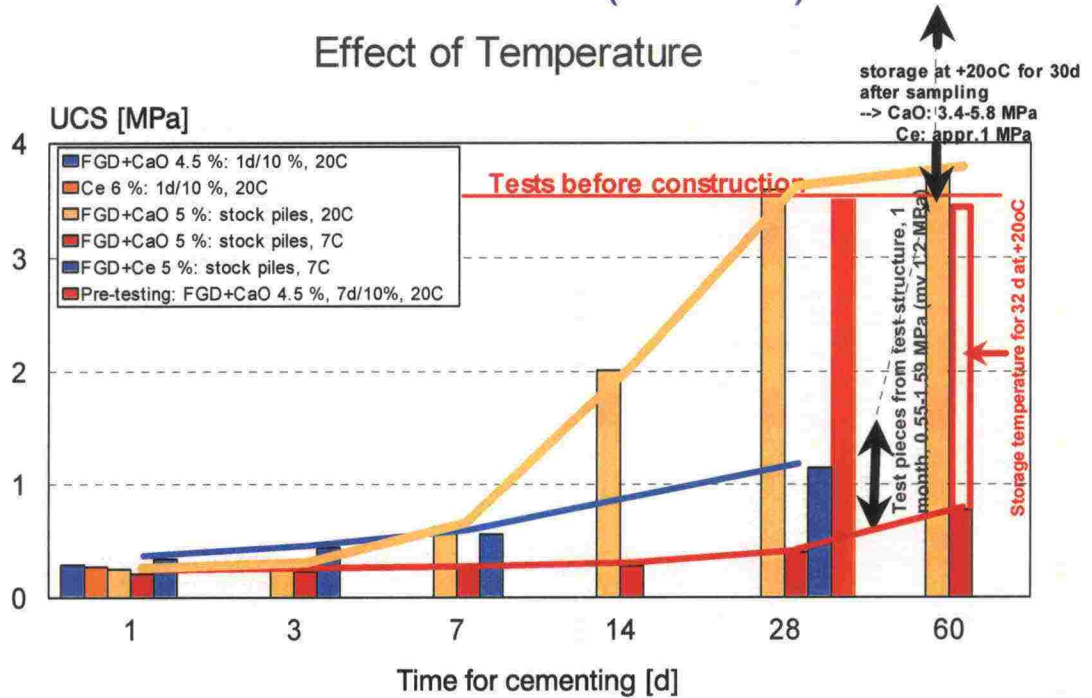


Figure 5-16: Strength development of FA-structures at different temperatures

### Environmental impacts

The environmental impacts of the test structures have been studied primarily by analysing samples from groundwater pipes. To date, the results from all test sites have been very positive. The concentrations of potentially harmful substances in all groundwater samples have been either below detection limits or below the Finnish guide values for drinking water.

The analyses of lysimeter water beneath the test structures in Sipoo (see Figure 5-5) showed that there was some leaching of substances from the NRC-material courses directly to the environment. The concentrations of potentially harmful substances in the lysimeter waters below the FA-structure and the reference structure are presented in Tables 5-3 and 5-4. The results show, for example, that the readily soluble molybdenum leached from the FA-structure during the first year after construction.

After this the leaching of molybdenum is significantly less during the second and third year as shown in Figure 5-17. The FA+FGD -structure was quite permeable only during the first year after construction. Thereafter the lysimeters beneath the FA+FGD -structure have been totally dry, which indicates that the permeability of the structure clearly has decreased. The most probable reason for this was the development of ettringites in the FA+FGD -material.

The lysimeter waters obtained from the FA- structure (Table 5-3) also have high a chlorine content, but this is also the case with the lysimeter water obtained from the reference structure (Table 5-4). The reason for high chlorine values is the spreading of salt on the road during summer to prevent dust spreading from the road surface. The impact of salt spreading is so great that the impact of any chlorine leaching from the structure because of fly ash or FGD is only marginal. However, the leaching of sulphate from the test structure is slightly higher than that from the reference structure.

Lysimeters have also been installed at some fibre sludge test sites. However, the hydraulic conductivity of these structures has been so low that the lysimeters have remained dry for several control years. In these cases it is evident that infiltrating water will not infiltrate through the NRC-course, but will flow on the surface of the NRC-course, through the crushed stone course to the sides of the road.

Table 5-3: Substances analysed from lysimeter waters obtained from FA test structure (Sipoo, Knuters). At the same site and control period the lysimeter well of a FA+FGD structure has been dry, and no sampling has been possible for comparison.

Analysed item	Method	Unit	Drinking water guide-lines	Date of sampling				
				29.7.98	1.7.99	5.11.99	3.8.00	6.11.00
pH	SFS3021	-	6,5-9,5	11,58	11,2	8,8	7,6	9,3
Electric conductivity	SFS3022	mS/m	<250	990	406	800	730	900
Arsenic, As	AH102	mg/l	0,01	0,2	0,064	0,012	0,007	0,01
Boron, B	ISO9390	mg/l	0,3-1	1,8	<1	-	0,84	1,68
Chromium, Cr	SFS5074, 5502	mg/l	0,05	1,4	0,35	0,24	0,2	0,23
Molybdenum, Mo	AAS	mg/l	0,07	8	2	1,5	0,9	1,52
Selenium, Se	AH102	mg/l	0,01	0,2	0,065	0,020	0,07	0,033
Vanadium, V	AH102	mg/l	-	1,4	0,68	0,085	0,16	0,099
Sulphate, SO <sub>4</sub>	ISO/DIS 10304-2	mg/l	150-250	240	100	60	68	88
Chloride, Cl	ISO/DIS 10304-2	mg/l	100-250	2300	950	2400	2900	2900
Nitric-nitrogen, NO <sub>2</sub> -N	SFS3029	mg/l	0,03-0,15	1,2	2,7	0,43	1,7	0,2
Nitrate-nitrogen, NO <sub>3</sub> -N	ISO/DIS 10304-2	mg/l	6-11	10	4,5	1,7	16	1,2

Table 5-4: Substances analysed from lysimeter waters obtained from the reference structure (Sipoo, Knuters). The results can be compared with the results in Table 5-3

Analysed item	Method	Unit	Drinking water guide-lines	Date of sampling				
				29.7.98	1.7.99	5.11.99	3.8.00	6.11.00
pH	SFS3021	-	6,5-9,5	7,92	8,0	7,4	7,6	7,4
Electric conductivity	SFS3022	mS/m	<250	253	492	1850	2600	3100
Arsenic, As	AH102	mg/l	0,01	<0,01	0,0072	0,032	0,006	<0,01
Boron, B	ISO9390	mg/l	0,3-1	0,09	<1	-	0,04	0,14
Chromium, Cr	SFS5074, 5502	mg/l	0,05	0,006	0,006	0,062	0,008	0,003
Molybdenum, Mo	AAS	mg/l	0,07	0,017	0,021	0,036	0,02	0,013
Selenium, Se	AH102	mg/l	0,01	<0,02	0,0036	0,033	0,09	0,076
Vanadium, V	AH102	mg/l	-	<0,05	<0,001	0,001	0,003	0,002
Sulphate, SO <sub>4</sub>	ISO/DIS 10304-2	mg/l	150-250	71	57	89	95	110
Chloride, Cl	ISO/DIS 10304-2	mg/l	100-250	670	1500	3900	2800	12000
Nitric-nitrogen, NO <sub>2</sub> -N	SFS3029	mg/l	0,03-0,15	0,004	0,005	0,035	0,042	0,018
Nitrate-nitrogen, NO <sub>3</sub> -N	ISO/DIS 10304-2	mg/l	6-11	0,9	0,75	0,77	15	2,9

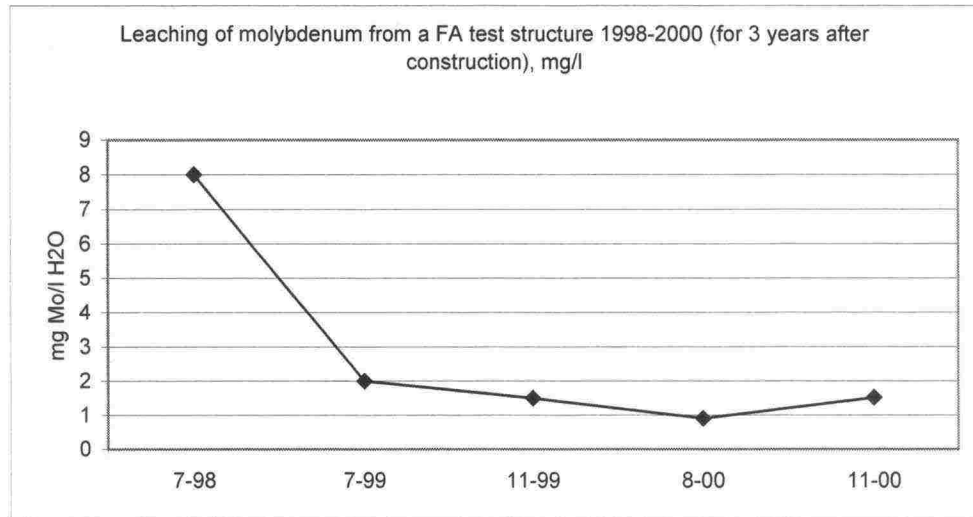


Figure 5-17: Leaching of molybdenum from the test structures in Sipoo (analysis of lysimeter waters)



## 6 EVALUATION OF NRC-TECHNOLOGY

### 6.1 Life Cycle

Full-scale tests on fly ash and its mixtures with other residues and binders have shown that these NRC-structures essentially differ from conventional structures based on natural stone materials. The mass of material required for recycled structures could be as low as 25 % of the mass required for conventional structures (see Ch. 6.2). Thus, there will be environmental benefits such as less transport of materials and, consequently, less consumption of energy and less emission of CO<sub>2</sub> and other pollutants. Furthermore, the NRC technology will reduce the disposal of valuable materials and consequently reduce private and public costs of waste disposal. Thus, less transport, less landfills as well as lower waste charges and taxes.

The lifetime of a structure and the long-term duration of its quality are factors that essentially contribute to its economy and other benefits. The data and information obtained from the full-scale test structures are indispensable for the evaluation of these factors associated with NRC-technology. On the basis of the follow-up studies and measurements it has been possible to prove that the lifetime of NRC-structures is longer, and the quality of NRC-structures will remain high for a longer period than conventional structures. Accordingly, the investment costs of NRC-construction can be distributed over a considerably longer time period and the maintenance costs are smaller, compared to conventional structures. Based on data and information from test structures *Table 6-1* presents estimates of the lifetimes of different NRC- structures in low-volume roads [15].

*Table 6-1: Estimates of lifetimes of NRC-structures in low-volume roads.  
Lifetime is here the period between the construction and the renovation. [15]*

STRUCTURE	LIFETIME [YEARS]
FA (solid)	30
FA as binder	30
Fibre-ash	40
Gypsum-ash	40
Slag-ash	40-50 (difficult to predict)
Crushed stone (conv.)	6-8
Crushed stone + filter cloth (conv.)	10-15

The studies noted above have given the following reasons for the excellent durability of NRC-structures:

- NRC-structures are based on the utilisation of cementitious materials that do not mix with subsoil or embankment materials as do the granular stone materials used in conventional structures.
- Flexible road structures with a 200 mm NRC-course can be well compacted in one course.
- The NRC-materials that have shown high long-term durability in laboratory tests have performed in a similar manner in test structures.



- In general, the NRC-materials have high (and fibre ashes have excellent) deformation durability that prevents failure when subjected to smaller frost heaves or settlements.
- Properties of FA such as strength development over a longer time period and self-healing behaviour are advantageous, compared to conventional structures.
- FA and fibre-ash structures become relatively impermeable ( $k = 10^{-7} \dots 10^{-9}$  m/s). Therefore, water infiltrating through the structural layers above the NRC-layer will eventually be transported horizontally along the NRC-surface and not through it. As a result, the amount of water accumulating beneath the road structure will be minimal, minimising frost heave and loss of bearing capacity during freeze-thaw cycles.
- Paper sludge will first freeze below  $-5^{\circ}\text{C}$  [1] - according to the tests of SGT the freezing temperature is  $-1 \dots -3^{\circ}\text{C}$ . This freezing point depression probably decreases the amount of frost heave in a structure.

## 6.2 Economic and Environmental Benefits

One of the most valuable environmental benefits obtained from using NRC-technology includes the preservation of non-renewable natural resources, since the use of gravel and crushed stone will be reduced. Accordingly, NRC-technology will protect the landscape, including beautiful and valuable areas of groundwater sources. Additional important benefits will be obtained by decreasing the amount of waste handling of industrial residues (see section 6.1).

NRC-technology will contribute to significant reductions in the use of natural stone materials. For example, by using NRC-materials (FA, fibre-ash, gypsum-ash, slag-ash) it is possible to achieve a bearing capacity of a road structure that is four times higher than a road constructed with crushed stone. Thus, a NRC-solid structure course of only 20 cm may substitute for a crushed stone course of 80 cm. Also, when reusing low-quality stone material from an old structure that is being stabilised with NRC-materials, it is possible to obtain a bearing capacity that is at least as high as the bearing capacity of NRC-solid structures (i.e. structures that consist of NRC-material only). The studies also indicate that there is almost no loss of bearing capacity of NRC-structures during freeze-thaw cycles in early spring. Reductions in the use of stone material will also be achieved because of longer lifetimes and the decreasing need for maintenance of NRC-structures. Also, NRC-materials and -structures are clearly lower in weight than stone materials.

Approximately 70 million tonnes of stone materials are consumed in soil construction in Finland every year. About 60 % of this amount is gravel and sand. An effective use of NRC-technology could contribute to the savings of stone material of about 24 %, or 16,5 million tonnes/year, i.e. almost the total amount of the yearly gravel consumption. The author has calculated the amount of hypothetically potential savings of stone material in Table 6-2. The calculations presented in Table 6-2 exclude potential savings during maintenance.

The calculations are based on the following premises:

- The lifetime of NRC-structures is on the average two times longer than the life of conventional stone structures.
- The total amount of FA produced in Finland is approximately 1,2 million tonnes annually. The total amount of FA available for soil construction is approximately 0,85 million tonnes (roughly 70 %) each year.
- In comparison with conventional gravel structures the bearing capacity of NRC-structures will be (on average) four times larger for stabilised structures and slag-ash structures, three times larger for FA structures and two times larger for fibre-ash structures.

Table 6-2: Savings with NRC-technology. Calculations.

NRC- STRUCTURE	Use of residue [Mt/year]		Total length of a low-volume road [km] <sup>1)</sup>	Savings of stone material [Mt/year]
	FA	Others		
FA structures	0,4	-	275	4,0
Fibre-ash structures; mixture 1:1	0,2	0,2 <sup>2)</sup>	140	2,6
Gypsum-ash structures having 15 % FA	0,1	0,67 <sup>3)</sup>	390	3,2
Slag-ash structures having 15 % FA	0,05	0,28 <sup>4)</sup>	150	2,7
Stabilisation of old road structures with 10 % binder	0,05	-	210	4,0
			1165	16,5

1) The amount of material (see: use of residue) can be used to construct a low-volume road, the width of which is 6 meters and the length

of which is calculated in the column (total length of low-volume road)

2) Fibre sludge

3) Phosphogypsum

4) Stainless steel slag

One can conclude from the calculations shown in *Table 6-2* that the theoretical savings could be about 16,5 million tonnes annually in Finland. The assumed amounts of different residues used in *Table 6-2* are only part of the total amounts produced. *Table 6-3* shows estimates of the total amounts that could be used as NRC-materials in Finland, the amounts available for NRC-usage, and the primary areas of usage for each residue.

According to *Table 6-3* there should be sufficient material available when NRC-technology will become significant in the construction sector. The estimated amount of available FA (assuming a 70 % recycling rate) is relatively high. Therefore it is not likely that this figure will be higher, as there are also other uses for FA (e.g. for cement, as a filler in asphalt, and as forest fertiliser). Additionally, there is a relatively large variation in the seasonal and annual production of FA, depending on the prices of feedstock and energy as well as on energy consumption. Thus, the total amount of FA might occasionally be lower than the estimates shown in *Table 6-3*, and then the availability of FA could restrict the development and use of NRC-technology.

Table 6-3: Estimated availability of residues in Finland

RESIDUE	TOTAL AMOUNT FOR NRC-APPLICATIONS	AVAILABLE AMOUNT FOR NRC- APPLICATIONS		USAGE IN FINLAND
	Tonnes / year	Tonnes / year	% of total amount	
FA	1 200 000 <sup>1</sup>	850 000	70	Southern and Central Finland
Fibre sludge	450 000 <sup>2</sup>	200 000	45	Up to Southern Lapland
Phosphogypsum	1 200 000 <sup>2</sup>	570 000	48	Eastern Finland
Stainless steel slag	300 000 <sup>1</sup> (in 2000); appr. 500 000 <sup>1</sup> (in 2002)	280 000 (in 2000)	90 (in 2000) 56 (in 2002)	Southern Lapland and Oulu region

- 1) dry weight
- 2) total weight

The former calculations used to quantify the potential for NRC-construction have significant implications for the development of the Finland's road network. In Table 6-2 the calculations were used to estimate the total length of 6,0 meters wide low-volume roads that can be improved with NRC-technology annually. The average total would be about 1165 km / year. Although the former calculations were only applied to low-volume roads, the relative benefits of NRC-technology might be similar for other types of roads and field structures as well.

The total amount of industrial residues that is available for NRC-technology is estimated to be 1,9 million tonnes each year (estimated by the author). Presently, all of these residues are disposed of in landfills or used as secondary fillers. The disposal of this amount of industrial residues requires 30 landfill hectares each year (supposing the average height of the course is six meters and the average bulk density about one tonne/m<sup>3</sup>). The construction costs of a landfill can be relatively high, largely depending on the prevailing requirements for the construction of landfill liners and covers. For a common municipal waste landfill, the costs of a bottom lining system is about 250 FIM/m<sup>2</sup>, and the costs of a surface cover structure about 150 FIM/m<sup>2</sup> (based on calculations of different projects by SCC Viatek Oy). Thus, the construction costs of 30 landfill hectares will be approximately 120 million FIM. In addition to construction costs there will also be costs for transport, waste handling and waste taxes. Additional factors to be considered are the loss of land value in and around landfills, and environmental damage. It can be estimated that the total waste costs for disposal of industrial residues will be between 100 and 250 FIM/tonne. Thus, total waste costs to industry for disposal of the 1,9 million tonnes would be between 190 and 475 million FIM annually (without waste taxes).

The economy of NRC-technology has been summarised and discussed in a report dealing with a long-term study of different structures used for low-volume roads [29, 30]. Different low-volume road applications were compared relative to their differing geotechnical and environmental properties, and their relative economics were also compared. When calculating the costs of different applications total life cycle costs were considered. The construction costs are based on the data and information obtained from the test structures included in the study, and maintenance costs were based on the data supplied by FinnRa. Figure 6-1 shows the total costs of different structures (FIM/road meter): the costs are calculated from the time of renovation until the time of the first minor repair at the site. The estimates for the life

times of the different structures shown in *Table 6-1* have been based on the observations and measurements at the test sites. It should be noted that follow-up studies at different test sites will continue and estimates of the life-cycle costs and lifetimes should become more precise.





Figure 6-1: Total costs of structure [29]

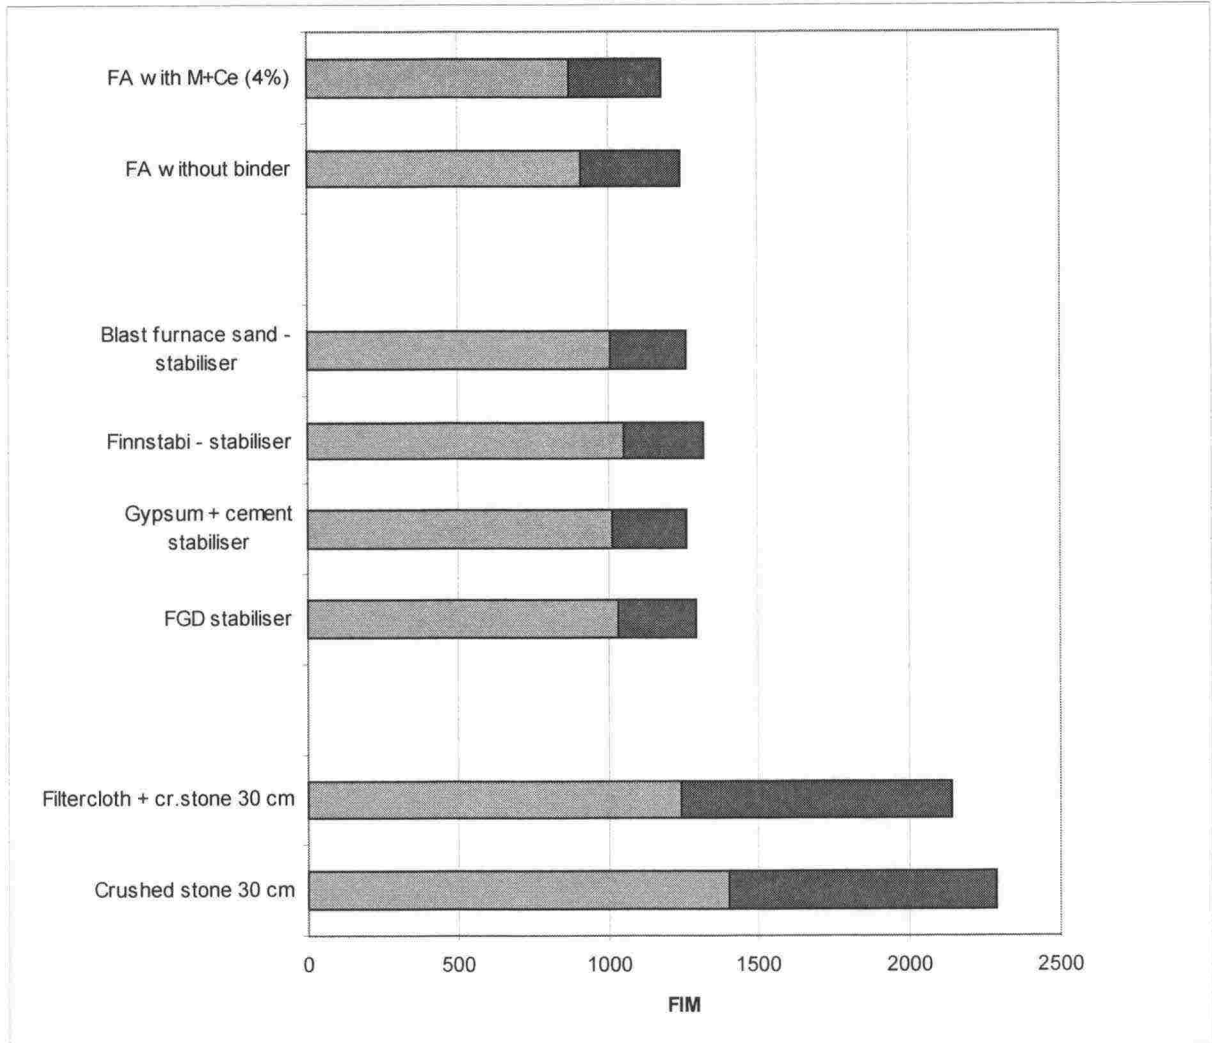

### 6.3 Environmental Impact

Sampling and analyses of the groundwater at each of the test sites, and the soil at some of the test sites, have been included in the studies dealing with the environmental impacts of NRC-structures. These studies indicate that these NRC-structures entail no risk to the environment.

In addition to the studies noted above, most of the industrial residues included in the studies have been subjected to leaching tests, mainly column tests (NEN 7343), and the results are shown in *Table 4-10*. The results indicate that the limit values suggested, for example for molybdenum (Mo) [31], may be too low and restrictive to the use of industrial residues, as the amount of molybdenum leaching from most residues, such as FA, usually will exceed the limit values. Therefore, more detailed studies for the effects of molybdenum have been carried out in the project "Tuhkat hyötykäyttöön" [6]. The leaching and distribution of molybdenum from coal ash structures to the soil and groundwater have been studied by using a mathematical dynamic transportation model [VI]. The results can be summarised as follows:

- Molybdenum occurs in coal fly ashes in different percentages: a readily soluble fraction, a less readily soluble fraction and an insoluble fraction.
- The relative amounts of the different fractions differ between FAs from different sources.
- The solubility of molybdenum is controlled by pH as shown in *Figure 6-2*. The pH of a FA structure is typically high (10.5 – 12.0). Thus, the soluble molybdenum will be leached from the FA layer relatively quickly, but it will be retained below the FA layer in the soil layers with lower pH (6.0 – 7.0) as shown in *Figure 6-3*.
- *Figure 6-3* shows pH and water content at different courses of a seven years old test construction with FA –structural course. Ten centimeters beneath the FA-course the pH-value is already close to the pH-value of the subsoil.
- The calculations of the dynamic transportation model are based on results from a large amount of laboratory tests involving leaching tests (the column test NEN 7343 and the batch leaching test CEN 12457) as well as tests to determine the adsorption of molybdenum on different soil types. The validity of the model has been tested by comparing the results with results from samples that were taken from the test pits of two and twenty year old FA structures. The samples were taken from different depths at both of the sites and analysed for the concentration of molybdenum. The model has proved to be valid. Therefore, it is now possible to reliably determine the long-term transportation of molybdenum into the subsoil and groundwater. Similar studies could be carried out for other constituents as well.
- The calculations of the dynamic transportation model on road structures indicate that molybdenum concentrations in groundwater will not exceed the drinking water limit values for at least 100 years after construction. These results were independent of the thickness of the FA layer (less than one meter) and the subsoil type. In fact, the concentration values will be far lower than the limit values for drinking water in Finland. This corresponds with the results from follow-up studies at the test sites (see Chapter 5).
- The calculations have also shown that soil courses immediately beneath FA-courses (0 – 20 cm) will adsorb molybdenum. The highest concentration is caused by the readily soluble fraction, and the leaching of this fraction will take place during the first year after construction. This fraction will be transported to

lower layers depending on the adsorption capacity of the soil. However, the concentrations will be so low that the limit values for polluted soil will not be reached. The calculated values correspond with results from the test sites.

- Based on the dynamic transportation models nomograms have been created to estimate the amount of molybdenum that will be transported into groundwater and soil for a period of 100 years after construction. The molybdenum concentration is given as a function of the NRC-layer's thickness, the type of subsoil beneath it, and the column test results for the material in question. If required, similar nomograms could be created for many other constituents as well (e.g. for Ba, Cr, Ni, Se, V).

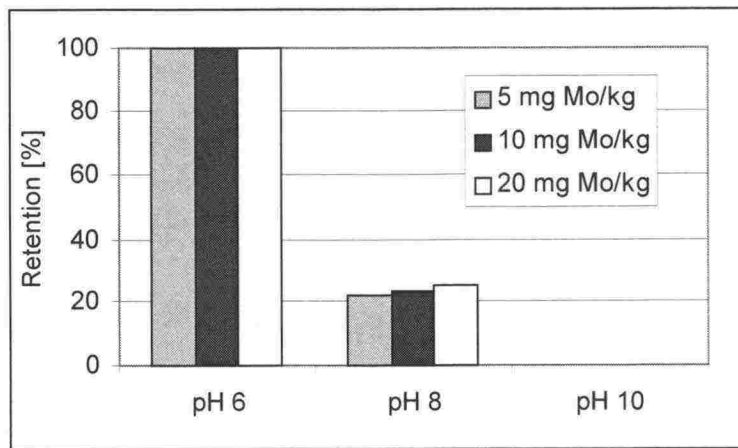


Figure 6-2: Solubility of Mo as a function of pH. The figure shows the retention of Mo in a clay at different pH-values [ 32]

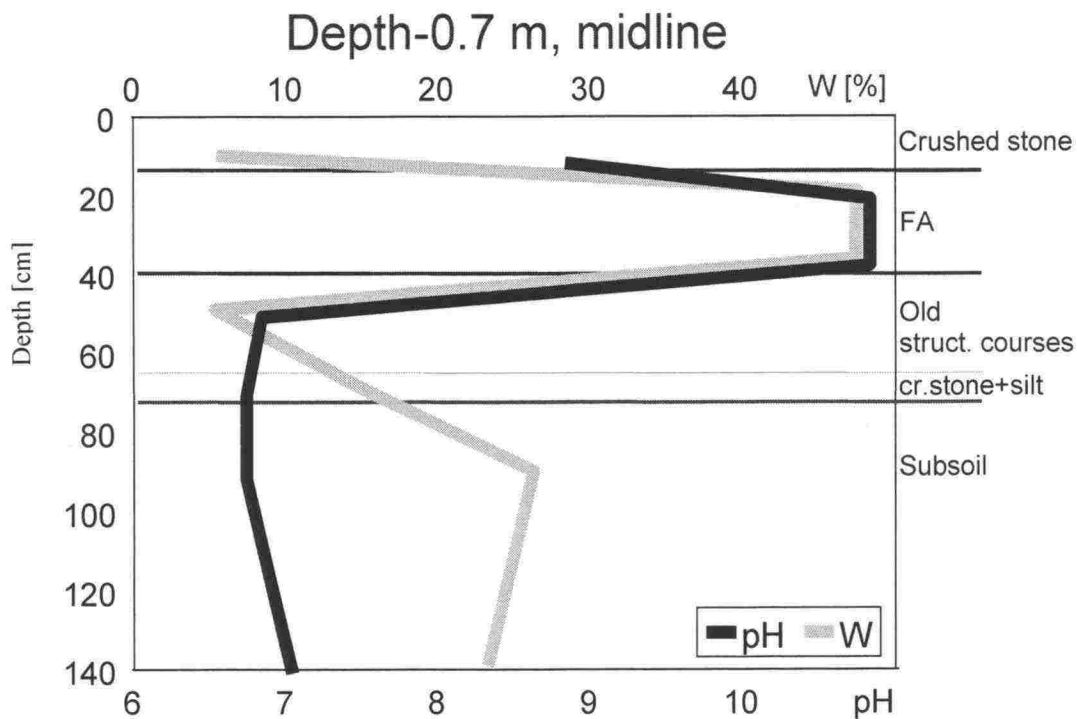


Figure 6-3: pH-values in the FA layer and below the FA layer (w = water content of the materials in different layers) [15]

## 7 CONCLUSIONS AND FURTHER RESEARCH

### 7.1 In General

The studies indicate that it is most profitable to recycle the FA 1) as binder for processing other construction materials and 2) as base material and without further processing, for a solid structural course. In soil construction there are several applications that meet the principles for sustainable development for FA. The general conclusions of the studies on FA as a NRC-material are as follows:

- PFA, WFA and MFA are equal in quality and are often better than CFA for NRC-applications.
- FA can be used as a stabilising component for the stabilisation of stone materials or soft soil (peat, clay, gyttja).
- FA plays an important role in the manufacture of NRC-materials when combined with other industrial residues such as fibre sludge, phosphogypsum and stainless steel slag.
- NRC-structures based on the use of FA are particularly cost-effective over their total lifetimes.
- By using NRC-structures, it is possible to obtain significant savings of natural stone materials and to reduce the need for disposal sites and landfills.
- The long-term durability of NRC-structures has been observed to be clearly better than the long-term durability of conventional stone material structures.

### 7.2 NRC-materials

Studies on materials have confirmed that the quality of most FA in Finland is adequate for use in NRC-construction. One of the most important reasons is the BAT<sup>2</sup> of incineration in Finnish power plants in general. Consequently, the loss of ignition (LoI) is relatively low at present. General aspects dealing with the use of FA as a soil construction material follow:

- FA is a quite valuable raw material for many soil construction applications
- Approximately 70 % of the total available amount of FA could be recycled for use in soil construction. The remainder can be recycled for use in other applications. Only a very small portion need to be disposed of in landfills or as secondary filling material because of inferior quality, the small amount available or the unfavourable geographical location of production.
- There is a significant variation in the quality of FA from different power plants, despite the use of similar fuels or fuels from same supply source. FA quality variations among peat combusting plants is larger than variations among coal combusting plants. Accordingly, separate FA batches from individual power plants may differ considerably from each other. Therefore, it is important to have continuous control of the geotechnical quality parameters of FA.
- During open-air pile storage of FA, a large part of the inherent and important geotechnical properties of FA will be lost because of excess moisture. A pile-FA cannot be recycled for use in as many applications as a dry FA, and the proper

---

<sup>2</sup> BAT = Best Available Technology. The author wishes to emphasise that the applied technology utilised in power plants in Finland is the best possible.



ties of a pile-FA application will be of lower quality than with a dry FA. Therefore, adequate dry storage arrangements for FA will be an essential precondition for the development of a controlled recycling system. This is also necessary because most FA is produced during the coldest season, when there are very little on-going soil construction projects.

- Fibre-ash has proven to be an excellent road construction material. Fibre-ash structures are durable and withstand deformation. A fibre-ash layer in a road structure will effectively reduce frost damage such as frost heaves, settlements and cracking of the road surface / pavement. Fibre-ash properties can be varied widely by properly proportioning components and by properly choosing binders or binder mixes.
- Gypsum-ash and slag-ash are very suitable materials for base courses, as their rigidity can be quite easily controlled with the proper choice of a binder. High rigidity and appropriate long-term strength development as well as excellent durability against freezing and thawing, makes it possible to use slag-ashes even in very demanding construction projects. Both phosphogypsum and stainless steel slag are being produced in large amounts each year, but to date only small amounts are recycled.
- Reactive FA appears to be a competitive alternative for other more conventional binders, for the stabilisation of old road structures, or soft soils like peat, gyttja and clay.

### 7.3 Laboratory Tests

The research methodology described in Chapter 3 has been used in the studies dealing with different NRC-materials and -test structures. The research methodology is very functional and efficient. It will determine the most optimal material recipes. The geotechnical simulation tests in the laboratory will give reliable and relevant results concerning the behaviours of NRC-materials. The materials that have met the criteria for the laboratory tests are observed to exhibit corresponding behaviour in full-scale test structures, and achieve target properties quite well.

The criteria that have been established for durability, to resist the effects of saturation, frost, freeze-thaw cycles and frost heave appear to be at least adequate. Experience has shown that the laboratory tests on NRC-materials related to durability relative to saturation, frost susceptibility and frost heave resistance are essential. The criteria established for those effects are quite appropriate. The freeze-thaw test simulates conditions that are much more severe than actual conditions in situ. Accordingly, the test might lead one to conclude that a given material is inadequate relative to durability. However, good results in a freeze-thaw test would indicate that the material will have an adequate if not excellent long-term durability in arctic climate conditions such as in Finland.

Laboratory investigations during a NRC project are very important. Wide variations in quality and in project related requirements are important reasons for testing all materials. This applies to residues and material mixes that are being used for the first time, but it also applies to relatively well known NRC-materials. Because of variations in NRC-material properties, and variations in NRC-structures, the methodology shown in *Figure 7-1* (at the end of this chapter) enables one to optimise the most economically feasible solution for each project. This type of methodology makes it possible to obtain significant cost savings.



#### **7.4 Environmental Acceptability**

The environmental laboratory tests have indicated that there is little or no potential risk to the environment arising from the use of FA and its mixes that utilise other industrial residues. The industrial residues that have been researched and referred to in this study include fibre sludge, phosphogypsum, and stainless steel slag. In order to minimise or eliminate environmental risk, the natural precondition for this is that correct and proper methods must be applied to the manufacture and usage of the materials. However, one of the primary restrictions for the use of NRC-technology can be traced to the inadequacy of prevailing legislation. Industrial residues are considered as waste materials and are regulated according to the existing waste decrees. Consequently, the use of these residues is subject to a relatively laborious permit process, both for construction site and for material treatment. In addition, there are no official, geotechnical and environmental criteria and guide lines dealing with NRC-construction that could help the permitting authorities arrive at their decisions. Therefore, the authorities become very conservative due to public safety considerations, and the permitting process can become very unreasonable.

#### **7.5 NRC-structures and -construction**

NRC-structures have exhibited excellent performance when tested in full scale and constructed according to the principles presented in Chapter 3. Conclusions;

- The thin and flexible NRC-structures utilised for the low-volume roads have been performing well, as outlined in Chapter 3, and their long-term durability might be even better than was described in Chapter 6.
- The NRC-structures were relatively simple to construct at different sites, and it has been possible to use available existing equipment for construction. However, the material manufacturers often request special equipment. However, in order to achieve better quality and higher productivity, this type of special equipment will have to be developed.
- NRC-materials based on the use of FA could also be used to develop structures for other applications, including highways, pedestrian routes, parking and storage areas, as well as sports grounds.
- Specific dimensioning standards applicable to NRC-structures should be developed.
- An effective quality assurance system that controls the total NRC-construction process is required in order to avoid inadequate materials and construction.
- The work methods used in full-scale construction operations have been adequate, but there is a need for improvement.

## 7.6 Further Research

Additional research and development efforts are preconditions for the wide implementation of NRC-technology based on the use of FA. Some suggestions for further research and development are presented by the author:

- Systematic research dealing with variations in the geotechnical quality of the FA
- Development of economically feasible and large enough dry storage systems for FA
- Development and testing of fibre-ash materials based on different types of fibre sludge (at present the only full-scale tests that exist have utilised deinking sludge)
- Development of FA binders into distinctive products for different end uses, especially for PFA, MFA and WFA.
- Development of different types of NRC-materials based on the use of slag-ashes that have very good geotechnical properties
- Continuing studies investigating the long-term properties of existing NRC-test structures, to obtain reliable estimates of their lifetime and durability, and to obtain additional long-term performance data (very important)
- Research and development dealing with the applicability of NRC-structures for different road types and field applications
- Development of applicable dimensioning standards for use with NRC-structures and research on their comparability with conventional dimensioning standards
- Dynamic transport modelling of potentially environmentally risky substances in addition to molybdenum (see Chapter 6)
- A thorough study dealing with the environmental and economic benefits derived from the use of NRC- technology
- Development of quality assurance / control systems, especially applicable to rapid and accurate proportioning of binders, and for more effective testing of structural density in the field.
- Development of a more appropriate laboratory procedure for the determination of the freeze-thaw behaviour
- Studies dealing with dynamic load durability of NRC-structures
- Research studying the effects of temperature and fatigue load on the strength development of FA materials at the early stages of construction and following construction
- Development of a mathematical model to predict the long-term duration of NRC-structures
- Research on the correlation between segregation potential, frost resistance and freeze-thaw durability of the materials.
- Thorough studies on the eco-efficiency of NRC-construction in comparison with the eco-efficiency of conventional soil construction based on the use of natural stone materials, both in Finland and in the total EU. In EU the total consumption of stone materials is about 2-billion tonnes/year. How much of this could be compensated with NRC-materials and, consequently, what kind of ecological savings could be obtained?
- Development of equipment, especially for the mixing process (quality of the mixing, control system, moveability, price, capacity etc.).

## USE OF INDUSTRIAL BY-PRODUCTS IN ROAD STRUCTURAL COURSES

### PLANNING PROCESS

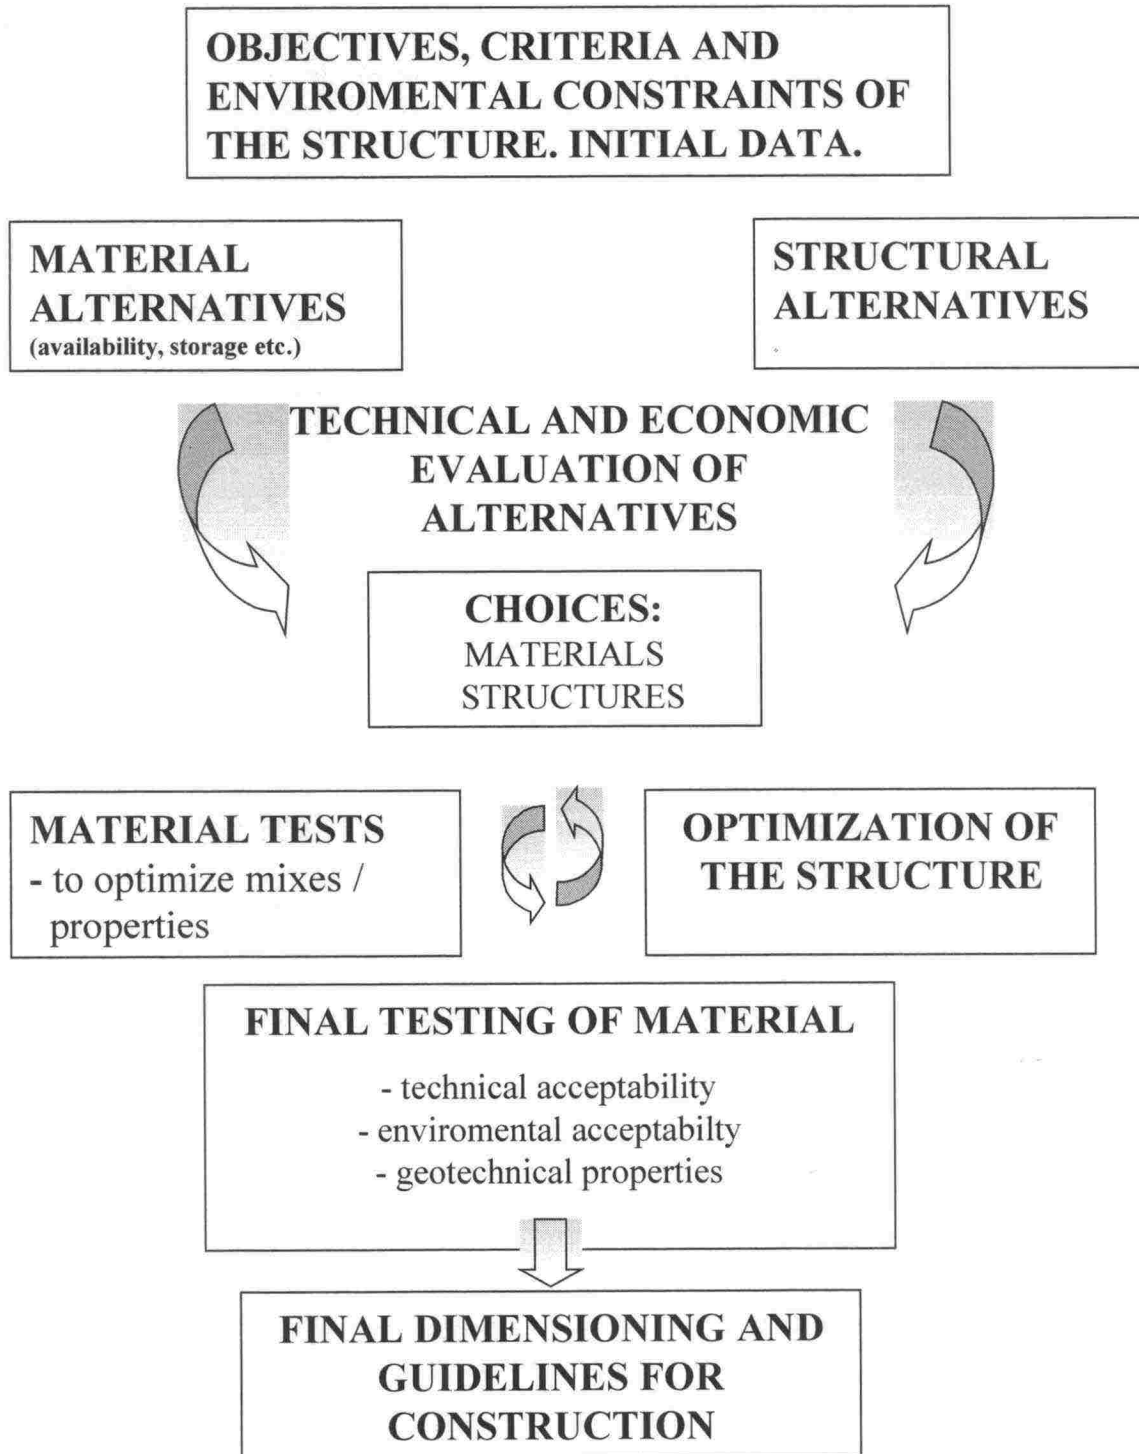


Figure 7-1: A methodology to optimise NRC-structures

## REFERENCES

- 1 Moo-Young Jr., H.K. (1995): Evaluation of Paper Mill Sludges for Use as Landfill Covers. Doctoral Thesis. Rensselaer Polytechnic Institute, Troy, New York.
- 2 Majumdar, A.K. (1999): Performance of Fly Ash as Fill Material and Construction of Pavements. Paper 83 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 3 Pavlenko, S., Shishkanov, A., Solin, A., Malyshkin, V. (1999): Technological Complex for Utilization of High-Calcium Ash and Slag for Abakan Thermal Power Plant. Paper 44 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 4 Karim, A.M.K., Lowell, C.W., Salgado, R. (1997): Building Highway Embankments of Fly/Bottom Ash Mixtures. FHWA/IN/JTRP-97/1, Joint Transportation Research Program, School of Civil Engineering, Purdue University, W. Lafayette, Indiana.
- 5 EuroSoilStab (2000): Development of New Binders. Final task report. SCC Viatak oy/SGT and Partek Nordkalk Oy Ab. 9/2000. Not published.
- 6 Tuhkat Hyötykäyttöön (transl. Utilisation of Ashes) –project (1996-1998) reports on binder development, test construction and follow-up tests. Not published. Publication: see reference 16.
- 7 TFHRC (2001): User Guidelines for Waste and By-Product Materials in Pavement Construction. HTML-version by TFHRC (<http://www.tfhrc.gov/recycle/waste>).
- 8 Brendel, G.F., Balsamo, N.J., Wei, G., Golden, D.M. (1999): Use of Advanced SO<sub>2</sub> Control By-Products. Paper 48 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 9 Thomas, M.D.A., Shekata, M.H., Shashiprakash, S.G., Hopkins, D.S., Cail, K.(1999): Use of Ternary Cementitious Systems Containing Silica Fume and Fly Ash. Paper 38 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 10 Bergeson, K.L., Schlorhotz, S., Brown, R.C., Zhuang, Y., Kang, Z., Wang, L. (1999): Evaluation of Fly Ashes from the Henan Province of China for Use of Concrete Admixtures and Soil Stabilizers. Paper 40 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 11 Tishmack, J.K., Olek, J. (1999): Coal Consumption by U.S. Electric Utilities and its Impact on Fly Ash Composition. Paper 81 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 12 Berg, K.C., Bergeson, K.L. (1999): Durability and Strength of Reclaimed Class c Fly Ash in Road Bases. Paper 85 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.



- 13 Keating, R.W., Hodges, W.K. (1999): Environmental Effects of BGE's Brandon Woods CCP Structural Fill Site. Paper 89 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 14 Azuma, K., Noguchi, S., Kurisaki, K., Ozasa, K., Takahashi, K. (1999): Earth Retaining Excavation Using Sheet Pile and Selfsupported Earth Retaining Wall by Deep Mixing Method Using Coal Ash. Paper 90 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 15 SGT studies (1990-2000) on the properties of diverse industrial residues. Unpublished reports that include relevant data from project clients like FinnRa, diverse paper manufacturers, Outokumpu Polarit Oy, and Kemira Chemicals in Finland.
- 16 Finergy (2000): Guide for Ash Construction. Road, Street and Field Structures. (Tuhkarakentamisohje Tie-, katu- ja kenttärakenteisiin) Energia-alan keskusliitto ry Finergy. Helsinki 2000 (in Finnish).
- 17 Waste Act 1072/93 (Finland).
- 18 Environmental Protection Act 86/2000 (Finland).
- 19 Chang, W.F., Mantell, M.I. (1990): Engineering Properties and Construction Applications of Phosphogypsum. Phosphate Research Institute, University of Miami, U.S.A.
- 20 Report on the utilisation of filterwaste and calciumchloride in soil construction. Laboratory investigations and full-scale test construction. SCC Viatek Oy/SGT for Kemira Chemicals in 2000. Not published.
- 21 ASTM (1989): Standard Specification for Fly Ash and Raw or Calcined Natural Pozzolan for Use as a Mineral Admixture in Portland Cement Concrete. ASTM C618-89a.
- 22 Use of Peat Ash in Road and Street Construction (Turvevoimalaitosten tuhkan käyttö tie- ja katurakentamiseen). Energiataloudellinen yhdistys. Raportti 25/1989 (reported in Finnish).
- 23 Helenius, J., Karvonen, E., Ipatti, A.(1992): Properties, Utilisation and Environmental Impact of Peat Fly Ash (Turvelentotuhkan ominaisuudet, hyötykäyttö ja ympäristövaikutukset). R&D report (T&K-tiedotteita IVO-B-03/1992) Imatran Voima Oy. Not published.
- 24 Isännäinen, S. (1994): Processing Ashes and Other Forest Industry Waste for Fertilising Purposes (Tuhkat ja metsäteollisuuden muiden jättejakeiden prosessointi lannoitekäyttöön soveltuvaksi). Report of VTT Energy (in Finnish).
- 25 Kauppinen, J. (1993): Use of a Stabilised Peat Ash in Road Construction (Stabiloidun turvetuhkan käytöstä tienrakennuksessa). M.Sc Dissertation for the Civil Engineering Department of the University of Oulu (in Finnish).
- 26 Walsh, Milja (1997): Utilisation of By-Products from Coal and Peat Combusting Power Stations (Kivihiili- ja turvevoimalaitosten sivutuotteet ja niiden hyötykäyttö). R&D Report 2. Energia-alan keskusliitto, Finergy. Helsinki (in Finnish).

- 27 Näätsaari, H. (1998): Leaching Tests for the Assessment of the Acceptability of Process Waste from Outokumpu Steel Mills in Tornio for the utilisation and landfill disposal (Liukoisuustestit Outokumpu Steel Oy:n Tornion tehtaiden prosessijätteiden hyötykäyttö- ja kaatopaikkakelpoisuuden arvioinnissa). M.Sc study for the University of Kuopio, Department of Natural and Environmental Sciences. (In Finnish, not published).
- 28 Konrad, J-M. (1980): Frost Heave Mechanics. Ph. D. Thesis. University of Alberta, U.S.A.
- 29 Haavikko, H. (2000): Economic Evaluation of New Repair Methods of Gravel Roads (Sorateiden uusien perusparannusteknologioiden taloudellisuus). M. Sc. Thesis. Department of Civil Engineering, Institute of Construction Economics, Tampere University of Technology. (In Finnish, not published).
- 30 Finnra (2000): Renovation of Gravel Roads. Long-term performance and Economy. (Sorateiden kelirikkovaurioiden korjaaminen. Koerakenteiden pitkäaikaiskäyttäytyminen ja taloudellisuus). Tielaitos, Tuotannon T&K, Tielaitoksen selvityksiä 10/2000, Oulu 2000 (in Finnish).
- 31 Sorvari, J. (2000): Environmental criteria of the mineral industrial waste materials used in earth construction (Ympäristökriteerit mineraalisten teollisuusjätteiden käytölle maarakentamisessa). The Finnish Environment 421. Finnish Environment Institute. Helsinki (in Finnish).
- 32 Envitop (2000): The mathematic modelling of the transport of molybdenum from CFA structures and the development of a tool for the assessment of environmental impacts (Molybdeenin kulkeutumisen mallintaminen kivihiilituhkarakenteista ja työkalun kehittäminen tuhkarakentamisen ympäristövaikutusten arviointiin). Report of Envitop 8.5.2000. Oulu (in Finnish, not published).
- 33 Kim, A.G., Kazonich, G. (1999): Mass Release of Trace Element from Coal Combustion By-Products. A paper for the International Ash Utilization Symposium. Lexington.
- 34 Kavalevova, E.S., Petropavlovsky, O.M., Krivenko, P.V. (2000): The Use of Steel Melting Slags in Earth Construction. A Paper for the International Conference on Practical Applications in Environmental Geotechnology, Ecogeo, 4-6 September 2000, Helsinki.
- 35 Bergeson, K.L., Barnes, A.G. (1999): Iowa Thickness Design Guide for Low Volume Roads Using Reclaimed Hydrated Class C Fly Ash Bases. Paper 85 for the 13<sup>th</sup> International symposium on Use and Management of Coal Combustion Products (CCPs). ACAA.
- 36 Rogbeck, J. (1999): Utilisation of Residues from PFBC. S-58193 Linköping, Sweden.
- 37 USEPA (1986): Test methods for evaluating solid waste. SW-846, 3<sup>rd</sup> edition, U.S. Environmental Protection Agency (USEPA). Washington D.C.

## APPENDICES

Participation of the author of the Doctoral Thesis, Pentti Lahtinen, in the papers and corresponding studies

- I New Methods for the Renovation of Gravel Roads
- II Paper Sludge in Road Construction
- III Deep Stabilisation of Organic Soft Soils
- IV New Methods for the Renovation of Gravel Roads
- V Use of Industrial Wastes in the Construction of Low-Volume Roads
- VI Molybdenum transport in coal fly ash soil constructions Roads

## **Participation of the author of the Doctoral Thesis, Pentti Lahtinen, in the papers and corresponding studies**

The doctoral thesis is based on several and separate studies and projects that have been carried out in the 1990's in Finland. Pentti Lahtinen's contribution to these studies and projects has been significant especially in the planning and management of the studies, in the analysis and evaluation of the results and in the reporting. In all of these studies and projects Pentti Lahtinen has been acting as a project manager and/or as an expert. Research groups to which Pentti Lahtinen's contribution has been outstanding have carried out the development of new materials and technology. All the papers (I – VI) that have been annexed to the doctoral thesis have been written by Pentti Lahtinen except a part of the Paper III. Pentti Lahtinen has presented himself all the papers except one in the conferences concerned. The background of the papers is shortly following:

### **I. New Methods for the Renovation of Gravel Roads**

*Lahtinen, P., Jyrävä, H., Suni, H. (1999). Paper for IRF Regional Conference, European Transport and Roads, Lahti 24.-26. May 1999. 8 Pages.*

The paper is based on several studies on the improvement of the low-volume roads by utilising NRC-materials. One of the writers, M.Sc., Mr Heikki Suni acted as the representative of the client for the study and did not directly participate the research work. M.Sc., Mr Harri Jyrävä has had the central role in the studies. Pentti Lahtinen has acted as the co-ordinator and as an expert in the studies.

### **II. Paper Sludge in Road Construction**

*Lahtinen, P., Fagerhed, J.A., Ronkainen, M. (1998). Paper for the Proceedings of the 4<sup>th</sup> International Symposium on Environmental Geotechnology and Global Sustainable Development, 9.-13. August 1998, Boston (Danvers). University of Massachusetts, Lowell, pp. 410-419. 9 pages.*

The paper is based, so far as is known, on the internationally first studies and development of fibre-ash materials and on the full-scale tests for a road (Rajalantie in Luopioinen) in 1996. The recipes for the material mixes have been given in codes as required by the industrial partner of the project. The representative of the industrial partner in the studies and in the paper was M.Sc., Mr J. A. Fagerhed who did not directly participate the research work. The main researcher of the studies was M.Sc., Ms Marjo Ronkainen. The work was carried out in close co-operation with Pentti Lahtinen who had a central role in the development of the materials and the technology as a whole.

### **III. Deep Stabilisation of Organic Soft Soils**

*Lahtinen, P., Jyrävä, H., Kuusipuro, K. (2000). Paper for the Proceedings of the Grouting Soil Improvement Geosystems including Reinforcement of the 4<sup>th</sup> GIGS, the International conference on Ground Improvement Geosystems, by the Finnish Geotechnical Society in Helsinki, 7-9. June 2000, pp. 89-98. 10 pages.*

The author of the doctoral thesis has had a central role in the development of the technology for the mass stabilisation of peat at the beginning of the 1990's. The development project was carried out in co-operation of SCC Viatic Ltd SGT and the University of Oulu. The project gave rise to a wider European interest in the development of deep stabilisation technology for organic soil in EU. Thus, partners from 6 EU countries started co-operation in a EuroSoilStab project in which Pentti Lahtinen has had the main responsibility for the development of new binders based on



industrial by-products. The paper is based on these studies on binder materials in which the use of fly ashes was an essential factor. Chapter 4 of the paper is written by M.Sc., Mr Kari Kuusipuro, and other chapters have been written by Pentti Lahtinen. In addition to the former writers central roles in the actual research work have had M.Sc., Mr Harri Jyrävä and M.Sc., Ms Aino Maijala .

#### **IV. New Methods for the Renovation of Gravel Roads**

*Lahtinen, P., Jyrävä, H., Suni, H. (2000). Paper for the Proceedings of the NGM-2000, XIII Nordiska Geoteknikermötet, Helsinki 5.-7. Juni 2000. Building Information Ltd., Helsinki, pp. 531-538. 8 pages.*

Like paper I this paper is based on several studies on the improvement of the low-volume roads by utilising NRC-materials. One of the writers, M.Sc., Mr Heikki Suni acted as the representative of the client for the study and did not directly participate the research work. M.Sc., Mr Harri Jyrävä has had the central role in the studies. Pentti Lahtinen has acted as the co-ordinator and as an expert in the studies.

#### **V. Use of Industrial Wastes in the Construction of Low-Volume Roads**

*Lahtinen, P., Jyrävä, H., Suni, H. (2000). Paper for the conference of Geo-Denver 2000, 5.-8. August 2000. Proceedings pending. 11 pages.*

Like paper I this paper is based on several studies on the improvement of the low-volume roads by utilising NRC-materials. One of the writers, M.Sc., Mr Heikki Suni acted as the representative of the client for the study and did not directly participate the research work. M.Sc., Mr Harri Jyrävä has had the central role in the studies. Pentti Lahtinen has acted as the co-ordinator and as an expert in the studies.

#### **VI. Molybdenum transport in coal fly ash soil constructions Roads**

*Lahtinen, P., Palko, J., Karvonen, T. (2000). Paper for Ecogeo-2000, International Conference on Practical Applications in Environmental Geotechnology, Helsinki 4.-6. September 2000. Proceedings pending. 7 pages.*

This paper is based on a specific research on the transportation of molybdenum from the soil structures to the surrounding environment. The responsibilities of the research have been following: Ph.D. Jukka Palko had the central role in the chemical analyses and in the studies for the soil's ability to absorb molybdenum. Professor, Dr. Tuomo Karvonen was responsible for the mathematical transportation modelling and Pentti Lahtinen for the geotechnical questions like typical structures and soil conditions. The paper focuses on the main conclusions of the research. The mathematical details of the model, the parameters etc. have been described more detailed in the research report.

## NEW METHODS FOR THE RENOVATION OF GRAVEL ROADS

P.O. Lahtinen, Viatek Ltd / SGT, Finland

H. Jyrävä, Viatek Ltd / SGT, Finland

H. Suni, FinnRa, Finland

### Abstract

Low-volume gravel roads cover around 40 per cent or 29 000 - 30 000 kms of the public roads in Finland. Additionally, there are considerably more private gravel roads. The imperfect structure of most of the gravel roads is the main reason for their significant frost and bearing capacity problems. FinnRa and Viatek Ltd have developed economic and sustainable methods to solve the gravel road problems in a R&D-project: New methods for the renovation of gravel roads. The new methods have been widely tested at the various test sites of the gravel road project.

The results of the gravel road project indicate that the technically and economically best methods are based on the use of industrial by-products in the structure layers or in the stabilisation of an old structure, on the stabilisation in general and on the use of different geo-reinforcement solutions. Methods based on insulation and drainage often are not as economical as the new methods. Also, they are not always sufficient to solve the problems. The most interesting industrial by-products include blast-furnace slags, fly ashes, flue gas desulphurisation residues (FGD) and gypsum for the stabilisation of an old structure, and ashes and mixes of ashes with fibre wastes for the base materials of road structures. In this paper we are concentrating on the construction technology based on recycled industrial by-products.

### Problems in connection with gravel roads

The gravel road project started in 1990. The first stage was to study problems connected with gravel roads at 52 different test sites. The test sites were chosen amongst the most problematic road sections in Savo-Karjala and Häme regions. The investigations at the test sites addressed the problems and damages as well as the current structures and the soil conditions. Based on the results the main types of problems could be determined and classified. New methods to solve the different types of problems were developed at the second stage of the project.

The typical problems of gravel roads are the frost susceptible subsoil with low bearing capacity, the thin and uneven structural layers that will be partly mixed with the subsoil during thawing, and the vicinity of ground water pipes. The typical problems are illustrated in the *Figures 1a* and *1b*.

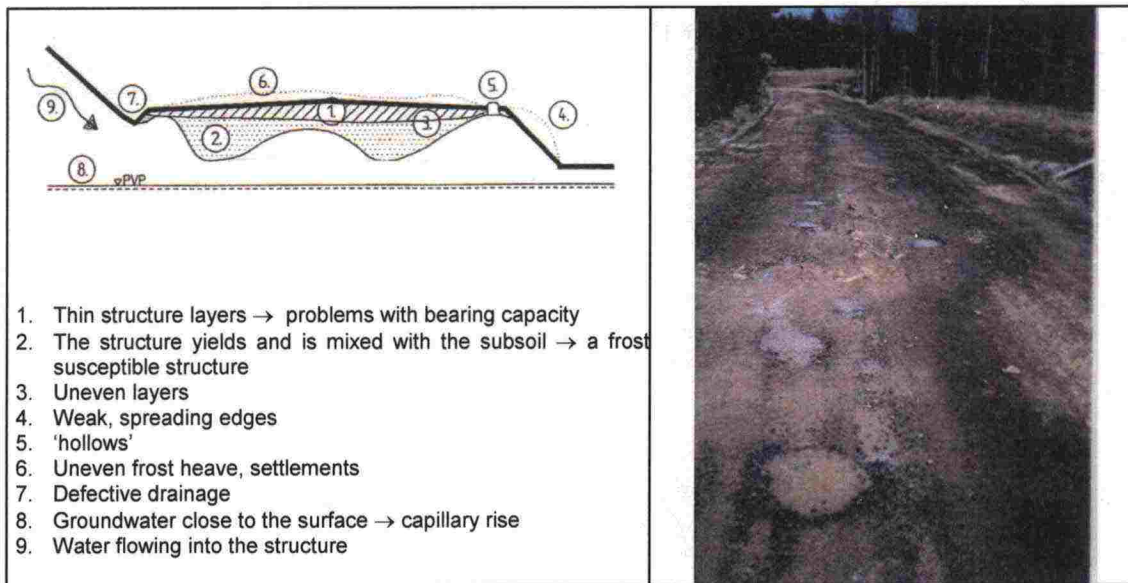


Figure 1a: Problems of the gravel roads

Figure 1b: A road before renovation

### Stabilisation of old structures

The stabilisation of old structures was studied and tested with eight different test structures (Table 1):

Table 1: Stabilisation of old structures

	Site	Binder	Year of construction	Binder quantity (%), layer thickness	Compression strength of tested materials, MPa		
					28 days <sup>1)</sup>	28 days <sup>2)</sup>	6-7 y. <sup>3)</sup>
1	Polvijärvi, Ruvaslahti pt 15798	Phosphogypsum + Ce 1:1	1991	10 %, 15 cm	3,4 (30 days)	-	1,1 - 1,8
2	Kuorevesi MT 3424	Slag (+ 2% CaO)	1992	30 %, 15 cm	0,3/0,6 <sup>5)</sup>	-	2,5 - 3,8
3	Kuorevesi, MT 3424	Lohjamix	1992	6,5 %, 15 cm	1,4 <sup>6)</sup>	-	0,4 - 0,9
4	Kuorevesi, MT 3424	THK <sub>2</sub> + F 1:1	1997	7 %, 30 cm	1...1,5	1,3 - 1,6	~ 1
5	Kuorevesi, MT 3424	F+THK <sub>2</sub> +Slag (S)	1997	5 %, 20 cm	3...	1,6 - 1,7	~ 3,5
6	Kangasala, Savontie MT 311	F + CaO 8:1	1992	12 %, 20 cm	2,1 <sup>4)</sup>	-	0,9 - 1,1
7	Laitila	F+THK <sub>2</sub> + Ce 1:1:1	1998	6 %, 25 cm	1,8	0,4...0,6	-
8	Laitila	Ash (IVO) + Merit 6:4	1998	15 %, 20 cm	1,7	0,3...0,6	-

1) Preliminary laboratory tests

2) Test pieces moulded during the construction work

3) Samples taken from the structure layers

4) Result after 30 days of curing: binder quantity 12 %

5) Granulated blast-furnace slag 30% + Cao 0,6% (30 days / 90 days)

6) FGD-mix 8% (30 days)

F = Binder of Kemira Pigments Oy, based on gypsum type by-products: Finnstabi

Slag. = Blast-furnace sand by SKJ

Lohjamix = A binder mix based on by-products of energy production

THK<sub>2</sub> = Secondary hydrated lime

Slag (S) = Fine-grained blast-furnace slag by SKJ

Merit = Fine-grained blast-furnace slag by Merox Oy: Merit 5000

Ash (IVO) = Coal fly ash from IVO, Meri-Pori power station

All test structures have been executed with following work sequences: At first the surface of the old structure was homogenised to a depth of around 200 mm. After this the binder materials was spread on the surface and mixed with the material of the old structure. A spring harrow and/or a road grader was used at sites 1, 2 and 3. A digging machine was used at site 6, and a milling machine at other sites. After compacting a grushed stone surface of 100 mm was spread on the structure.

The follow-up studies have been carried out at each of the test sites. The studies included the monitoring of the road condition, and measurements of the load bearing capacity and the surface level. Additionally, the temperatures, frost heaves, settlements and moistures were measured with electric geo-instruments. Six or seven years after the construction a part of the structures were opened and checked, and samples taken for the laboratory tests.



The less effective mixing results achieved at older test sites where the spring harrow was used in mixing could not be noted when comparing the structure quality between different sites. The performance of all test sites has been as anticipated: the structures have no damages, the bearing capacity has exceeded the target value in the spring, and no harmful, uneven frost heave as noted.

Until now, the follow-up of the older structures has continued from 6 to 7 years, and no weakening of the structures has been observed, except small quality decrease in the structures stabilised with binders Lohjamix and gypsum.

### Recycled materials in the structure layers

Recycled materials used in totally 14 test structures have been based on different fly-ash types, on fibre-ash mixes and on mixes of biotite+crushed stone (Table 2)

Table 2:1: Test sites with recycled soil construction materials

	Site	Material	Year of constr	Binder type and quantity	Compression strength, MPa		
					Lab 28 d <sup>4)</sup>	28 d <sup>5)</sup>	6-7 y
1	Ruvaslahti	Biotite-crushed stone	1991	Ce + slag (12 %, 2:1)	n.1,3 <sup>6)</sup>	-	1,4 - 2,4
2	Kangasala MT	Peat-ash, coal ash	1992	4 % Ce + slag	1,4	-	0,9 - 1,5
3	Kiuruvesi	biotite-gypsum 1:1	1991	Ce + slag (12 %, 2:1)	0,8	-	0,1 - 0,2
4	Koria pt 15467	Ash (Voikkaa)	1998	none	10,9	0,9 - 3,2	-
5	Koria pt 15467	Ash (Anjalankoski)	1998	Ce 3 %	> 10	3 - 3,8	-
6	Koria pt 15467	Ash (Lahti)	1998	F+THK <sub>2</sub> 6 %	5,2	2,0 - 5,7	-
7	Koria pt 15467	Ash (Myllykoski)	1998	Ce 6 %	0,9	1,2 - 1,5	-
8	Jämsä pt 16569	Mänttä-fibre-ash <sup>1)</sup>	1998	Ce 7 % *	0,6	0,4	-
9	Jämsä pt 16569	Nokia-fibre-ash <sup>2)</sup>	1998	Ce 6,6 % *	0,3	0,3...0,4	-
10	Jämsä pt 165 69	Jämsänkoski-fibre-ash <sup>3)</sup>	1998	Ce 4,8 % *	0,5	0,5	-
11	Jämsä	Ash UPM, Jämsänkoski	1998	Ce 6 %	2,0	1,2 - 1,6	-
12	Jämsä	Ash UPM, Jämsänkoski	1998	Ce 4 %	4,1	1,4 - 2,7	-
13	Laitila pt	Coal ash (IVO)	1998	F+THK <sub>2</sub> 3 %	2,9	1,2 - 2,6	-
14	Laitila pt	Mixed ash (UPM)	1998	F+THK <sub>2</sub> 5 %	2,6	0,8 - 1,2	-


\* = exceptionally based on the material's wet weight

- 1) Metsä-Tissue fibre waste + Mäntän Energia fly ash 45:55
- 2) Fort James fibre waste + Kaipola fly ash 100:40
- 3) Jämsänkoski fibre waste + fly ash 20:135
- 4) dry ashes have been used in the preliminary laboratory tests
- 5) Test pieces made in connection with construction at the test sites; moisture added to the ashes before construction
- 6) The binder mixes used in the laboratory tests: a. slag+Ce 1:1, 10 %: 1,1 MPa, b. slag+Ce 1:2, 15%: 1,4 MPa

The oldest test structures were constructed by grading the old road surface before the recycled material layers were spread and compacted. The test structures of new roads were started by pushing the surface material to a bank of the road sides. The side banks supported the recycled material layers during compacting. See *Figures 2a* and *2b*. The thickness of the 'recycled structure' is from 200 to 250 mm. A surface layer of 100 mm was spread on the recycled structure. All material mixes were made before spreading. Different mixing methods were tested in connection of the material mixing. The biggest problems during the construction were to arrange the storage and mixing for the dry fly ash, and to make acceptable mixes of fibre waste and fly ash. However, the problems could be solved with help of the best available equipment for storage, transports and mixing. For example, the fibre waste and fly ash can be mixed with a platform-mixer, and the mix proportions as well as the moisture of fly ashes can be sufficiently managed with a batch-mixer.



*Figure 2a: Preparing for construction*

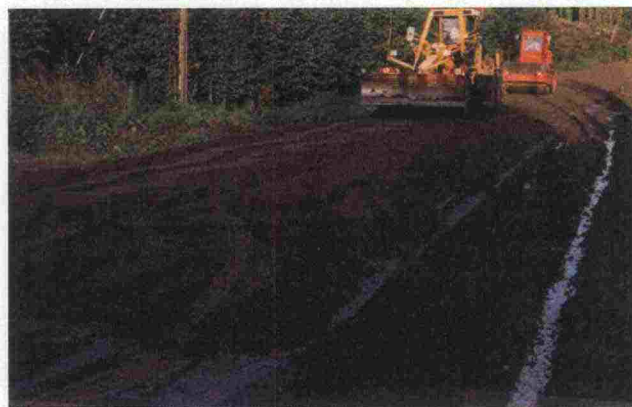

*Figure 2b: Finishing an ash-structure*

Geo-instruments were installed into the test structures like at the stabilisation sites, and the follow-up studies and measurements have been carried out. The results have shown that the structures perform as anticipated. The bearing capacity of the roads has remained at an acceptable level, and there are no observations of harmful frost heave. The only problems have been noted in connection with the biotite, the strengthening of which is quite difficult. On the other hand, for example, the good strength of the peat-ash-structure has not shown any deterioration during the 7 follow-up years after the construction. See Table 2 and *Figure 3*.





Figure 3: Open structure - after 7 years of renovation

**The economy of the new structures**

The economy of the new structures was assessed with help of the oldest test structures. The comparison of new and old methods was made by taking into account the construction and maintenance costs during a timespan of 15 years. It was assumed that the producers' price of the industrial by-products was 0 (zero) FIM. However, the transports, handling etc. costs have been assessed as full costs based on the prevailing competitive price level. The new methods have been compared with the traditional methods using crushed stone and crushed stone with filter cloths. The comparison (Figure 4) indicates that the structures with recycled materials and the stabilisation of an old structure are the most cost advantageous methods for the renovation of the gravel roads. The savings can be even as high as 50 %.

**Long-term costs of different structures, FIM/m**

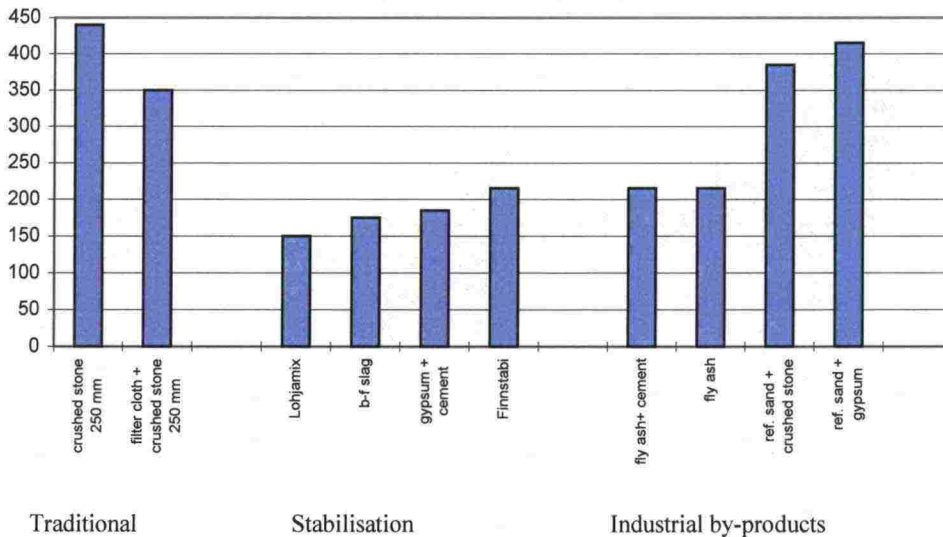


Figure 4: Comparison of the long-term costs of different stuctures

## Conclusions

The basic problems of the gravel roads, the frost heave and the weak bearing capacity in the spring, usually result in really bad traffic conditions. The traditional renovation methods of the gravel roads are expensive and require significant amounts of un-renewable natural stone materials. Therefore, development of environmentally friendly and cost effective renovation methods is necessary, even inevitable. The gravel road project has succeeded in the development of several viable solutions to renovate gravel roads:

- Both technically and economically excellent results can be achieved by the **stabilisation** of an old structure with help of binders based on different industrial by-products. So far, the best by-product components for binders are different slags, gypsum and ashes.
- Another competitive group of solutions is based on the **recycling of industrial by-products** as base materials for new gravel road structures. Often a relatively good frost insulation can be achieved with the (so-called) recycled structures. So far, different ashes, refined slags (sands), and mixes with fibre wastes and gypsum are found to be the best recycled materials for this purpose.
- No harmful effects on the groundwater quality have been observed after the construction.



## PAPER SLUDGE IN ROAD CONSTRUCTION

P.O. **Lahtinen**, Viatek Ltd / SGT, Luopioinen, Finland

J.A. **Fagerhed**, Fort James Suomi Oy, Nokia, Finland

M. **Ronkainen**, Viatek Ltd /SGT, Luopioinen, Finland

**Abstract:** Paper sludge is generated in large quantities by the paper industry. Costs of waste handling and waste taxes are the main reasons for the studies to develop commercial utilization of the paper sludge in Finland. The studies indicate that paper sludge gives new interesting options for the soil (e.g. road) construction. The properties of the paper sludge can be improved and adjusted for the target construction by mixing it with other industrial wastes (like ashes) and with commercial binder materials. In this way, for example, the road materials based on paper sludge can achieve the optimal combination of strength, bearability, resilience and frost susceptibility.

Fort James Suomi's deinking sludge has been studied by Viatek /SGT for utilization as a road construction material. The R&D project started in 1995 with laboratory tests on the materials in order to create suitable alternatives for the pilot construction. Two fiber-ash mixtures were chosen for the first pilot construction in 1996. The monitoring results obtained in 1997 were very promising. The results are the exclusive proprietary of Fort James Suomi Oy.

### 1. INTRODUCTION

The feasibility studies on the deinking sludge of Fort James Suomi (Nokia) for soil construction purposes started in 1994. In soil construction it is possible to utilize large volumes of deinking sludge in case the technical and environmental acceptability of the new materials can be proved. The first tests in the laboratory indicated that the most interesting usage areas of the materials would be in the road and land-fill constructions. Materials for road constructions were chosen as the first target of the actual R&D project.

Deinking sludge is a soft material, and not able to sustain the climatic and loading stresses without being mixed with additives and binder components. According to the laboratory tests, the most promising road construction materials would be the mixtures of deinking sludge and fly ash (named as fibre-ash), in certain proportions. As a result, two different fibre-ash mixes were chosen for the pilot road construction in Luopioinen (the village road called Rajalantie). The pilot construction was taking place in 1996. The pilot construction included testing of construction methods in material mixing, spreading and compaction, as well as the quality and properties of the pilot road structures.

## 2. DEVELOPMENT OF MATERIALS

Deinking sludge is composed of short fibres and paper fillers such as kaolin, talc and calcium carbonate. The solid material content of the deinking sludge is around 50 %. Deinking sludge was characterized by studying different types of deinking sludge for the development process. In regard to soil construction, there are clear differences between the properties of different types, and the best type was chosen for further studies. Mixes having different proportions of sludge, fly ash and binder have been passed through versatile tests. After this, cement was chosen to be binder in the final pilot construction materials.

The strength of the fibre-ash material can be improved by increasing the proportion of fly ash in the mixture. Also, the quality of fly ash will affect the strength. Figure 1 shows the test results (unconfined compressible strength, kPa) of three different fly ashes and each with three different proportions. Fly ash C gave best results and was chosen for the further studies and for the pilot construction.

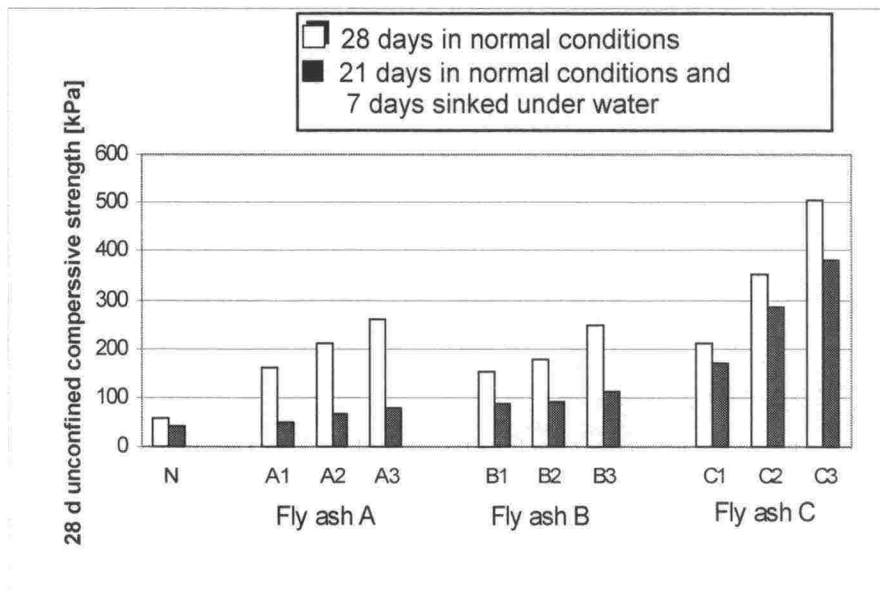


Figure 5: Compressive strength (10 % strain) of sludge with three different fly ashes

Figure 2 gives unconfined compressible strength test results (kPa) of the deinking sludge with different binders. The results show that cement was the most effective binder.

In road construction, the construction material shall be durable against the stress caused by the traffic and different climatic conditions (like different humidity, temperature and freeze-thawing conditions). The tests show that sludge-fly ash and sludge -cement mixtures could be possible, but in certain circumstances the freeze-thawing durability might become a critical factor. Without fly ash addition the sludge is slightly frost susceptible.

Therefore, a mix of sludge-fly ash-cement was chosen for the next stages of the R&D project with the objective to optimize the proportions of fly ash and cement in the mixes. After these screening tests a mix of certain proportioning with fly ash and cement was chosen for the further studies (the proportions are related to the humid weight of the sludge).

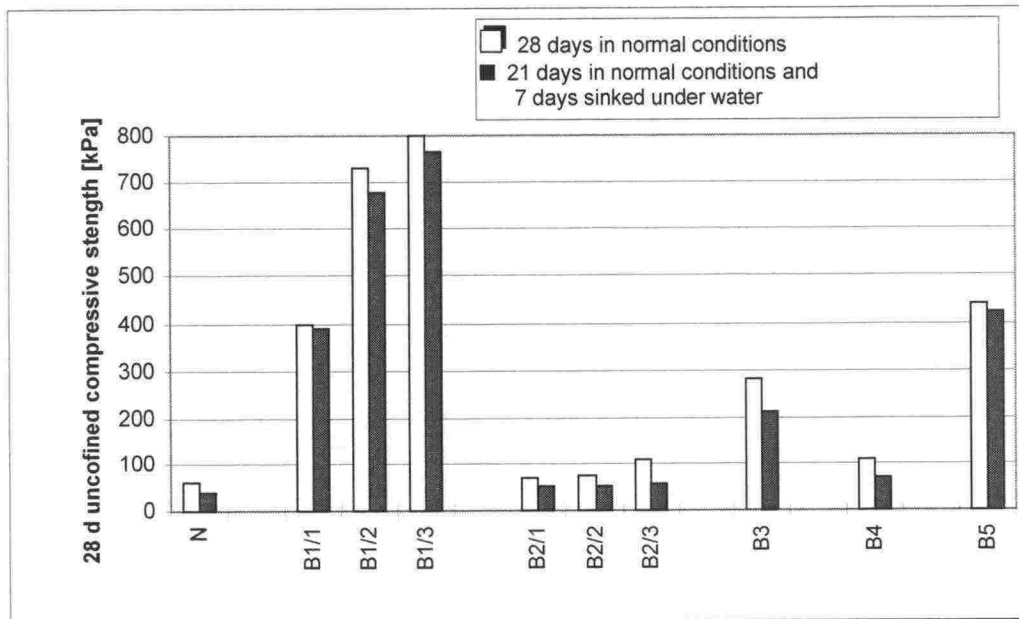


Figure 6: Compressive strength (10 % strain) of sludge with different binders

After the above mentioned screening tests, the technical properties have been tested by using 2 mixes: sludge + fly ash + cement and sludge + cement. In Figure 3 it can be seen, that the materials are strengthening in the course of time and that they resilient against very heavy loading stresses.

The tests conducted with the materials included water resistance, permeability, frost susceptibility and freeze-thaw durability. The results in Table 1 inform that in extreme circumstances there might develop problems.

Table 3: Compression strengths (kPa) after certain tests

	Sludge+fly ash + cement	Sludge+cement
Water resistance (impregn. with water)	210	260
Freeze-thaw durability	165	130
Permeability	380	240

The dimensioning parameters of the materials were defined, and these are shown in Table 2.

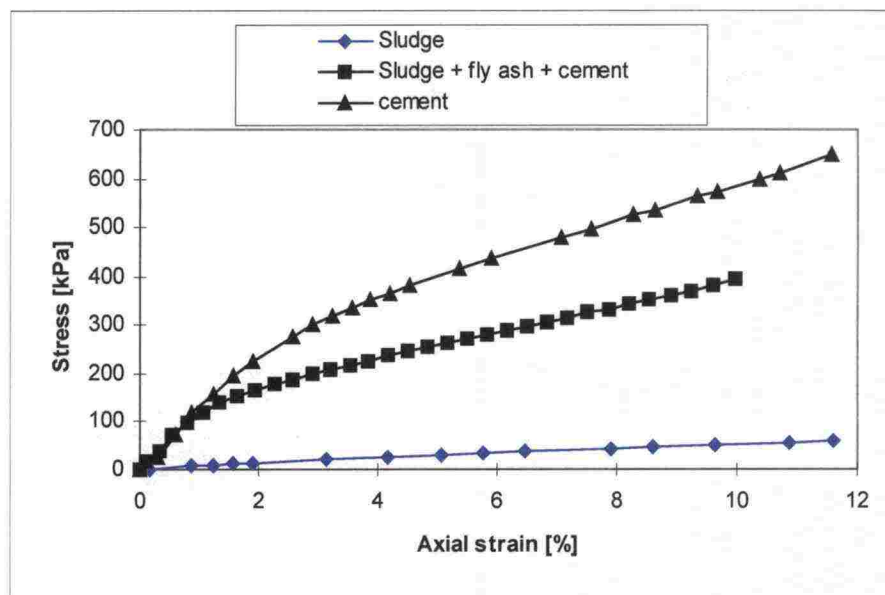


Figure 7: Stress vs axial strain

Table 4: Dimensioning parameters for pilot road construction

Parameter	Sludge+fly ash +cement	Sludge+cement	Sludge without binder
Compression strength, yield, kPa	170	190	-
Compression strength, strain 10 %, kPa	400	590	50
Thermal conductivity, W/mK	0,66	0,63	0,59
Water permeability, k, 10 <sup>-9</sup> m/s	7	6	3
Frost susceptibility, segr.potential, mm <sup>2</sup> /Kh	0,11	1,1	1,6

Also construction technical properties have been tested in the laboratory. The materials were tested above the optimal water content level because it is not economically viable to dehydrate the deinking sludge before construction. However, the water content of the mixes were clearly below the liquidity index of the materials. As a result the dynamic compaction method was noted to be more effective than the static method. The target level of the compaction degree was set to 95 % (proctor).

The environmental acceptability of the deinking sludge was tested with several standard methods: CEN, NEN, DIN and EPA (TCLP) tests. The mixes have been tested by analyzing the seepage waters after applying the 28 days' permeability test with acid (pH 4) leachate. The concentrations of harmful substances in the leachates from the deinking sludge were low or below the detection limit. The values were compared with the available Dutch and German criteria.



### 3. PILOT ROAD CONSTRUCTION

#### 3.1. The construction site

The village road Rajalantie in Luopioinen was badly damaged because of the frost heave during winters. The renovation of the village road being current the road was the ideal site for the pilot construction. Figure 4 gives information about the road's condition before renovation. The road had very thin construction layers. The frost susceptible soil consists of silt and silt-till.



Figure 8: Rajalantie in Luopioinen, Finland – before renovation

#### 3.2. The pilot applications

The basecourse layers above the filtering cloth consisted of the materials to be tested. There were two different fibre-ash mixtures and two different reference mixtures to be tested. Each material was to be spread at its separate road section. Each section was appr. 200 meters long. The design of the pilot construction is shown in Figure 5. The tested materials were as follows:

Section I	Fly ash with B1+B2
Section II	Sludge with fly ash and B1/4 (mix 1)
Section III	Crushed gravel
Section IV	Sludge with fly ash and B1/5 (mix 2)

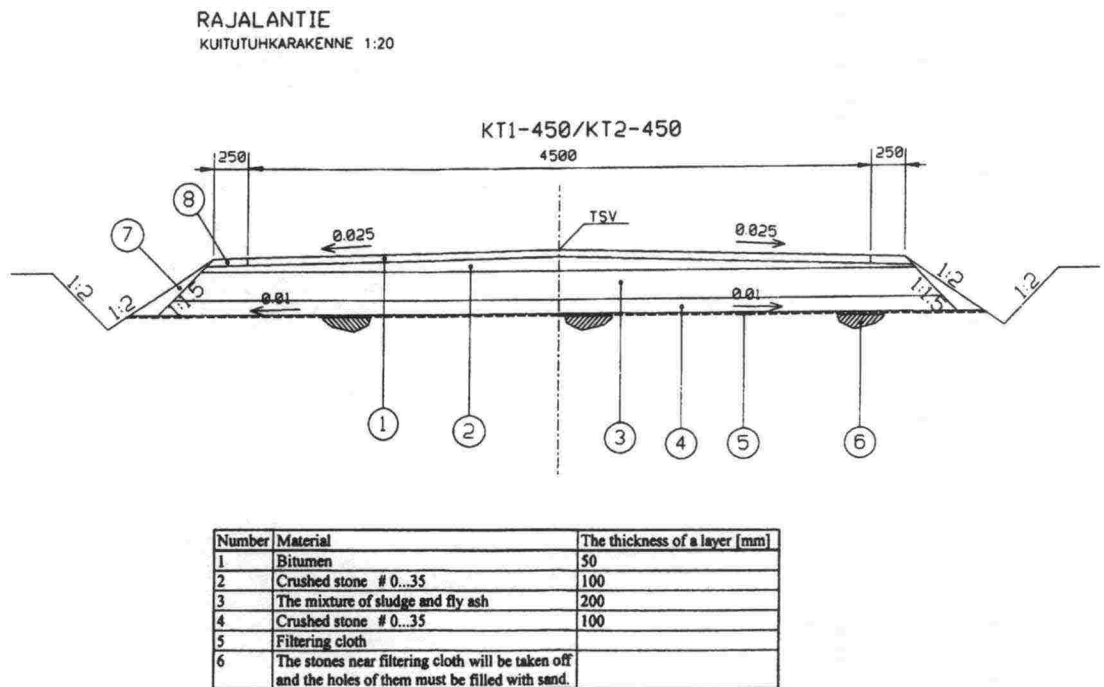


Figure 9: Design of the pilot construction

### 3.3. The testing of work methods

Before pilot construction it was seen necessary to test the work methods, i.e. the methods of mixing and compacting. The testing was conducted as a small scale test in practice in the factory area of Fort James Suomi in Nokia. Real alternative mixing and compacting equipment were used. The normal quality control was conducted during the testing, and the strength and plate loading tests after testing. As a result, the following choice was made for the pilot construction: a vibratory roller for the compacting, and a shovel mixer for the material mixing.

### 3.4. The construction

The materials were mixed on a separate field close to the pilot road site. Immediately after mixing the material was transported to the construction site for spreading. The asphalt spreader was used in order to leave an even, homogenous and loose layer. After spreading the layer was immediately compacted with a 4 ton vibratory roller 4 to 6 times. Final compacting was done on the covering crushed stone layer – Figures 6 and 7.





*Figure 10: Mixing of the fiber-ash components*



*Figure 11: Compacting on a crushed stone layer*

The construction with fiber-ash proved to be easier than expected. During the construction process the moisture content of the material stayed relatively constant. The working speed with the asphalt spreader was around 50 m/h, which can be achieved when the transport of materials is arranged efficiently. Spreading of material could have been made with other methods as well, like with a wheel-loader or with a blade grader. There were no difficulties in compacting either, and it was possible to use the road soon after the compacting. A downpour during the spreading did not impede or retard the compacting.

### 3.5. The long-term monitoring

The pilot construction was installed with geoinstruments in order to measure the moisture content, frost heave, settlements and temperature of the different sections. Additionally, the control programme included measurements of the bearing capacity and sampling for the testing of strength.

Now, the pilot construction is almost 2 years old and the monitoring results are very promising. Table 3 gives some of the monitoring results after the 1st year of construction.

Table 5: Some results of monitoring (geotechnical properties)

		Crushed gravel	Mixture 1	Mixture 2
E <sub>2</sub> -modulus <sup>1)</sup> , MPa	Shortly after construction	34/27	25/16	18/15
	1 month later	46/35	95/43	42/26
	Spring 1997	36/27	89/53	52/27
Frost heave (mm)	During the 1st winter	61...110	24...67	26...65
Av. settlement (mm)	During the 1st year	4	3	3

1) Plate loading test; 1st figure at the middle and 2nd figure at the edge of the road

The results after 1 year show that the bearing capacity of fibre-ash sections is 30 % to 50 % better than the bearing capacity of the reference section with crushed stone. The frost heave of the reference section was even 100 mm being the cause of cracking at the middle part of the road pavement. The fibre-ash sections were undamaged.

After the first year, the testing of the piece samples has proved that the properties of the fiber-ash materials have remained almost unchanged. In Figure 8 the section is opened for control. The fiber-ash layer was undamaged and strong, which indicates that the material is durable and resilient against the frost movements.



Figure 12: Fiber-ash section opened for control



The environmental monitoring has not given any results which could indicate harmful releases from the sludge or ashes in the environment. On the other hand, this could be expected after a time period of only one year. The seepage samples are taken from the drainage pipes, and the content of harmful inorganic substances is analyzed. As reference values there are the background contents based on the environmental studies at the site before construction (Table 4).

Table 6: Concentrations in the seepage water samples at the pilot construction site

	Unit	Place 1 <sup>1)</sup>				Place 2 <sup>2)</sup>		Criteria <sup>3)</sup>	
		Ref.	1	2	11	2	11	A	B
F <sup>-</sup>	µg/l	70,0	60,0	95,0	95,0	55,0	65,0	1500	
Cl <sup>-</sup>	mg/l	2,9	1,1	3,7	0,7	66,0	34,0		100
SO <sub>4</sub> <sup>2-</sup>	mg/l	14	4,9	24,4	13,0	48,0	52,0		150
TOC	mg/l	7,7	2,4	5,0	9,3	4,9	21,0		(2,0) <sup>4)</sup>
Ca	mg/l	19,2	8,3	21,7	16,9	36,1	31,7		100
Mg	mg/l	2,8	0,74	3,4	2,58	11,2	10,6		50
Al	µg/l	15,0	8,0	358,0	419,0	377,0	1370,0		200
As	µg/l	0,59	0,32	1,22	0,80	1,77	1,72	10	
Cd	µg/l	0,03	0,06	0,13	0,11	0,18	0,19	5	
Co	µg/l	0,11	<0,03	0,41	0,35	1,62	2,16	40	
Cr (tot)	µg/l	3,49	1,86	1,79	1,67	2,17	51	50	
Cu	µg/l	4,45	1,40	5,46	4,45	9,56	31,5	1000	
Pb	µg/l	<0,03	<0,03	0,45	0,45	0,37	1,37	10	
Ni	µg/l	2,14	0,99	3,22	1,95	5,52	6,23	20	
Fe	µg/l	<1,2	<1,2	420	328	380	1790		200
Zn	µg/l	39,0	22,0	73,0	52,0	16,0	43,0	3000	
Hg	µg/l	0,02	0,10	<0,01		<0,01		1	
Note	1	Ref. values from watersamples taken before construction. Other samples taken 1 month, 2 months and 11 months after construction							
	2	1 month after construction no sample could be taken because of drying; other samples taken 2 months and 11 months after construction							
	3	Criteria: Finnish drinking water limit values. A: substances considered hazardous or harmful on human health. B: Limit values for the technical / aesthetical quality							
	4	Target value, not a limit value; all samples exceeded this target value							

#### 4. CONCLUSIONS

The material studies and the pilot road construction have proved that it is possible to develop technically viable road construction materials based on the deinking sludges and fly ashes from incineration. In regard to the utilization, different types of sludges and ashes have different properties. Therefore, it is not possible to judge the materials' suitability for soil construction without specific characterization studies.

The properties of the industrial waste materials differ also significantly from the traditional stone materials used in soil construction. The applicability of waste materials for the soil construction has to be tested in regard to the geotechnical and environmental stress factors. Thereafter, the suitable waste materials have to be found right additives and binder materials in right proportions in order to develop economically, technically and environmentally optimal material mixes. Hand in hand with the material studies, the laboratory testing methods of Viatak/SGT have been developed and adapted to the specific requirements of the new materials.

The R&D project has shown that there are several alternatives to mix the deinking sludges with for the soil construction purposes. A mixture of sludge with fly ash - the fiber-ash material - is one of the most potential alternatives. The project has created new ideas and new possibilities for innovative material and method development for different target constructions. The continuity of the research and development work is important in order to create commercial materials and solve a part of the industrial waste problem.

## DEEP STABILISATION OF ORGANIC SOFT SOILS

P.Lahtinen, H.Jyrävä

*Viatek Ltd, Finland*

K.Kuusipuro

*Partek Nordkalk Oy Ab, Finland*

**ABSTRACT:** New binder mixtures for organic clay, gyttja and peat have been studied in a Brite Euram EuroSoilStab project. Over 30 different peat, gyttja and clay samples have been used as test materials. Cement, various limes and ashes, gypsum and blast-furnace slag have been used as binder components. Many factors contribute to the stabilisation of soil. Thus the stabilisation features of different binder mixtures cannot be accurately determined on the basis of soil type. Several well functioning mixtures of 2 or 3 compounds have been found during the project. Further research has been done on the mixture ratio, and both quantity and curing time have been optimised for each mixture on a test series. Additional information about stabilised soils has been obtained from the preloading and 3-axial tests and from studies on chemical reactions. Some results of these tests are presented in this paper.

### 1. Introduction

Stabilisation of peat and gyttja is much more difficult than stabilisation of clay. The greatest challenge is to find good, competitive binders which could be used for as many peat and gyttja types as possible. In EuroSoilStab project, over thirty different soil samples taken from both Finland and Sweden were tested to find the best 2 or 3 compound binder mixtures. The best mixtures were selected for further testing. In these tests the optimal mixture ratio was determined for each mixture. Also, tests on quantity of binder have been made, as well as tests on the effects of curing time. Other technical and environmental features of these materials will be researched later.

The binder mixtures used in the tests have been composed of various types of limes, cements and blast-furnace slags. Gypsum-based Finnstabi® has also been used. In addition, there are tests in which some of the compounds have been replaced by various ashes.

## 2. BINDERS AND TEST MATERIALS

Components used in binder mixtures are presented in Table 1.

Table 1. Components of binders

Code	Definition
F	Finnstabi® (Gypsum)
T	Slaking residue, Ca(OH) <sub>2</sub>
C or Ce	Portland cement
K or slag	Furnace slag (FIN)
M or slag	Merit (furnace slag SWE)
L	Quicklime, CaO
A or ash	Flyash (coal)

Most of these components are industrial by-products. Properties of soil types used in these tests are presented in Table 2. Both of the gyttja materials were found to be very hard to stabilise with lime-cement mixture, which is the most common binder in the Nordic countries. Thus it was important to find suitable binders for these soils as well.

Table 2. Properties of untreated clay/gyttja

Material	water content %	humus content %	$\varnothing \leq 2 \mu\text{m}$ fraction %
Clay /FI	99	0	86
Gyttja /FI	148	8,6	19
Clay /FI	66	4,9	30
Gyttja /FI	111	9,9	<5

The properties of unstabilised peats are presented in Table 3. In Kivikko (Peat/FI) there are two different peat layers. Peat used in this project is a 1:1 mixture of these two types.

Table 3. Properties of untreated peat

Material	water content %	LOI %	pH
Peat/FI	668	95	4,7
Peat/SWE	869	89	5,8



### 3. STABILISATION OF CLAY AND GYTTJA

#### 3.1 Test methods

Mixture ratios, optimisation of binder quantity and effect of curing time were investigated with unconfined compression tests (constant rate of strain 1%/min). Height of test specimens was 100 mm and diameter was 50 mm.

#### 3.2 Mixture ratios

Three combinations of binders were tested to investigate the effect of varying the mixture ratios. These combinations were gypsum-lime (FT), gypsum-lime-cement (FTC) and gypsum-lime-slag (FTM).

Tests for FT mixture showed that an increase in proportion of gypsum resulted in reduced strength. Raise in the proportion of lime did not have similar effects. In fact, in some cases stabilisation effect was even better than with FT 1:1 mixture (Figures 1 and 2). These results can be explained by the fact that lime reacts with clay minerals and can be used alone as binder but gypsum does not have similar property.

Unlike FT mixture, neither of the three compound binders gypsum-lime-cement (FTC) and gypsum-lime-slag (FTM) appeared to be sensitive to varying mixing proportions. Especially the results for FTC mixture tests were quite close to each other. Concluded, these tests show that proportions of 1:1 with FT mixture and 1:1:1 with FTC and FTM mixtures are quite close to the optimum ratio in these soil types.

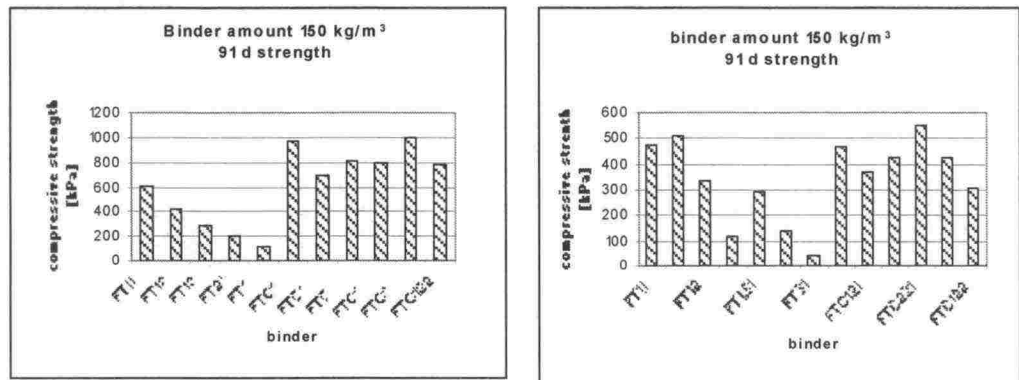


Figure 1. Proportions of mixtures. Stabilised clay, Kivikko (left) and stabilised gyttja from Porvoo (right), land

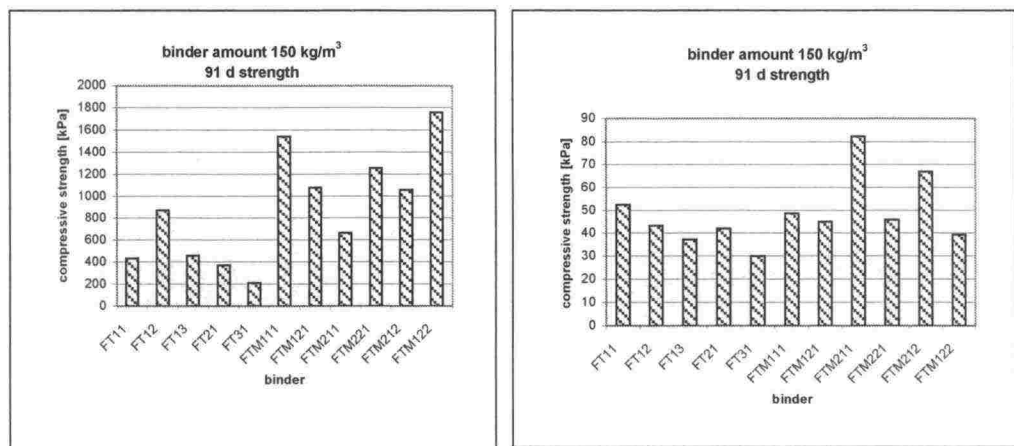


Figure 2. Proportions of mixtures. Stabilised clay of Uppsala (left) and stabilised gyttja of Enångren (right), Sweden



### 3.3 Optimisation of binder quantity

In binder quantity tests the amount of binder was gradually increased from 60 to 240 kg/m<sup>3</sup>. In almost all cases the higher binder quantity resulted in increased strength. It seems that in these high water content soft clays and gytija all binder can react if amounts from 60 to 240 kg/m<sup>3</sup> are used. The only exception was the FTC mixture used in Swedish clay. In this case, the strength did not increase after 160 kg/m<sup>3</sup>. The difference between FTC and FTK/FTM mixtures in clay is remarkable: when high amounts of binder are used, the slag based binders reach better strength than cement based binders. (Figures 3 and 4)

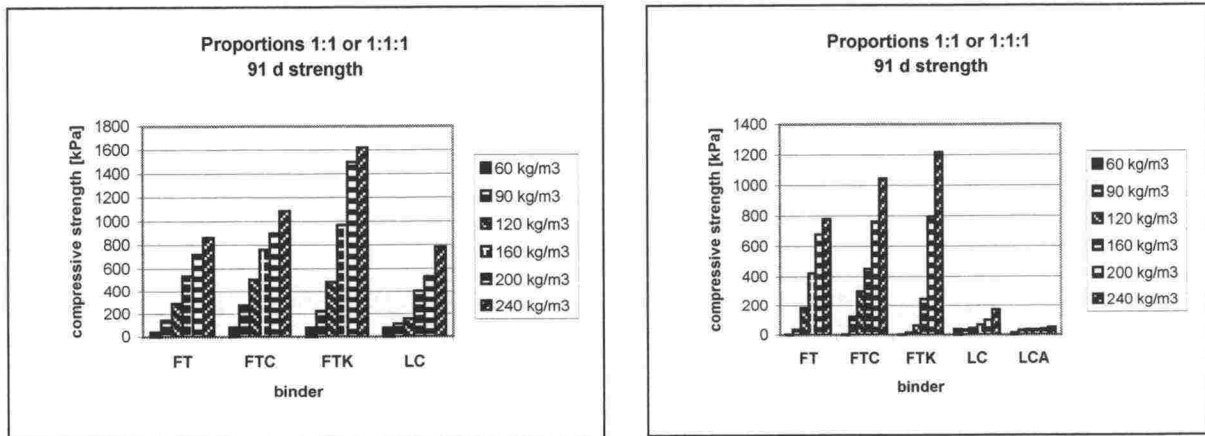


Figure 3. Optimisation of binder quantity. Stabilised clay of Kivikko (left) and stabilised gytija of Porvoo (right), Finland

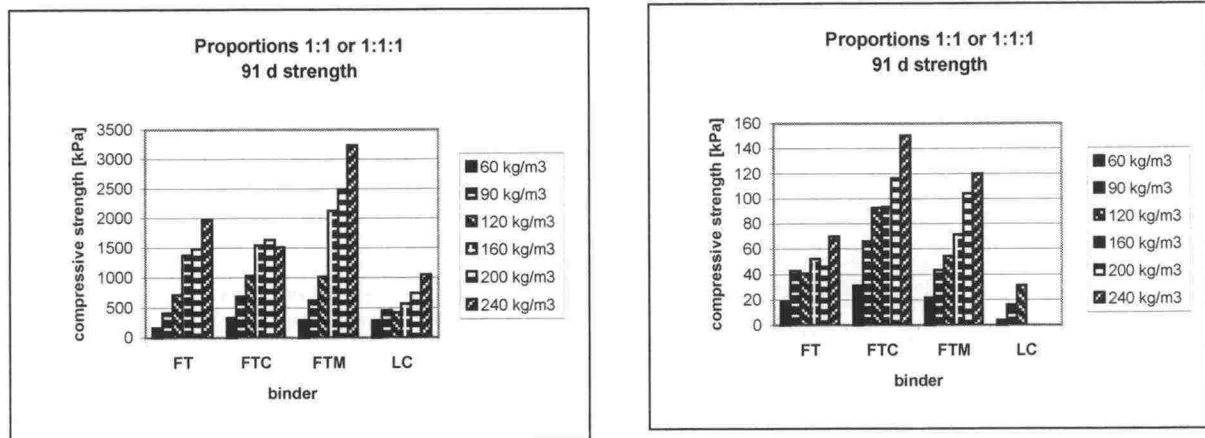


Figure 4. Optimisation of binder quantity. Stabilised clay of Uppsala (left) and stabilised gytija of Enånger (right), Sweden

### 3.4. Effect of curing time

In these tests, every binder mixture reached better strength as the curing time prolonged. This effect was especially strong with slag based FTK binder (Figure 5). However, lime-cement (LC) and lime-cement-ash (LCA) mixtures did not have any remarkable stabilisation effect in gytija.

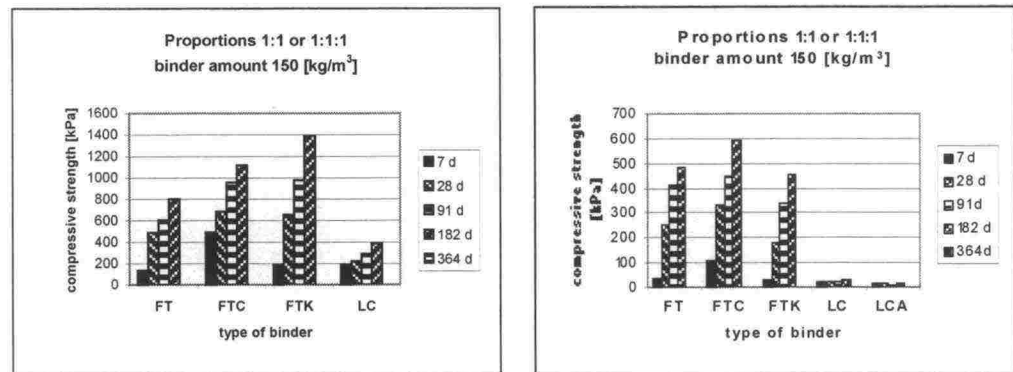


Figure 5. Effect of curing time. Stabilised clay of Kivikko (left) and stabilised gyttja of Porvoo (right), Finland

#### 4. CHEMICAL REACTIONS IN CLAY AND GYTTJA

The formation of various new reaction products due to soil-binder reactions was identified by X-ray diffraction (XRD) with help of X-ray fluorescence analysis (XRF) and scanning electron microscope.

It is a well known fact that the type of reaction products is same in hydration of cement and reactions between lime and clay minerals. The form of these calcium silicate hydrates is however gel or microcrystalline and therefore they cannot be identified by XRD method.

If lime, cement or slag is used with gypsum as binder, an ettringite will form. This can clearly be seen in both XRD analysis (Table 4) and SEM-pictures in which ettringite shows as needle-like structures (Figure 7).

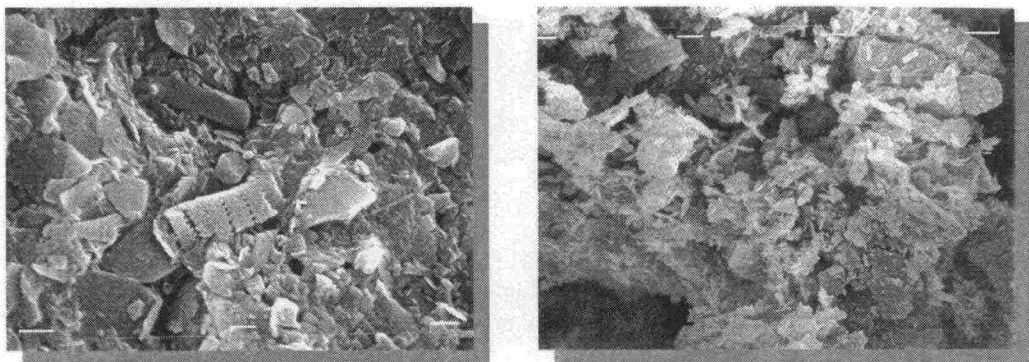


Figure 6. Left: Gyttja of Porvoo, Finland, magnification x5000. Right: lime-cement stabilised gyttja, magnification x3500.

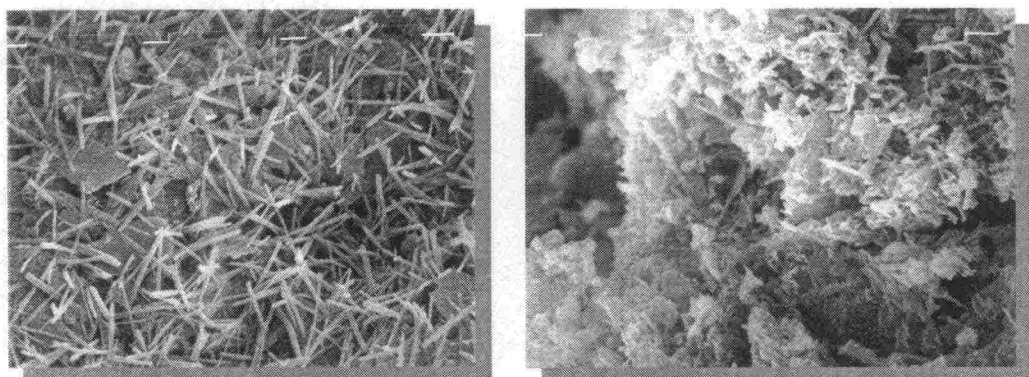


Figure 7. Left: Lime-gypsum stabilised gyttja, magnification x3500. Right: Lime-gypsum-slag stabilised gyttja, magnification x3500.

Table 4. Results from XRD-analysis.

Soil + binder	Ettringite	Ca(OH) <sub>2</sub>
	%	%
FT + Clay (FIN)	10	2
FTK + Clay (FIN)	7	0
LC + Clay (FIN)	< 1	1
FT + Gyttja (FIN)	9	1
FTK + Gyttja (FIN)	9	< 1
LC + Gyttja (FIN)	2,5	6,2

Some differences in structure can be seen if the SEM-pictures of unstabilised gyttja and lime-cement (LC) stabilised gyttja are compared (Figure 6). However, LC treated gyttja did not achieve any remarkable strength. This can also be seen in XRD analysis in which crystalline Ca(OH)<sub>2</sub> can be identified. This indicates that lime is unable to react with clay minerals due to the high humus and sulphur content of such soils.

## 5. STABILISATION OF PEAT

### 5.1. Test methods

The diameter of the peat specimens tested was 68 mm and the preload used during curing time was 18 kPa. These measures correspond to the preference test methods suggested during the EuroSoilStab project.

### 5.2. Mixture proportions

The peat and binder components were previously mentioned in Chapter 2. All the mixes tested composed of cement combined with ash, slag or Finnstabi®. Cement has been used as reference binder. Although peat from Kivikko, Finland (KI) seems quite similar to peat from Söderhamn, Sweden (SÖ), their reactions with binders are opposite to each other. As can be seen in Figure 8 the cement content determines the strength of stabilised KI-peat and the slag content determines the strength of SÖ-peat. This is true for both Ce+slag binder and Ce+ash binder. KI-peat reaches its highest strength with pure cement, but the strength of SÖ-peat with cement is less than 50% of the strength gained with Ce+slag binder. It should also be noticed that the strength of KI-peat stabilised with Ce+F binder remains constant although the ratio of Ce+F varies from 1:1 to 3:1 (Figure 8, below).

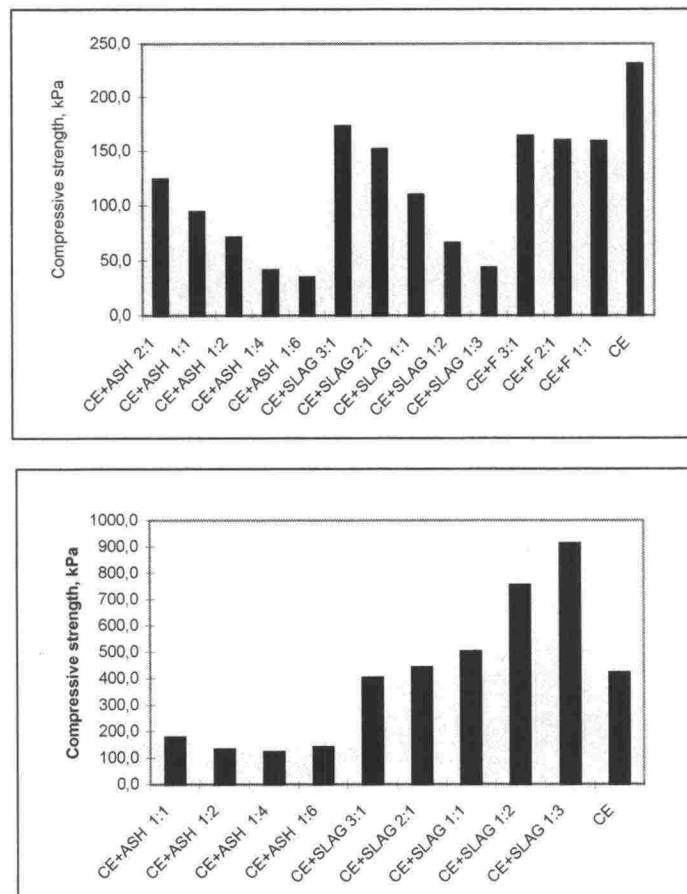


Figure 8. Effect of mix proportions on strength properties. Above: Peat of Kivikko. Below: Peat of Söderhamn

### 5.3. Binder quantity

In the tests the quantity of binder varied from 150 to 400 kg/m<sup>3</sup> but with ash up to 500 kg/m<sup>3</sup>. The increase of binder quantity affects much more peat treated with binders containing slag than it affects peat treated with pure cement. So, if binder quantities of 400 kg/m<sup>3</sup> are used, the strength of KI-peat treated with Ce-slag 1:1 binder reaches the strength of KI-peat treated with pure cement. Concluded, the type of binder giving the highest strength depends also on the quantity of binder.

### 5.4. Curing time

The curing time tests were done with 28, 90 and 180 days of curing. According to the results, it is clear that strength obtained with pure cement is very low after 28 days. Curing time between 28 and 90 is essential with binders Ce+slag and Ce+F. It has been shown that with slag-containing binders, the curing continues from 90 days to 180 days. These results clearly have shown how important it is to take the actual curing time into account when different binders are compared in practice.



### 5.5. The reference method of 3-axial tests on peat

A reference test did not exist for the 3-axial tests on stabilised peat. Therefore, a separate study was performed to compare the effects of different test methods on the results. The test variables were saturation, consolidation, loading speed and drained / un-drained situation. The test pieces were mixtures of KI-peat and binder, Ce+slag (1:1). Binder quantity was  $250 \text{ kg/m}^3$ , and curing time was 28 days.

The results of different test methods are given in Figure 9. The results show clearly that the chosen test method has a significant effect on the results. For example, the results obtained with saturation are quite close to each other, but without saturation there are significant differences. Concluded, it is recommended to use a saturated, consolidated and drained tests with a loading speed of  $0,02 \text{ mm/min}$ . The use of lower speed would take even several days with high highly compressible soils. However, the effect of loading speed on results needs further studies.

The tests were made only with one peat type and mix. It is found necessary to widen the scope of tests to peats at different stages of decomposition and with different types and quantities of binder.

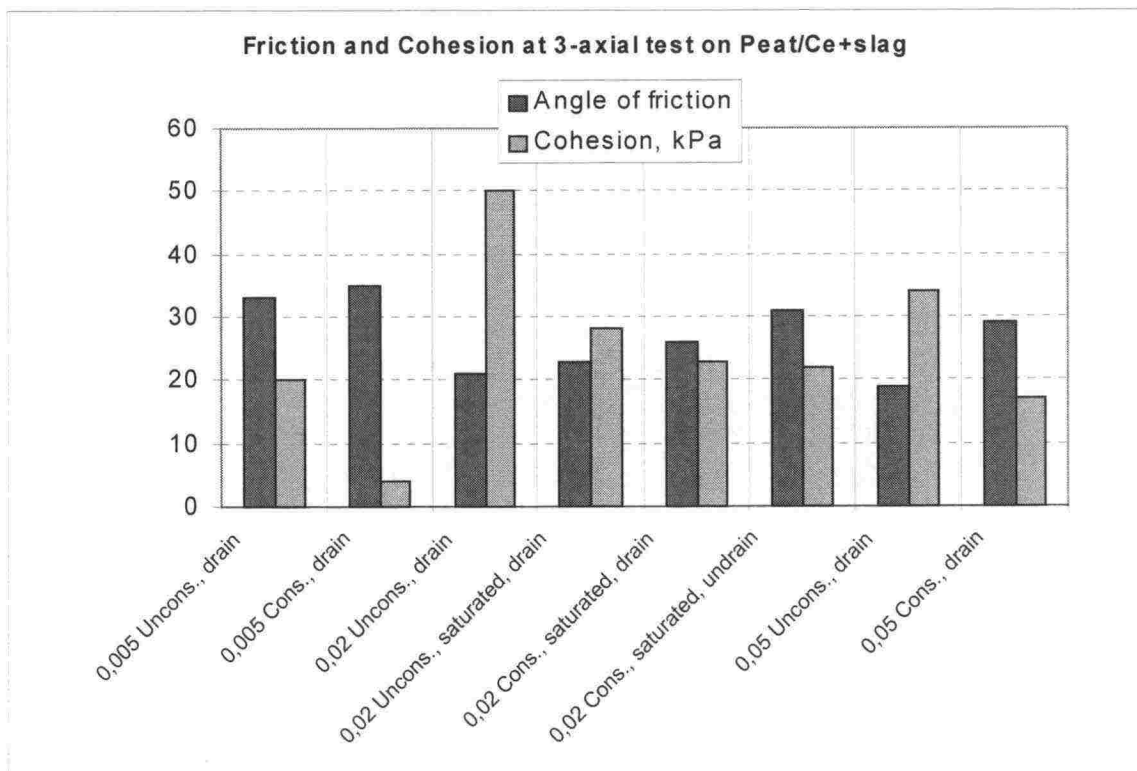


Figure 9. Cohesion and angle of friction with different methods of 3-axial tests on a peat mix

### 5.6. Effect of preloading on the strength of a stabilised peat

Preloading after stabilisation will compact the stabilised peat and increase its strength. In the laboratory the preloading is performed with a load of 18 kPa. In this research project, there was tested the effect of different loads; 20, 40, 60 and 80 kPa. It was noted that the stabilised peat was compacted very quickly, within 1 to 2 days, with each of the loads. After the initial compaction there could be noted practically no creep (Figure 10).

The initial compaction was decisively affected by the given load. The bigger the given preload, the better the obtained strength (Figure 11). Hence, it is recommended to use preloading in the practice. However, the amount of preloading is restricted by the stability of the embankment.

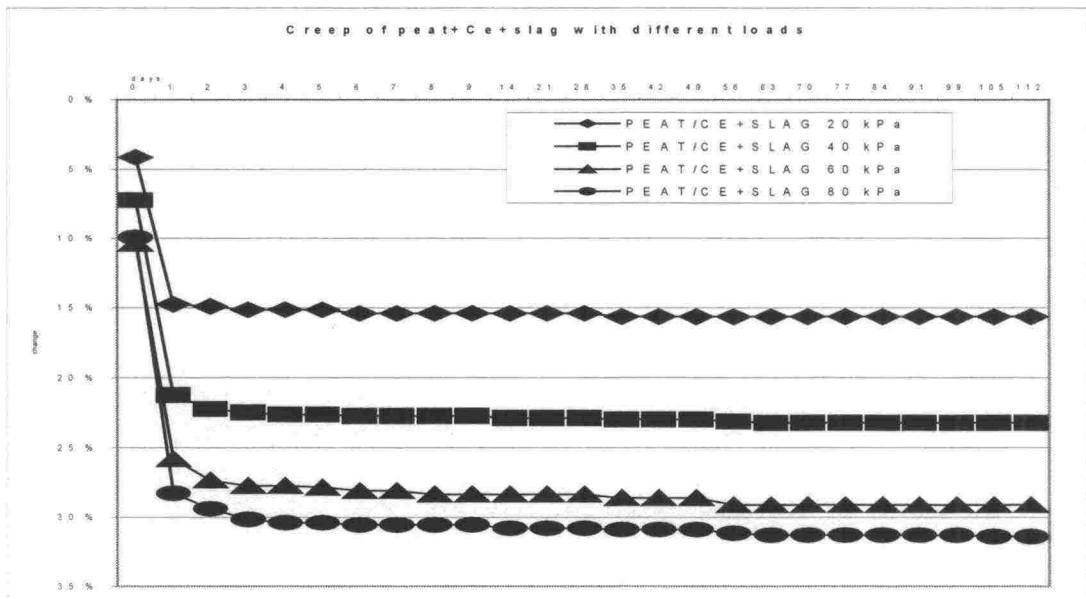


Figure 10. Effect of preloading on a stabilised peat (creep)

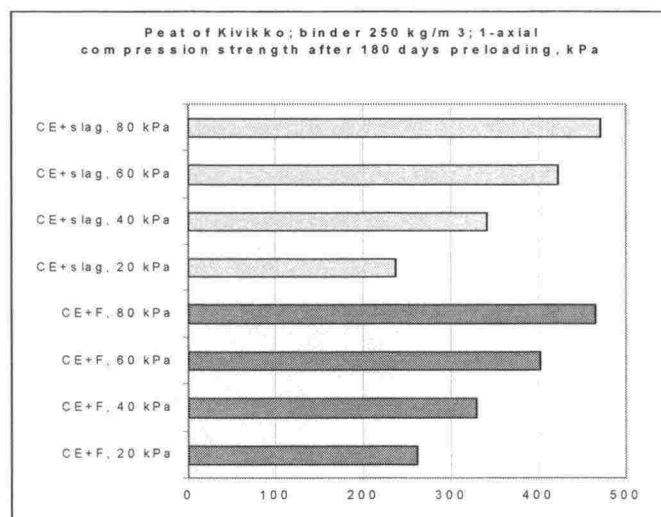


Figure 11. Effect of preloading on the strength of the stabilised peat

## 6. CONCLUSIONS

Lime-cement mixtures have been the most used binders in Scandinavian deep stabilisation. This project has shown that many other mixtures can be used as well. In fact, these new binders can be much more effective than lime-cement binders. This is true especially for gyttja and peat soils. Several conclusions can be drawn at this point of research:

1. The two and three component mixtures used in this project have proved their efficiency and value as binders and should be widely used and researched.
2. Two seemingly similar soils can be very different in terms of stabilisation features.
3. Binders composed of blast-furnace slag and gypsum combined with lime and cement are very potential. They open new possibilities for deep stabilisation method.
4. Laboratory tests are very important in finding suitable binders for various soils. Successful designing of deep stabilisation should also include optimisation of binder quantity and curing time.
5. Preloading has a clear effect on the stabilised peat. In practical situations the preloading can be varied to obtain the target strength with a lowest possible amount of binder.

## NEW METHODS FOR THE RENOVATION OF GRAVEL ROADS

P.O. Lahtinen

*Viatek Ltd / SGT, Luopioinen, Finland*

H. Jyrävä

*Viatek Ltd / SGT, Luopioinen, Finland*

H. Suni

*Finnish National Road Administration (FinnRa) / R&D, Oulu, Finland*

**ABSTRACT:** In the 1990's, FinnRa and Viatek Ltd have been developing new economic and sustainable methods to solve frost and bearing capacity problems of gravel roads in Finland. The new methods have been widely tested at various test sites. The results indicate that the technically and economically best methods are based on the use of industrial by-products in the structure layers or in the stabilisation of old structures, on the stabilisation in general and on the use of different geo-reinforcement solutions. Methods based on insulation and drainage are often needed though not as effective and economical as the new alternatives. The most interesting industrial by-products include blast-furnace slags, fly ashes, flue gas desulphurisation residues (FGD) and gypsum for the stabilisation of an old structure, and ashes and their mixes with fibre wastes for the base materials of road structures.

### 1. Problems in connection with gravel roads

The typical problems of gravel roads are the frost susceptible subsoil with low bearing capacity, the thin and uneven structural layers that will be partly mixed with the subsoil during thawing, and the groundwater level close to the soil surface. The typical problems are illustrated in the Figures 1a and 1b.

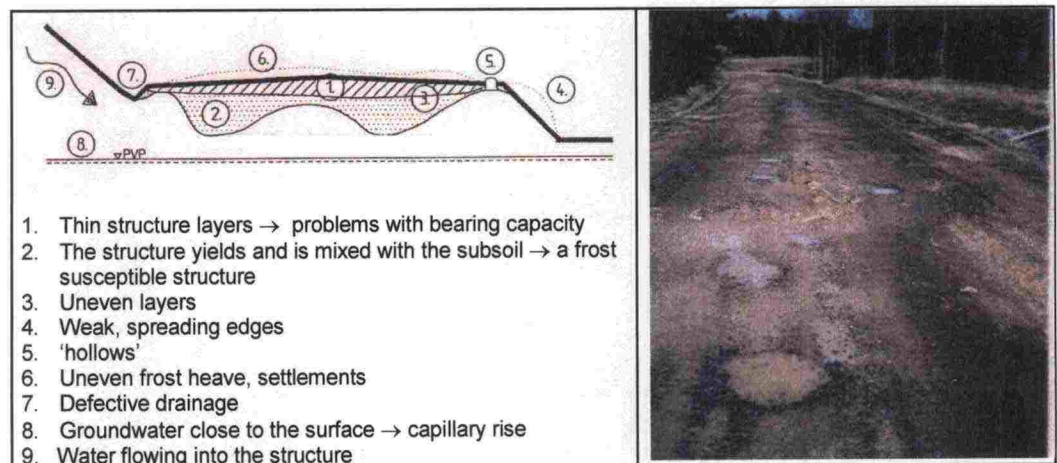


Figure 13a: Problems of the gravel roads

Figure 1b: A road before renovation



The gravel road project started in 1990. The first stage was to study problems in connection with gravel roads at 52 different test sites. The test sites were chosen amongst the most problematic road sections in Savo-Karjala and Häme regions. The investigations at the test sites addressed the problems and damages as well as the current structures and the soil conditions. The main types of problems could be determined and classified on the basis of the results. New methods to solve the different types of problems were developed at the second stage of the project.

## 2. Development of recycled materials

Before construction, the development of new, recycled materials and structures based on the recycled materials (later RM-structures) require laboratory investigations through many stages. Firstly, certain critical properties must be tested to find optimum, technically viable mixes of materials. This is followed by tests on all important technical properties, on susceptibility to weather conditions, on load resistance and on environmental acceptability. Figure 2 is describing the principles of the development process:

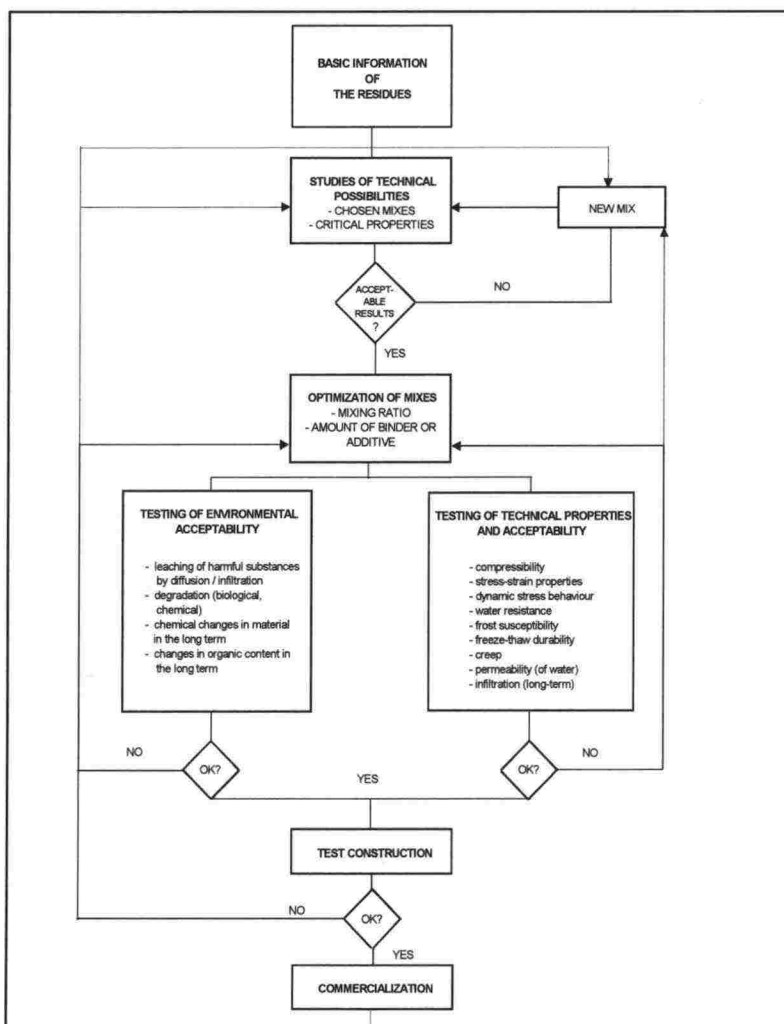


Figure 2: Development process for recycled materials in soil construction applications

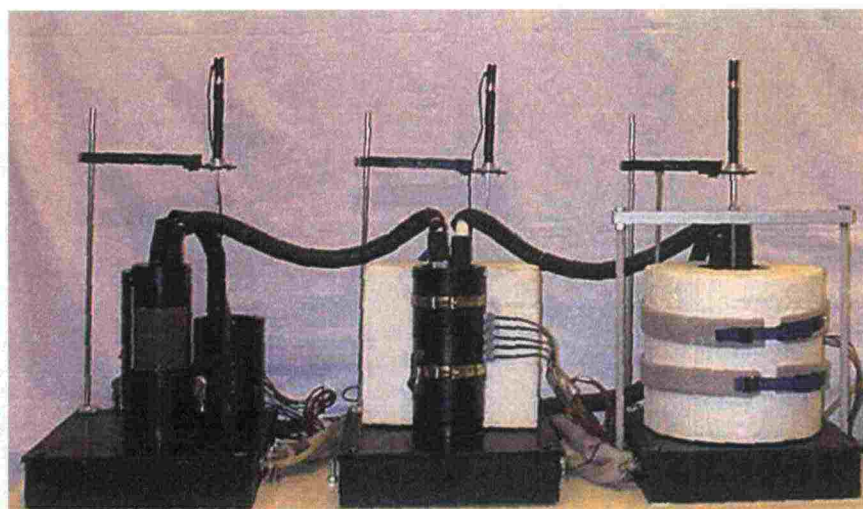


Figure 3: Frost heave testing. Equipment

Viatek Ltd/SGT has developed test combinations that will give more information about the long-term load behaviour of construction materials than the separate tests. The frost heave test is an example - the equipment for which is shown in Figure 3 above.

### 3. Stabilisation of old structures

Stabilisation of old structures has been studied and tested for example with the eight different test structures in Table 1. In many cases the construction process had following work sequences: At first the surface of the old structure was homogenised to a depth of around 200 mm. After this the binder materials was spread on the surface and mixed with the material of the old structure. A spring harrow and/or a road grader was used at sites 1, 2 and 3. A digging machine was used at site 6, and a milling machine at other sites. After compaction, a crushed stone surface of 100 mm was spread on the structure.

Follow-up studies have been carried out at each of the test sites. The studies included both monitoring of the road condition and measurements of load-bearing capacity and the surface level. Temperatures, frost heaves, settlements and moistures were also measured with electric geo-instruments. Six or seven years after the construction a part of the structures were opened and checked, and samples taken for the laboratory tests.

At older test sites where spring harrows were used as mixing equipment the mixing results were not found quite satisfactory. However, this did not affect the outcome, which could be noted as the quality of the older test sites was compared with the others. The performance of many of the test sites has been as anticipated: the structures have no damages, the test sections have improved bearing capacity and trafficability, and no harmful, uneven frost heave has been noted. Until now, the follow-up studies at older test sites have been continuing 5 to 6 years.



Table 1: Stabilisation of old structures.

Site	Binder	Year of construction	Binder quantity (%), layer thickness (cm)	Compression strength MPa		
				28 days <sup>1)</sup>	28 days <sup>2)</sup>	in 97-99 <sup>3)</sup>
1	Polvijärvi, Ruvaslahti pt 15798	1991	10 %, 15 cm	3,4 (30 days)	-	1,1 - 1,8
2	Kuorevesi MT 3424	1992	30 %, 15 cm	0,3/0,6 <sup>5)</sup>	-	2,5 - 3,8
3	Kuorevesi, MT 3424	1992	6,5 %, 15 cm	1,4 <sup>6)</sup>	-	0,4 - 0,9
4	Kuorevesi, MT 3424	1997	7 %, 30 cm	1- 1,5	1,3 - 1,6	~ 1
5	Kuorevesi, MT 3424	1997	5 %, 20 cm	3 -	1,6 - 1,7	3 - 6
6	Kangasala, Savontie MT 311	1992	12 %, 20 cm	2,1 <sup>4)</sup>	-	0,9 - 1,1
7	Laitila	1998	6 %, 25 cm	1,8	0,5 - 0,7	0,5 - 0,8
8	Laitila	1998	15 %, 20 cm	1,7	0,4 - 0,6	0,4 - 1,2

1) Preliminary laboratory tests

2) Test pieces moulded during the construction work to estimate the actual performance after construction

3) Samples taken from the structure layers in 1998/1999; min. 1 year after construction

4) Result after 30 days of curing: binder quantity 12 %

5) Granulated blast-furnace slag 30% + Cao 0,6% (30 days / 90 days)

6) FGD-mix 8% (30 days)

F = Binder of Kemira Pigments Oy, based on gypsumtype by-products: Finn-stabi

Slag. = Blast-furnace sand by SKJ

Lohjamix = A binder mix based on by-products of energy production

THK<sub>2</sub> = Secondary hydrated lime

Slag (S) = Fine-grained blast-furnace slag by SKJ

Merit = Fine-grained blast-furnace slag by Merox Oy: Merit 5000

Ash (IVO) = Coal fly ash from IVO, Meri-Pori power station

#### 4. Recycled materials in the structure layers

Recycled materials have been tested in more than 20 test structures. The materials have been based on different fly-ash types, on fibre-ash mixes and on mixes of biotite + crushed stone (Table 2).

The oldest test structures were constructed by smoothing the old road surface before the recycled material layers were spread and compacted. The construction was started by pushing the surface material as banks on the road sides. The side banks acted as supports for the layers of recycled material during compaction., see Figures 4a and 4b. The thickness of the 'recycled structure' is from 200 to 250 mm. A surface layer of 100 mm was spread on the recycled structure.

All material mixes were made before spreading. Different mixing methods were tested. The biggest problems of the construction process included the heterogeneity of the by-product's properties, the arrangement of storage and mixing for dry pulverised materials like ashes, and the efficient mixing of fibre waste and fly ash. However, with help of the best available equipment the problems could be solved. For example, the fibre waste and fly ash can be mixed with a platform-mixer, and the mix proportions as well as the moisture of fly ashes can be sufficiently managed when using a batch-mixer.

Table 2: Examples of test sites with recycled soil construction materials

	Site	Material	Year of constr	Binder type and quantity	Compression strength, MPa		
					Lab 28 d <sup>4)</sup>	28 d <sup>5)</sup>	97-99 (min after 1 year)
1	Ruvaslahti	Biotite-crushed stone	1991	Ce + slag (12 %, 2:1)	n.1,3 <sup>6)</sup>	-	1,4 - 2,4
2	Kangasala MT	Peat-ash, coal ash	1992	4 % Ce + slag	1,4	-	0,9 - 1,5
3	Kiuruvesi	biotite-gypsum 1:1	1991	Ce + slag (12 %, 2:1)	0,8	-	0,1 - 0,2
4	Koria pt 15467	Ash (Voikkaa)	1998	none	16,9	3,0	1,7 - 4,5
5	Koria pt 15467	Ash (Anjalankoski)	1998	Ce 3 %	8 - 9	3,0	2,9
6	Koria pt 15467	Ash (Lahti)	1998	F+THK <sub>2</sub> 6 %	4,1	2 - 3	2,6
7	Koria pt 15467	Ash from deposit (Myllykoski)	1998	Ce 6 %	0,9	1,0	0,9
8	Jämsä pt 16569	Fibre-ash (Mänttä) <sup>1)</sup>	1998	Ce 7 % *	0,6	0,4	0,4
9	Jämsä pt 16569	Fibre-ash (Nokia) <sup>2)</sup>	1998	Ce 7 % *	0,3 - 0,4	0,4	0,5
10	Jämsä pt 165 69	Fibre-ash (Jämsänkoski) <sup>3)</sup>	1998	Ce 6,25 % *	0,6 - 0,7	0,5 - 0,6	0,4
11	Jämsä	Ash (Jämsänkoski)	1998	Ce 6,2 %	2,3	1,5	0,8
12	Jämsä	Ash (Kaipola)	1998	Ce 4 %	3,9	1,5 - 2	0,9
13	Laitila pt	Coal ash (Fortum) <sup>7)</sup>	1998	F+THK <sub>2</sub> 3 %	2,2	2,0	3,0
14	Laitila pt	Mixed ash (UPM)	1998	F+THK <sub>2</sub> 5 %	2,1	~1	0,9

\* = exceptionally based on the wet weight of the material

Metsä-Tissue fibre waste + Mäntän Energia fly ash 45:55

Fort James fibre waste + Kaipola fly ash 100:30

Jämsänkoski fibre waste + fly ash 20:100

dry ashes have been used in the preliminary laboratory tests

Test pieces made in connection with construction at the test sites to estimate the actual performance of the structures; moisture added to the ashes before construction.

The binder mixes used in the laboratory tests: a. slag+Ce 1:1, 10 %: 1,1 MPa, b. slag+Ce 1:2, 15%: 1,4 MPa

Ash layer 350 mm





Figure 4a: Preparing for construction

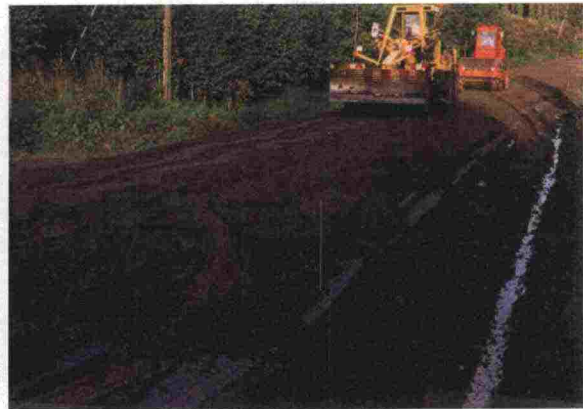


Figure 4b: Finishing an ash-structure

Geo-instruments were installed into the test structures, and the follow-up studies and measurements have been carried out. The results have shown that the structures are performing as anticipated. The bearing capacity of the roads has remained at an acceptable level, and there are no observations of any harmful frost heave. The condition and trafficability of the roads have improved essentially. The major problems have been found only in connection with the biotite material, the strengthening of which is quite difficult. On the other hand, for example, the peat-ash structure (Site 2, Table 2) has not shown any deterioration during the 7 follow-up years; see also Figure 5.



Figure 5: Open structure - after 7 years of renovation

## 5. Structures with geotextiles

Renovation methods based on geotextiles have proved to be technically feasible and cost effective as well as easy and quick to use. The project has been testing both nets and woven geotextiles in the test structures. In most of the test constructions the geotextile has been spread over the whole width of the road, Figure 6. However, at one of the test sites the geotextile was used as an reinforcement of the road edge.

The geotextiles have been equipped with extension stripes in order to study and measure the tensions developing in the geotextile during the use of the construction. After several years of use, there have been no major damage to the geotextiles that have been tested. For example, the developed tensions have been relatively small in comparison with the strength of the materials. During the test period also the road sections with these geotextiles have proved to be durable and in need of much less maintenance than before.



Figure 6: Geotextile spread on an embankment

## 6. The economy of the new structures

The cost benefits of the new structures has been assessed with help of the oldest test structures. The calculations have been made by considering costs of construction and maintenance within a time span of 15 years. It has been assumed that the producers' price for the industrial by-products is 0 (zero) FIM. Transport and handling costs etc. have been assessed on the basis of prevailing competitive price level.

The new methods have been compared with the traditional methods based on crushed stone and crushed stone with filter cloths. The comparison of costs in Figure 8 indicates that the structures with recycled materials and the stabilisation of an old structure are the most cost effective methods for the renovation of the gravel roads. The savings can be even as high as 50 %.



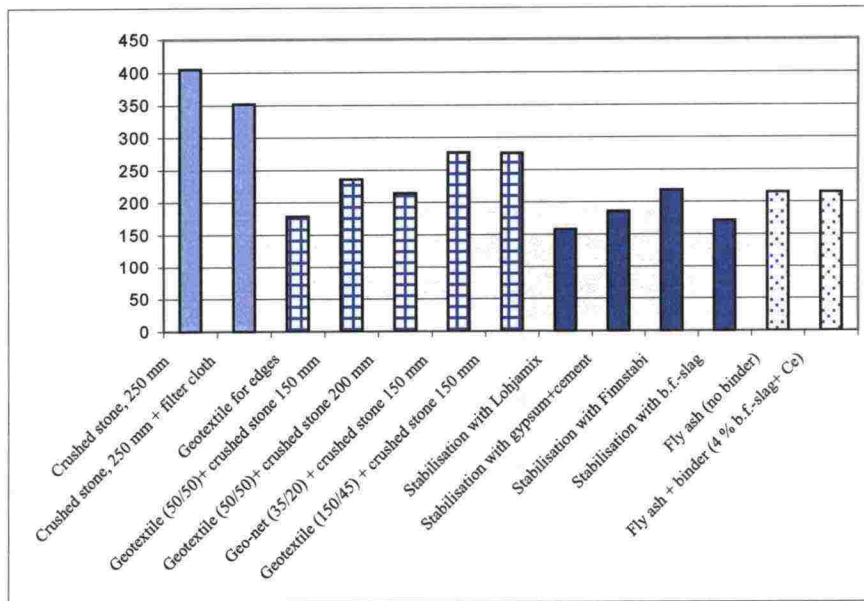


Figure 7: Comparison of the long-term costs of different structures (1000 FIM per 1000 metres of road)

## 7. Conclusions

The basic problems of the gravel roads, the frost heave and the weak bearing capacity in the spring, usually result in really bad traffic conditions. The traditional renovation methods of the gravel roads are expensive and require significant amounts of un-renewable natural stone materials. Therefore, development of environmentally friendly and cost effective renovation methods is necessary, even inevitable. The gravel road project has succeeded in the development of several viable solutions to renovate gravel roads:

- Both technically and economically excellent results can be achieved by stabilising an old structure with help of binders based on different industrial by-products. So far, the best by-product components for binders are different slags, gypsum and ashes.
- Another competitive group of solutions is based on the recycling of industrial by-products as base materials for new gravel road structures. Often a relatively good frost insulation can be achieved with the (so-called) recycled structures. So far, different ashes, refined slags (sands), and mixes with fibre wastes and gypsum are found to be the best recycled materials for this purpose.
- Industrial by-products are the basis for many excellent solutions, but extensive laboratory tests and full-scale field tests are needed to ascertain the final quality of the materials.
- In construction with recycled materials also the work methods and equipment have to be adapted for their use. Otherwise the final outcome might not be as successful as required. Especially the storage and handling of recycled materials call for further development.
- Quality control is of great significance for the outcome. Construction with recycled materials requires special control of the water content and compacting of the materials.
- No harmful effects on the groundwater quality have been observed during and after the construction.
- The structures based on geotextiles have also proved to be competitive, both technically and economically.

## USE OF INDUSTRIAL WASTES IN THE CONSTRUCTION OF LOW-VOLUME ROADS

Pentti O. Lahtinen<sup>1</sup>

Harri Jyrävä<sup>2</sup>

Heikki Suni<sup>3</sup>

### Abstract

Many types of industrial waste can be effectively used in soil construction applications instead of depositing them into landfills. Everywhere in the world road construction offers best possibilities for applications because of the need for high volumes of material. This has been noted by Viatek Ltd / SGT during its long-term research and development work on soil construction applications based on industrial wastes.

Industrial waste can be used as structural material for different types of road courses or as stabilizers of old structures that need to be renovated. There are many possibilities; for example as base courses or for frost insulating, weight reduction, drainage or sealing purposes. Most types of industrial waste are quite versatile and can be used to simultaneously solve different types of problems. One of the typical applications is the frost insulating and weight reducing base course.

Many properties of the new structures based on industrial waste justify their use instead of conventional structures based on natural stone materials. Usually, the justification is most evident because of the technical and cost advantages from the fact that the new structures can be made thinner and with less material than the conventional ones. This is specially useful regarding the low-volume roads. Also, recycling of industrial waste in soil construction will promote the principles of sustainable development when saving non-renewable natural resources and reducing the volume of waste deposited in landfills.

### Typical problems with low-volume roads

The typical problems with low-volume or gravel roads include the frost susceptible subsoil with low bearing capacity, the thin and uneven structural layers that will be partly mixed with the subsoil during thawing, and the groundwater level close to the soil surface. The typical problems are illustrated in the Figures 1a and 1b.

---

<sup>1</sup> Development Manager, Viatek Ltd/SGT, Luopioinen, Finland

<sup>2</sup> Project Manager, Viatek Ltd/SGT, Luopioinen, Finland

<sup>3</sup> Senior Research Manager, Finnish National Road Administration/R&D, Oulu, Finland



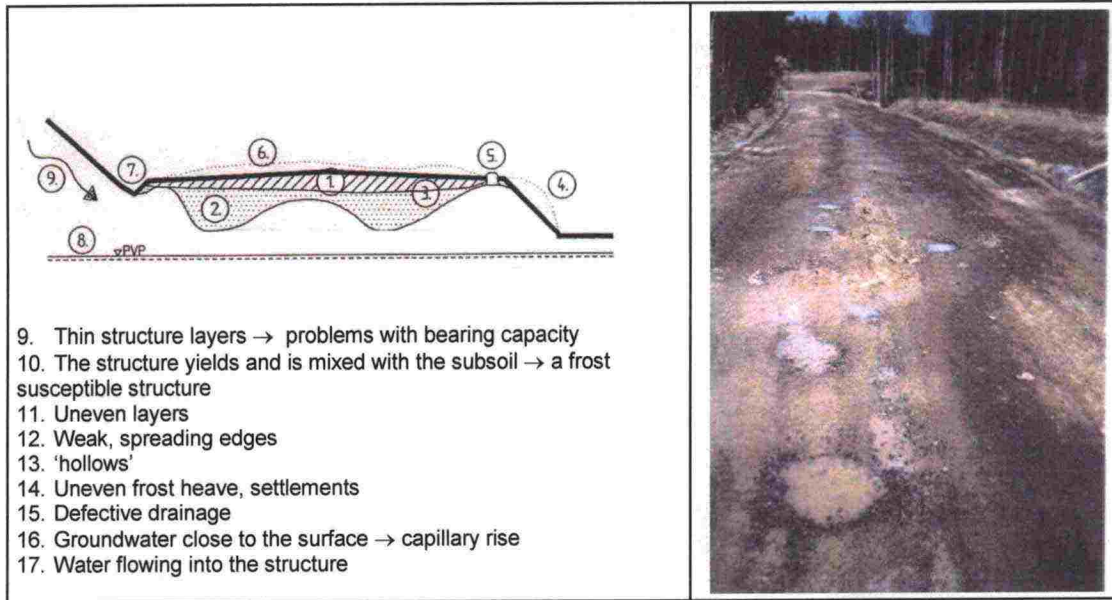


Figure 14a: Problems of the gravel road

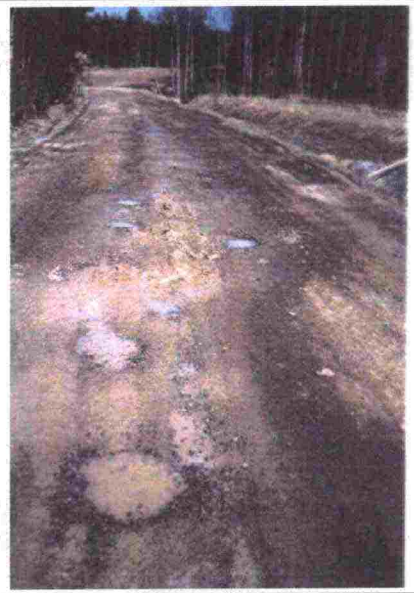


Figure 1b: A road before renovation

## Recyclable industrial wastes

Recyclable industrial waste can be found within many industrial branches: energy production, mining, chemical, steel, and the pulp and paper industry. The most significant waste types are the following ones;

- ashes from power stations (coal, peat and misc. ashes);
- slags, sands and sludge from steel industry (e.g. blast furnace slag, steel slags, steel smelting sludge);
- gypsum from chemical industry (e.g. phospho-gypsum, titanium-gypsum);
- sludge from pulp and paper industry (fiber sludge).

There are also other waste materials that can be used, but mostly as a component in the material mix to improve the properties of the basic material; for example, the filter waste from  $\text{CaCl}_2$ -production.

Within and between the groups above, there are essential differences between the individual types in regard to their characteristics and properties and, consequently, their scope of usage in soil construction applications. For example, the power stations produce various ashes, the characteristics of which depend on the properties and quality of the feedstock and the parameters of the incineration process itself.

In stabilization it is essential to use materials that possess cementing properties. Some of the ashes are pozzolan that need addition of moisture and certain additives to become cementing. Some of ashes are self-cementing. Therefore, the areas and methods of application will be different with different ashes.

With mixtures of 2 to 3 different waste materials it has been possible to develop new construction materials – i.e. recycled materials – having certain targeted properties (Figure 2). One of the best examples is the fiber-ash material, a mixture of fiber sludge and fly ash that has been tested in road and landfill constructions. Fiber-ash structures have an excellent combination of geotechnical properties: they have low weight and high bearing capacity, are resilient, frost insulating, not susceptible to frost and easy to apply during construction.

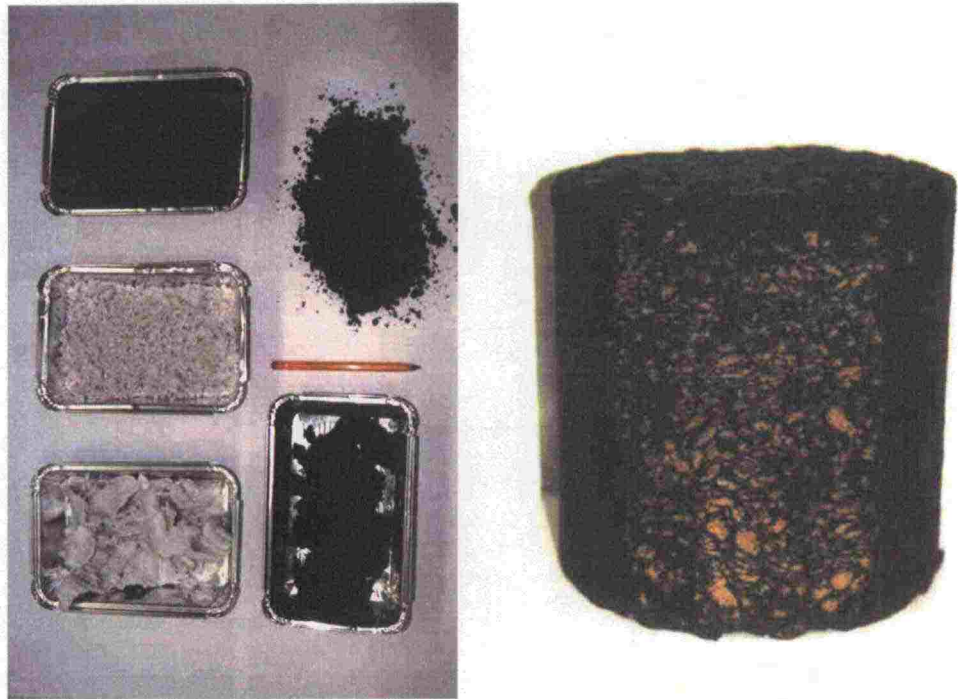


Figure 2: Industrial waste and a test piece

### Development of materials

Before construction, the development of new, recycled materials and structures based on the recycled materials (later RM-structures) require laboratory investigations through many stages. Firstly, certain critical properties must be tested to find the optimum, technically viable mixes of materials. This is followed by tests on all important technical properties; susceptibility to weather conditions, load resistance and environmental acceptability. Figure 3 illustrates the principles of the development process.

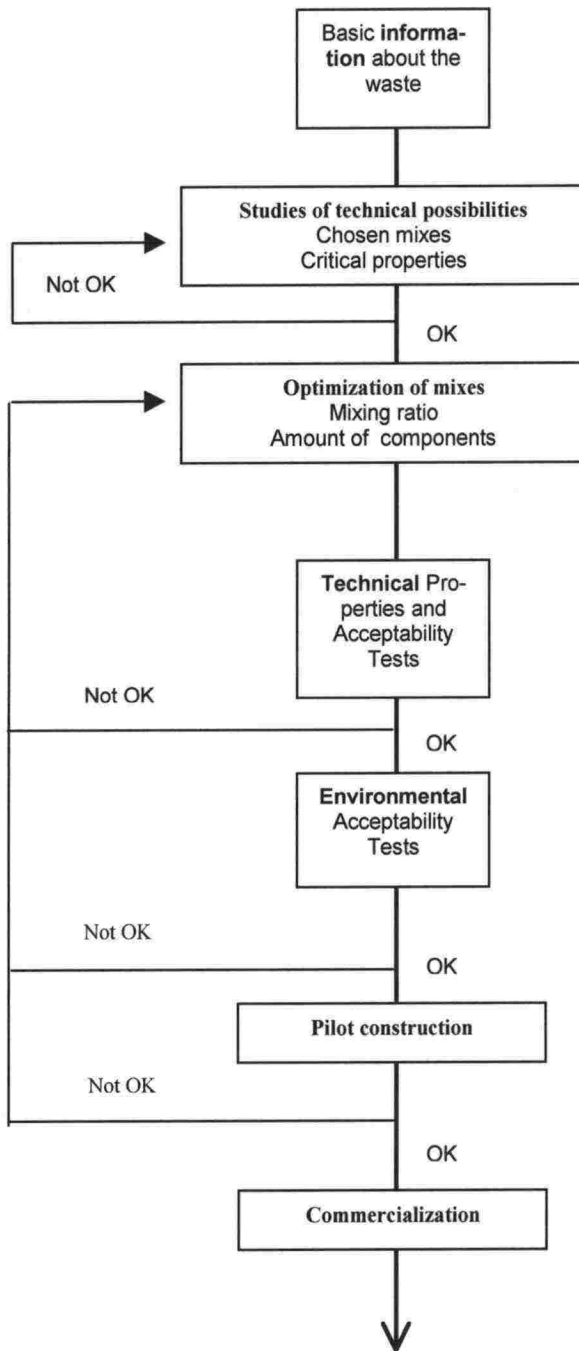


Figure 3: Development process for recycling materials in soil construction applications

Viatek Ltd/SGT has developed test combinations that will give more reliable information about the long-term load resistance of materials than the separate tests. The frost heave test is an example, the equipment for which is shown in Figure 4.



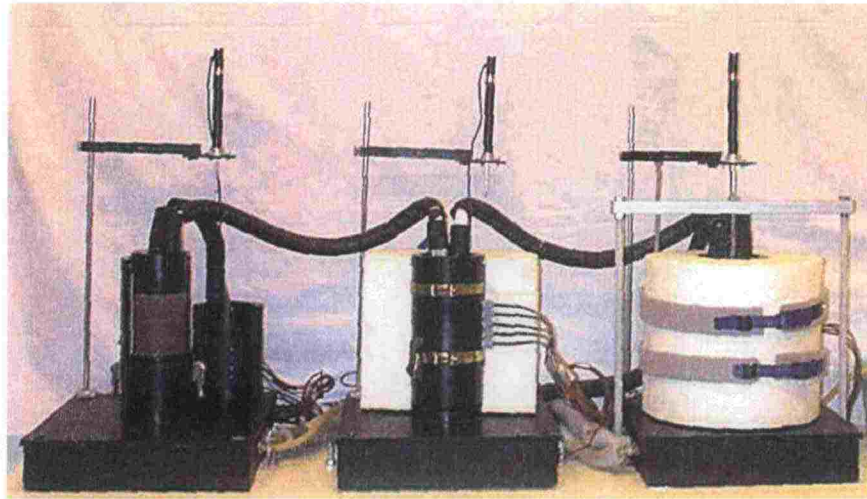


Figure 4: Frost heave testing. Equipment

### Full-scale testing of RM-structures

The RM-structures always have to be tested in full scale (in field tests) to ascertain the feasibility of the materials, structures, work methods and quality assurance methods. It is recommended to equip the test structures with versatile electronic geo-instruments (that measure e.g. moisture, temperature, displacements, strain) and to carry out the follow-up studies according to an adequate and scheduled program. After construction, the follow-up studies should be carried out for at least 2 to 3 years in order to obtain reliable feedback information about the properties and behaviour of the new materials and structures.

In co-operation with the Finnish National Road Administration (FinnRa) and other interested parties Viatek Ltd/SGT has studied and developed over 40 different recycled structures in the 1990's. Most of the structures have been made for FinnRa. Followed there are some examples on the test structures:

#### a. Renovating a gravel road by using peat-ashes

Figure 5a illustrates a gravel road before renovation. In Figure 5b, there is the same road immediately (one month) after construction. In Figure 5c, the structure was opened seven years after the construction. Based on the results it can be concluded that;

- The typical problems of a gravel road have been solved with help of an ash structure;
- The bearing capacity of the test section has remained relatively high;
- Seven years after the construction, the compression strength of the ash structure was as high as one month after the construction (i.e. 1,2 MPa).

After renovation, the frost heaves have been significantly lower, max. 50 mm, than before, i.e. more than 200 mm.



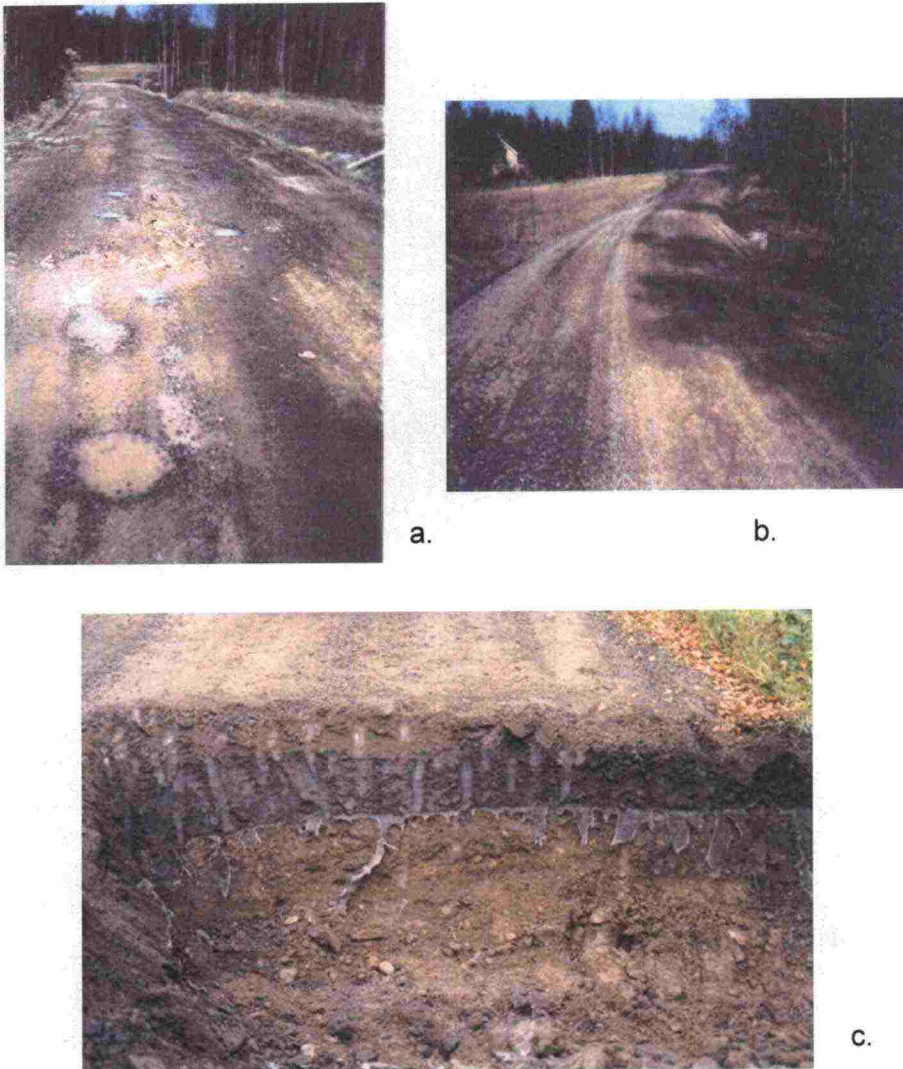


Figure 5: A gravel road a) before renovation using peat ash, b) immediately after renovation, and c) 7 years after renovation

#### b. Stabilization using blast furnace sand

Figure 6 shows an opened part of a gravel road which has been stabilized using blast furnace sand. The following conclusions are based on the results:

- The stabilization is a technically feasible way to solve problems of gravel roads;
- Seven years after the stabilization, the strength of the structure was significantly higher than 1 month after the stabilization;
- Frost heaves have been significantly lower than before stabilization.



Figure 6: Stabilized structure; blast furnace sand

c. Stabilization using gypsum and lime

In Figure 7 there is a gravel road stabilized using a mix of gypsum and lime. The following conclusions are based on the results:

- The structure has become rigid and slablike;
- The structure has maintained its improved properties 7 years after construction;
- Frost heaves have been lower than before stabilization.



Figure 7: Stabilized structure; a mix of gypsum and lime



#### d. Fiber-ash structure

The fiber-ash structure was used to renovate a village road with pavement. One of the objectives was to achieve the improvements with as thin structure layers as possible. The total thickness of the construction was 45 cm and the thickness of the fiber-ash layer only 20 cm. The fiber-ash layer was designed to act as a base course and insulating layer of the structure.

Figure 8 illustrates the fiber-ash road structures and construction. Following conclusions are based on the results:

- The construction process (Figure 8b) using fiber-ash was easy;
- The reference section (Figure 8a: conventional crushed stone structure) was already badly damaged two years after the construction;
- Two years after the construction, the fiber-ash section was even and without any damage (Figure 8c);
- The bearing capacity of the fiber-ash section is two times higher than the bearing capacity of the reference section;
- Frost heave of the fiber-ash section has been only around 40 mm, but the frost heave of the reference section has been up to 120 mm.



8a.





8b.




8c

Figure 8: Village road a) conventional reference section two years after construction, b) construction, c) fiber-ash section two years after construction

### The economic viability of recycled structures

In connection with full-scale testing there have been studies on the economic viability of different RM-structures. Figure 9 describes the long-term (i.e. 15 years) costs of different RM-structures in comparison with other more conventional structures. The costs are based on the assumptions that the purchase price of the industrial wastes for the RM-structure is zero (0) despite the fact that the industry will benefit from the reduction of waste handling costs when recycling. The costs included in the cost assessments are those of transportation, construction and maintenance. The comparison shows that for a certain purpose the RM-structures might be even 50 per cent less expensive than the conventional ones.

Figure 9: Comparison of the long-term costs (in FIM) of 100 meters of different road structures

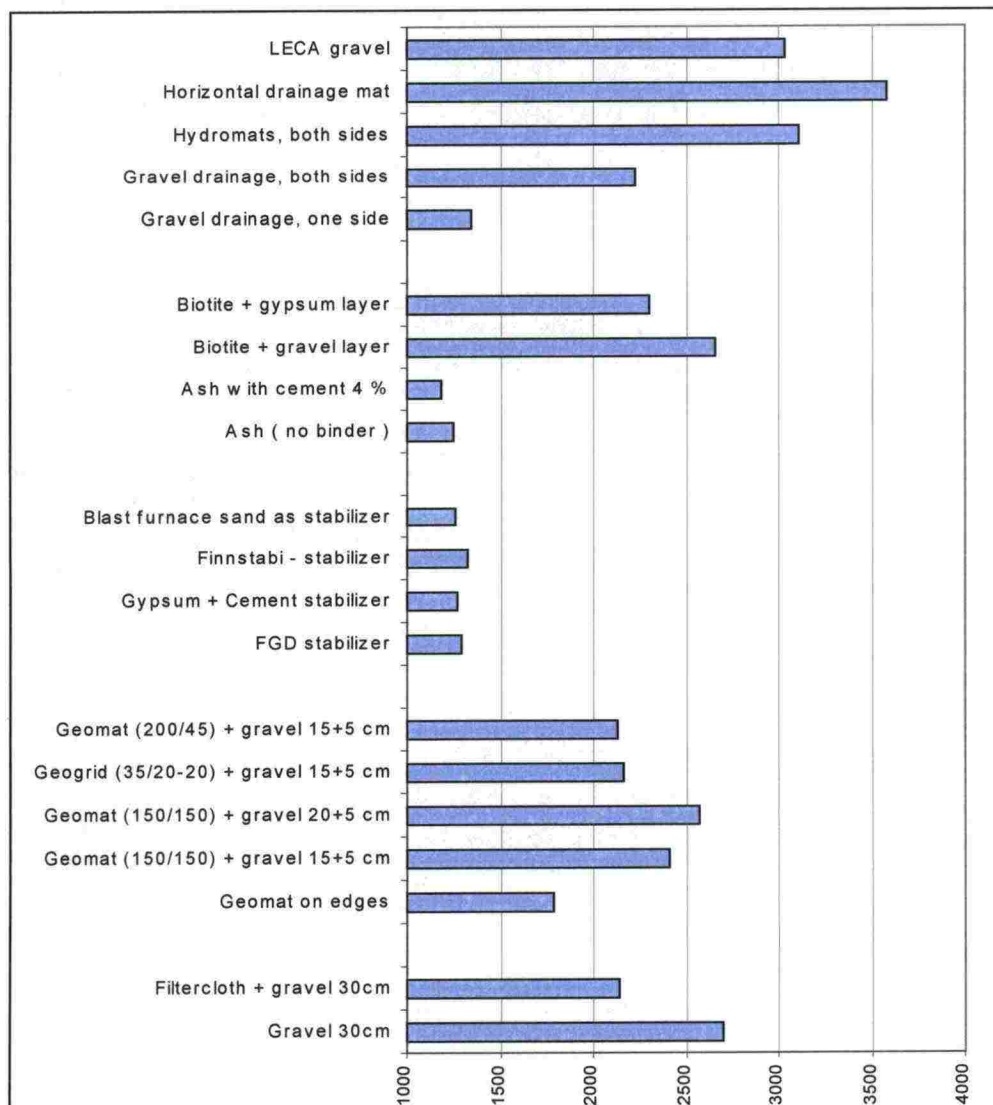

## Conclusions

The basic problems of the low-volume roads are frost heave and weak bearing capacity that usually cause really bad traffic conditions in the spring. Traditional renovation methods are expensive and require significant amounts of natural stone materials from non-renewable sources. Therefore, the development of new, environmentally friendly and cost-effective renovation methods is necessary, even inevitable. Here we have succeeded to develop several viable solutions:

- Technically and economically excellent results can be obtained by stabilizing old structures with help of binders based on different types of industrial waste or by-products. So far the best by-product binders are different slags, gypsum and ashes;
- Another competitive group of solutions is based on the recycling of industrial by-products as new materials for base courses of low-volume road structures. Often a relatively good frost insulation can be obtained with the so-called RM-structures. Different ashes, refined slags (sands) and mixes of fiber sludge with gypsum are found to be the best recycled materials for RM-structures, so far;
- Industrial by-products are the basis for many excellent solutions but extensive laboratory tests and full-scale tests are needed to ascertain the adequate quality of the final material mixes;
- Also, the work methods and equipment have to be adapted to the use of new recycled materials in construction. Otherwise, the final outcome might not be as successful as required. The storage and handling of recycled materials especially call for further development;
- Quality control is of great significance. Special control is needed with respect to the water content and compacting of the recycled materials;
- Groundwater contamination is always a concern when using waste materials in roadways. For example, in the case of gypsum  $H_2SO_4$  formation could be of concern. However, no harmful effects on the groundwater quality have been observed during or after the construction;
- The RM-structures are environmentally friendly. In comparison with conventional methods it is possible to cut down the consumption of non-renewable natural resources (gravel etc.) from 30 % to 80 %;
- The RM-structures are very cost-effective. In comparison with conventional methods it is possible to save up to 50 %.

## References

- Lahtinen, P., Fagerhed, J.A., Ronkainen, M.: *Papersludge in road construction*. A paper for the Proceedings of the 4<sup>th</sup> International Symposium on Environmental Geotechnology and Global Sustainable Development in Boston, U.S.A., August 9-13, 1998.
- Lahtinen, P., Jyrävä, H., Suni, H.: *New methods for the renovation of gravel roads*. A paper for IRF Regional Conference / European Transport and Roads, in Lahti, May 24-26, 1999.
- Lahtinen, P., Suni, H.: *New methods for the renovation of the gravel road network*. Finncontact 1999.
- Lahtinen, P.: *Use of industrial waste in road construction*. Finnish Highway & Traffic Engineering 2000, p. 21-25.



## MOLYBDENUM TRANSPORT IN COAL FLY ASH SOIL CONSTRUCTIONS

Pentti Lahtinen

Viatek Ltd/SGT, Luopioinen, Finland

Fax +358 3 5361584, e-mail [pentti.lahtinen@viatek.fi](mailto:pentti.lahtinen@viatek.fi) (correspondence)

Jukka Palko

Envitop Oy, Oulu, Finland

Fax +358 8 372586, e-mail [jukka.palko@envitop.com](mailto:jukka.palko@envitop.com)

Tuomo Karvonen

Helsinki University of Technology, Finland

Fax +358 9 4513827, e-mail [tuomo.karvonen@hut.fi](mailto:tuomo.karvonen@hut.fi)

**ABSTRACT:** There are remarkable possibilities to economically use a major part of coal fly ashes in soil construction applications. This, however, requires that the environmental effects of fly ashes are known and can be controlled. This paper discusses a research on the transport of molybdenum from ash structures to the environment in the long term. The research has involved both laboratory investigations on fly ash samples and tests on samples from full-scale constructions. The results have shown for example that; the amount of leachable molybdenum relative to the total content of molybdenum varies remarkably between the coal ashes from different sources; clay absorbs molybdenum more effectively than sandy moraine; with declining pH values the subsoil layer beneath the ash layer prevents further transport of molybdenum; the studies conducted at the 20 years old construction support the results of laboratory investigations. On the basis of the investigations a transport model was constructed for clay and moraine soils. The model can be used to calculate the transport of molybdenum in the soil and ground water beneath the coal ash layer during the next 100 years. The calculations indicate that the transport of molybdenum is insignificant and not beyond half metre under the fly ash structure.

**Keywords:** molybdenum, coal fly ash, environment, soil construction, transport model

## 1. INTRODUCTION

The Finnish research project discussed in this paper was about the transport of molybdenum from ash structures to the environment in the long term. The research was conducted on coal fly ash from three power plants (Fortum Power, Helsinki Energy and Pohjolan Voima) that incinerate coal from different sources. Coal fly ash was assembled during the production period in 1998, and more than 15 different samples were taken for the laboratory studies.

In addition to the laboratory studies two different full-scale constructions with fly ash from Helsinki Energy were studied during the research project. Soil samples were taken from a 20 years old test construction in Maunula. Soil samples and water samples from lysimetres and ground water pipes were taken from a 2 years old site in Knuters, Sipoo.

The concentration, availability and leaching of molybdenum were determined from the 15 fly ash samples. On the basis of the results it was possible to determine the differently behaving fractions of the ashes. Also the buffer and retention capacity of certain soil types (clay and sandy moraine) were determined with laboratory tests.

The results were used to construct a dynamic transport model for molybdenum. The model was tested with help of data from the full-scale constructions. On the basis of the model the first molybdenum nomograms were made to provide a tool for the environmental assessment of fly ashes.

## 2. LABORATORY INVESTIGATIONS

### 2.1. Concentration and availability of molybdenum

The molybdenum occurs in following different fractions in the fly ashes:

1. a permanently adsorbed part;
2. a fast released part;
3. a slowly released part.

In order to specify the relation and variation of the different fractions the laboratory investigations were constructed to determine the total content and availability (CEN prEN 12457) of molybdenum in the fly ash samples, and the long-term leaching (NEN 7343) of molybdenum from the strengthened but not stabilised fly ashes.

The results of the CEN and long-term leaching tests are compiled in Table 1 below.

Table 1: Results of laboratory investigations on Mo content of coal fly ashes (FA) from three power plants in Finland. CEN = total availability by CEN prEN 12457, NEN = leaching by NEN 7343.

FA 1	mg (Mo)/kg		FA 2	mg (Mo)/kg		FA 3	mg (Mo)/kg	
	CEN	NEN		CEN	NEN		CEN	NEN
4-99	4.1	4.12	4-99 I	7.1	7.51	5-99	3	0.83
5-99 I	4.3	3.44	4-99 II	7	4.9	10-99	5.7	1.08
5-99 II	3.9	4.12	4-99 III	4.7	4.93	11-99 I	5.3	1.18
10-99 I	2.8	-	10-99	5.1	-	11-99 II	6.6	-
10-99 II	3.8	4.34	11-99 I	4.7	5.44			
10-99 III	4.4	6.56	11-99 II	3.5	-			
11-99	4.2	-	11-99 III	3.4	-			
			12-99	3.1	3.06			

The results have indicated that the available (leaching) fraction of molybdenum in the different ashes varies remarkably, between 30 and 70 % of the total content. The correlation between the availability (CEN) and the long-term leaching (NEN) of molybdenum is given in Figure 1. These results show that there is not a clear correlation of these tests. Part of the ashes seems to have values of same level in both of the tests (FA1 and FA2) but part of the ashes shows long-term leaching that is only a fraction of the total availability (FA3). One of the reasons might be in the different strengthening and setting behaviour of the ashes.

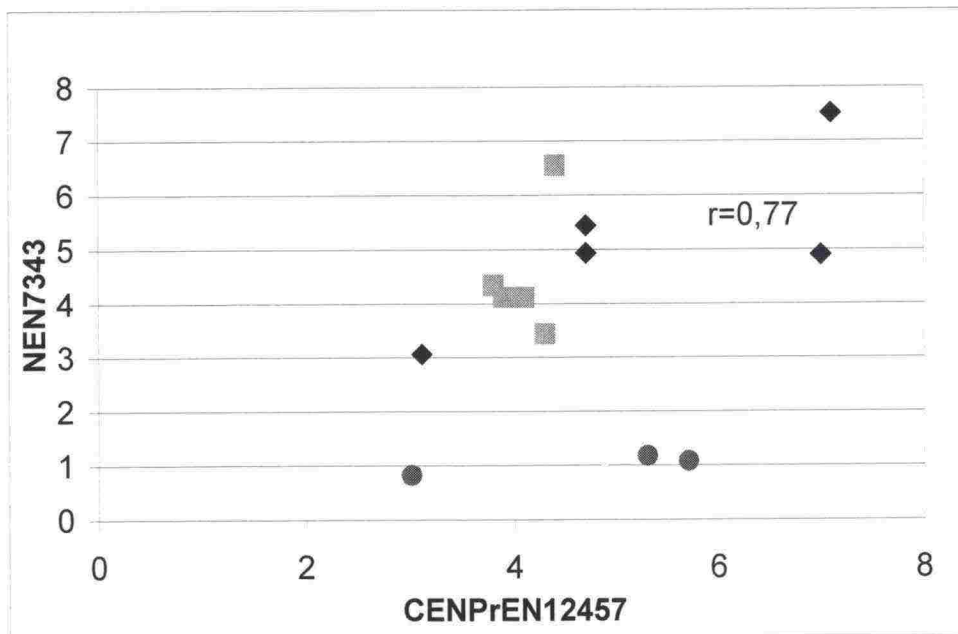


Figure 1: Correlation of results from CEN- and NEN-tests (compare Table 1)




## 2.2. Determination of the retention and the buffer capacity of soil


The retention capacity of the soil for molybdenum was investigated with two different soil types, with clay and sandy moraine. In a concentration of 5, 10 and 20 mg /kg molybdenum was added in the soil samples. The retention of molybdenum was studied at three different pH values (pH 6, 8 and 10). Figure 2 gives the results.

The results in Figure 2 show that the retention capacity of clay was high at pH 6 and for all Mo concentrations. At pH 8 the retention was a little more than 20%. Sandy moraine did not have as good a retention capacity. In case the Mo concentration is small ( $\leq 5$  mg/kg) all of the molybdenum is retained but with higher concentrations the retaining fraction is smaller. Neither of the soil types had retention capacity at  $\text{pH} \geq 10$ . The laboratory tests certified by the tests on field samples have shown that the retention capacity for molybdenum will remarkably increase with a declining pH value.

The seepage water from the ash construction was used to determine the buffer capacity of clay and sand moraine. In Figure 3 this can be seen by the pH value as a function of L/S (liquid/solid).

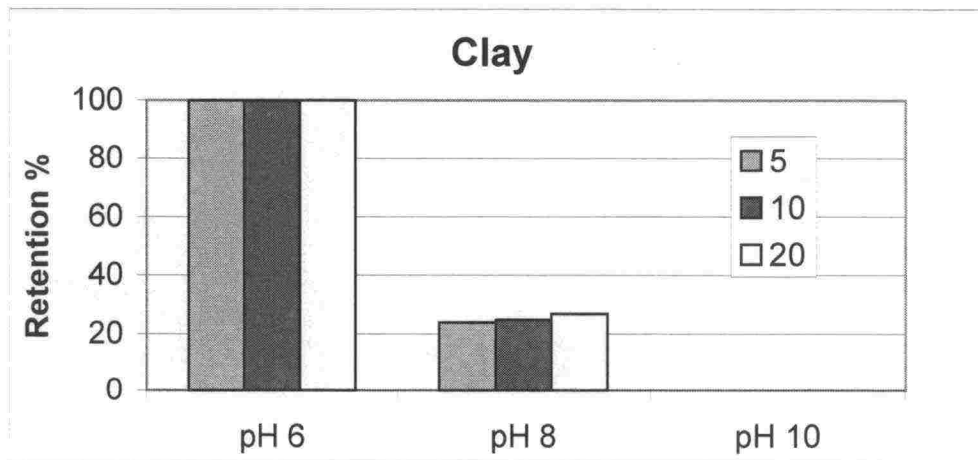

a.

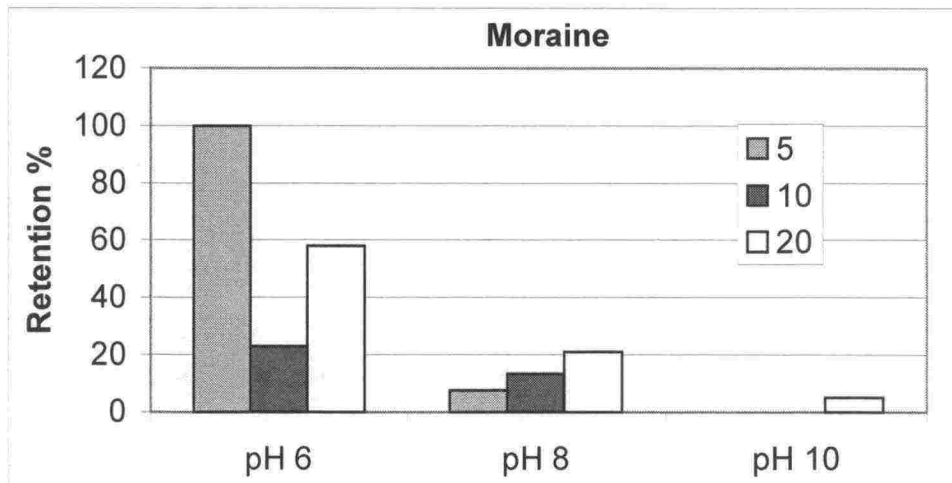

b.

Figure 2: Retention of Mo by clay (a) and sand moraine (b).

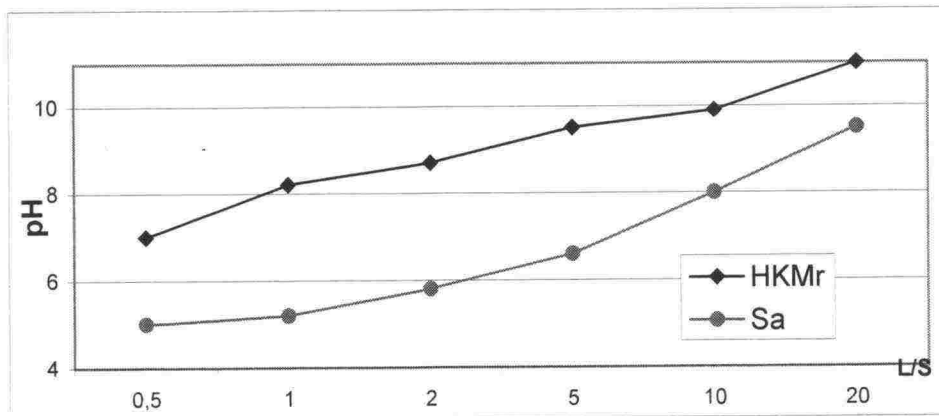


Figure 3: The buffer capacity of clay and sand moraine for molybdenum of water extracts from fly ash layer. Correlation of pH and L/S ( a mass of L=liquid percolating through the mass of S=solid).

### 3. THE DYNAMIC TRANSPORT MODEL FOR MOLYBDENUM

#### 3.1. Description and construction of the model

A dynamic transport model is used to calculate the amount of released molybdenum from an ash structure and the transport of the released molybdenum in the soil beneath the ash layer. Additionally it is possible to assess the increase of molybdenum content in the ground water zone. The parameters for the transport model are the data from the column (NEN-) test, i.e. the cumulative leaching of molybdenum as a function of L/S. The mathematical formula of the model was defined by precision of the leaching calculated by the model with the results of column tests. The transport model combines hydrological and chemical sub-models and uses the methodology of differential calculus to calculate the transport of molybdenum and its adsorption or desorption in a layer structure (van Genuchten and Gray 1978, Moldrup et al. 1994a, 1994 b).

#### 3.2. Testing of the model

The transport model has been tested with help of a 20 years old, gravel covered ash road. The thickness of the ash layer is 0,5 metres and the soil beneath is clay. The model was tested with help of the column test results of the 15 new ash samples because no leaching tests (NEN) were made on the ash for the full-scale construction 20 years ago.

Soil samples were taken from several depths (each 10 cm) of the full-scale structure. The total content and availability (CEN) of molybdenum were determined from the samples. A graph was drawn with the measured and calculated Mo content relative to the depth. These results have indicated that the calculated values match with the values determined in the laboratory. These also show that the model functions and that the chosen parameters are the right ones.

### 3.3. Nomograms based on the model

With help of pre-drawn nomograms the dynamic transport model is applicable for different ash structures and soil conditions. Figure 4 gives an example of a nomogram to determine the transport of molybdenum when the subsoil is clay and the yearly rain fall 200 mm. The nomogram gives the maximum molybdenum concentration beneath the ash layer in the long term with a given leaching (column test) of the ash material and thickness of the ash layer.

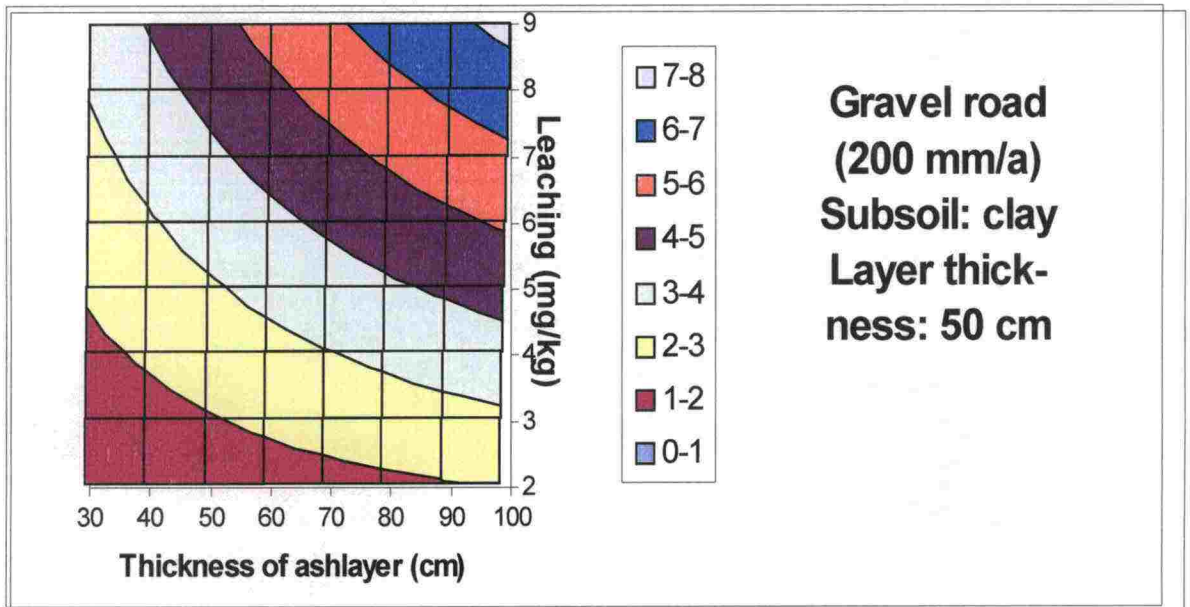


Figure 4: An example of a nomogram for a case specified as follows: a gravel road structure where there is 50 cm clay under the fly ash layer. The concentration of molybdenum in the clay layer is given as a function of the cumulative leaching of Mo and the thickness of the fly ash layer. Yearly rainfall is assessed to be around 200 mm.



## 4. CONCLUSIONS

The research project discussed in this paper has been concentrating on the transport of molybdenum in the environment of ash structures. Following aspects can be concluded on the basis of the results, for example

1. The total content and availability (leaching fraction) of molybdenum as well as their relation vary remarkably between the fly ashes from different sources. Therefore it is not possible to determine the leaching of molybdenum on the basis of the total content. Therefore, the quality control of fly ashes should include the determination of the leaching fraction e.g. with a CEN-test.
2. The pH value quickly decreases in the soil layers beneath a fly ash layer. Therefore the leaching fraction of molybdenum accumulates in the soil immediately underneath the fly ash layer which has been shown with field tests and the mathematical transport model.
3. The dynamic transport model constructed in this project has been shown to function properly with the chosen parameters. The model can be used to calculate the long-term transport of molybdenum in the soil and ground water. The values of the model were shown to correlate well with the values determined from samples taken at a 20 years old construction site. Similar dynamic transport models can be constructed to assess the transport of other substances.

The dynamic transport model has also been used to calculate the molybdenum concentration in the ground water in the long term. These results indicate that there is no environmental risk in regard to the molybdenum from the given ash constructions. Similar results have been obtained from the long-term monitoring at full-scale test constructions.

## REFERENCES:

- Moldrup, P., Poulsen, T.G., Rolston, D.E., Yamaguchi, T., and Hansen, J.A.A. (1994a): Integrated flux model for unsteady transport of trace organic chemicals in soils. *Soil Sci.* 157: 137-152
- Moldrup, P., Yamaguchi, T., Rolston, D.E., Vestergaard, K. and Hansen, J.A.A. (1994b): Removing numerically induced dispersion from finite difference models for solute and water transport in unsaturated soils. *Soil Sci.* 157: 153-161
- van Genuchten, M.Th., and Gray, W.G. (1978): Analysis of some dispersion corrected numerical schemes for solution of the transport equation. *Int. J. Num, Methods Eng.* 12: 387-404

ISSN 1457-9871  
ISBN 951-726-826-2  
TIEH 3200716E